


# HANSER

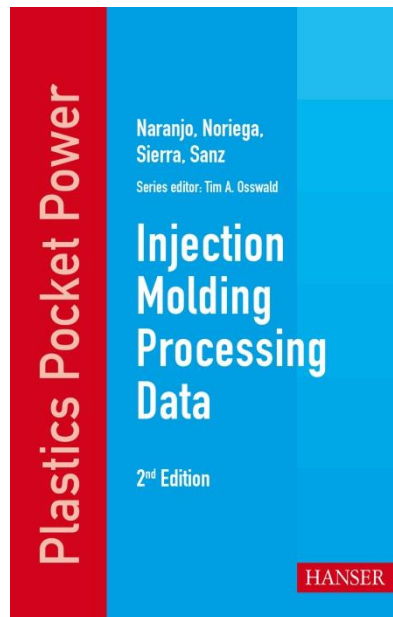

## Sample Pages

### Injection Molding, Processing Data

Alberto Naranjo C., Maria del Pilar Noriega E., Juan Diego Sierra M. & Juan Rodrigo Sanz

ISBN (Book): 978-1-56990-666-8

ISBN (E-Book): 978-1-56990-667-5

**For further information and order see**

[www.hanserpublications.com](http://www.hanserpublications.com) (in the Americas)

[www.hanser-fachbuch.de](http://www.hanser-fachbuch.de) (outside the Americas)

© Carl Hanser Verlag, München

# Table of Contents

<b>1</b>	<b>Introduction</b> .....	5
<b>2</b>	<b>Injection Technology</b> .....	6
2.1	The Injection Molding Cycle .....	7
<b>3</b>	<b>Useful Equations and Theory</b> .....	14
<b>4</b>	<b>Examples</b> .....	24
4.1	Runner System Balance .....	24
4.2	Shrinkage Prediction .....	25
4.3	Cooling Time Prediction .....	27
4.4	Effect of Process Parameters on Shrinkage .....	28
4.5	Theoretical Energy Consumption in an Injection Molding Process with PS .....	29
4.6	Processing Conditions of PA6 Parts and Theoretical Power-Cooling Requirement .....	30
4.7	Theoretical Water Flow Requirement for a Mold for PA6 Parts .....	34
4.8	Determining Viscosity Constants from the Curve	35
<b>5</b>	<b>Polymer Data (for Standard Materials without Fillers or Modifiers)</b> .....	37
5.1	Polyolefins .....	37
5.1.1	Low Density Polyethylene (LDPE) .....	37
5.1.2	High Density Polyethylene (HDPE) .....	41
5.1.3	Polypropylene Homopolymer (PP) .....	45


---

5.2	Styrenics	49
5.2.1	Polystyrene Homopolymer (PS)	49
5.2.2	High Impact Polystyrene (HIPS)	53
5.2.3	Styrene/Acrylonitrile Copolymer (SAN)	57
5.2.4	Acrylonitrile/Butadiene/Styrene Copolymer (ABS)	61
5.3	Polycondensates	65
5.3.1	Polyamide 6 (PA6)	65
5.3.2	Polyamide 66 (PA66)	69
5.3.3	Polyethylene Terephthalate (PET)	73
5.3.4	Polybutylene Terephthalate (PBT)	77
5.3.5	Polycarbonate (PC)	81
5.3.6	Polyphenylene Ether Modified (m-PPE)	85
5.3.7	Polyether Etherketone (PEEK)	89
5.3.8	Polyarylsulfone (PSU)	93
5.4	Vinyls	97
5.4.1	Polyvinylchloride (PVC) Rigid	97
5.4.2	Polyvinylchloride (PVC) Flexible	101
5.5	Others	105
5.5.1	Polylactic Acid (PLA)	105
5.5.2	Polymethylmethacrylate (PMMA)	109
5.5.3	Polyacetal (POM)	113
<b>6</b>	<b>Appendix</b>	<b>117</b>
<b>7</b>	<b>Definitions</b>	<b>120</b>
<b>8</b>	<b>Further Reading</b>	<b>123</b>

---

## 2 Injection Technology

A modern injection molding machine with its most important elements is shown in Figure 2.1. The components of the injection molding machine are the plasticating unit, clamping unit, control unit, and the mold.

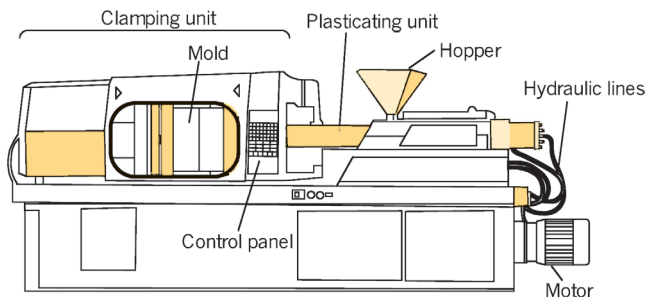

**Figure 2.1** Schematic of an injection molding machine. See Figure 2.7 for a more detailed representation of the machine

Today, injection molding machines are classified by the following international convention

Manufacturer type  $T/P$

where  $T$  is the clamping force in metric tons and  $P$  is defined as

$$P = \frac{v_{\max} p_{\max}}{1000}$$

where  $v_{\max}$  is the maximum shot size in  $\text{cm}^3$  and  $p_{\max}$  is the maximum injection pressure in bar. The clamping force  $T$

can be as low as 1 metric ton for small machines, and as high as 11,000 tons.

There is another classification regarding specific energy consumption (kWh/kg), the Euromap 60.1. There are 10 efficiency classes: Class 1 ( $> 1.5$  kWh/kg) to Class 10 ( $\leq 0.25$  kWh/kg). For small machines (screw  $\leq 25$  mm) the class definition is different.

## 2.1 The Injection Molding Cycle

The sequence of events during the injection molding of a plastic part, as shown in Figure 2.2, is called the injection molding cycle. The cycle begins when the mold closes, followed by the injection of the polymer into the mold cavity. Once the cavity is filled, a holding pressure is maintained to compensate for material shrinkage. In the next step, the screw turns, feeding the next shot to the front of the screw. This causes the screw to retract as the next shot is prepared. Once the part is sufficiently cool, the mold opens and the part is ejected. Figure 2.3 presents the sequence of events during the injection molding cycle. The figure shows that the cycle time is dominated by the cooling of the part inside the mold cavity. However, in some cases the plasticating time can be longer than the cooling time, e.g., when the mold cavity number is high for the plasticating unit capacity; the plasticating time is also longer than the cooling time when the parts have thin walls. The total cycle time can be calculated using

$$t_{\text{cycle}} = t_{\text{closing}} + t_{\text{injectionunitforward}} + t_{\text{injection}} + t_{\text{cooling}} + t_{\text{ejection}}$$

### 3 Useful Equations and Theory

#### ESTIMATING COOLING DURING INJECTION MOLDING

The cooling time for a plate-like part of thickness  $h$  can be estimated using

$$t_{cooling} = \frac{h^2}{\pi^2 \cdot \alpha} \ln \left( \frac{8}{\pi^2} \frac{T_M - T_W}{T_D - T_W} \right)$$

and for a cylindrical geometry of diameter  $D$  using

$$t_{cooling} = \frac{D^2}{23.14\alpha} \ln \left( 0.692 \frac{T_M - T_W}{T_D - T_W} \right)$$

In the above equations  $\alpha$  represents effective thermal diffusivity,  $T_M$  represents the average melt temperature,  $T_W$  the average mold temperature, and  $T_D$  the average part temperature at ejection.

### EQUATIONS FOR PRESSURE FLOW THROUGH A SLIT

Pressure flow through a slit, such as shown in Figure 3.1, is commonly encountered in flows inside injection molds. The Newtonian flow field is described using

$$v_z(y) = \left( \frac{h^2 \Delta p}{8\mu L} \right) \left[ 1 - \left( \frac{2y}{h} \right)^2 \right]$$


$$Q = \frac{W h^3 \Delta p}{12 \mu L}$$

When using the power law model equation the flow field is described by

$$v_z(y) = \left( \frac{h}{2(s+1)} \right) \left( \frac{h \Delta p}{2mL} \right)^s \left[ 1 - \left( \frac{2y}{h} \right)^{s+1} \right]$$

$$Q = \frac{W h^2}{2(s+2)} \left( \frac{h \Delta p}{2mL} \right)^s$$

where  $s = 1/n$  and  $v_z(y)$  is the velocity profile across the gap and  $Q$  the total volumetric flow rate through a slit of width  $W$ .

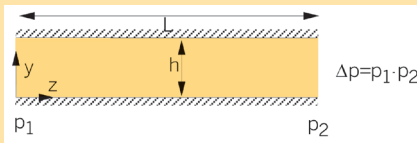

**Figure 3.1** Schematic diagram of a pressure flow through a slit



## 5 Polymer Data (for Standard Materials without Fillers or Modifiers)

### 5.1 Polyolefins

#### 5.1.1 Low Density Polyethylene (LDPE)


Basic technical data

- ▶ Density: 0.910 to 0.926 g/cm<sup>3</sup>
- ▶ Melting point: 105 to 115 °C
- ▶ Glass transition temperature: -133 to -120 °C

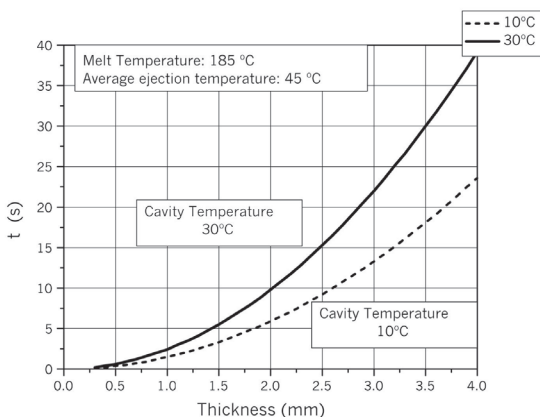


**Figure 5.1** Mold cooling with LDPE




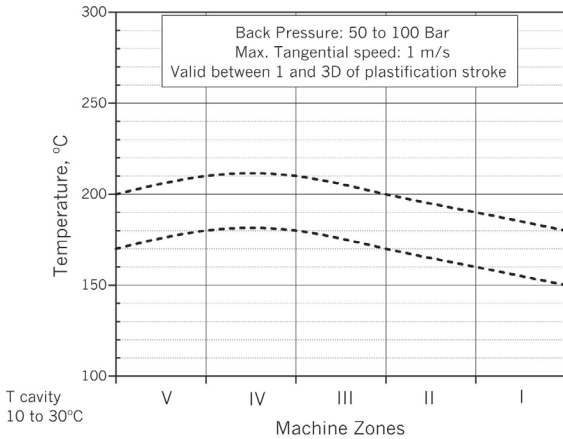


**Figure 5.2** Recommended temperature profiles for processing LDPE

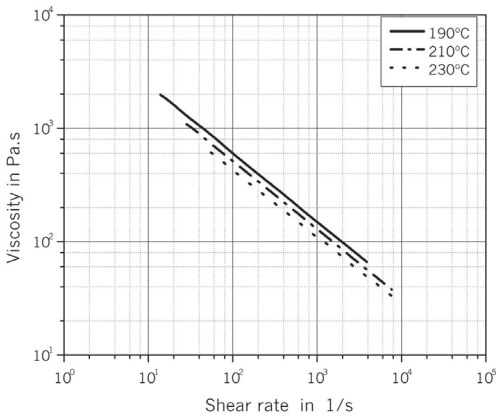

**Figure 5.3** Viscosity vs shear rate of LDPE

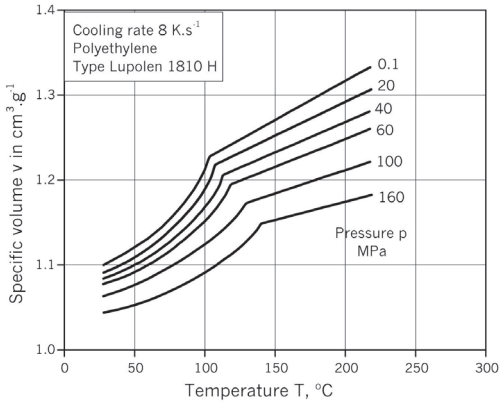

**Figure 5.4** PVT diagram for LDPE

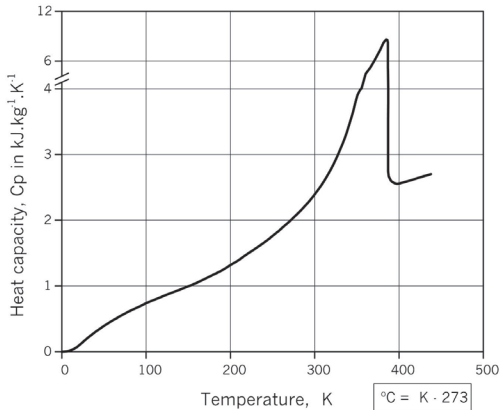

**Figure 5.5** Heat capacity vs temperature of LDPE