


# HANSER

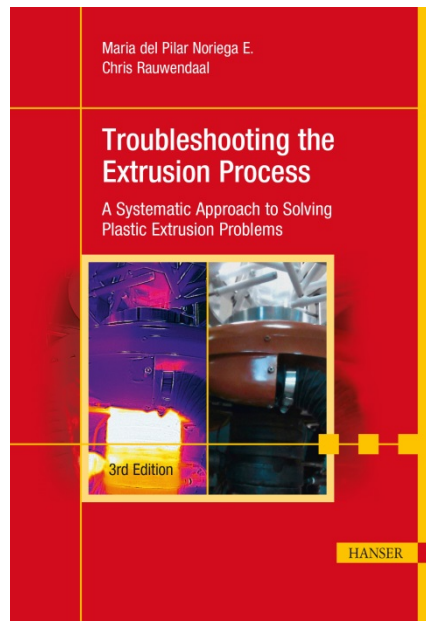

## Sample Pages

# Troubleshooting the Extrusion Process

Maria del Pilar Noriega E. and Chris Rauwendaal

ISBN (Book): 978-1-56990-775-7

ISBN (E-Book): 978-1-56990-776-4

**For further information and order see**

[www.hanserpublications.com](http://www.hanserpublications.com) (in the Americas)

[www.hanser-fachbuch.de](http://www.hanser-fachbuch.de) (outside the Americas)

© Carl Hanser Verlag, München

# Preface

One of the greatest challenges in actual extrusion operations is efficient and rapid problem-solving. Extrusion problems often result in downtime and/or out-of-spec product, and this can be very costly. However, because of the nature of the extrusion process, it is often quite difficult to determine the cause of the problem and find the proper solution, particularly if it must be done quickly. Despite the industrial importance of extrusion troubleshooting, no book currently deals exclusively with this topic. This book is an attempt to rectify this situation.

Both authors have worked in extrusion for many years and have been involved in numerous troubleshooting projects. Although it is impossible to discuss all possible extrusion problems, it is possible to discuss the main categories and to develop a systematic and methodical approach to solving extrusion problems. In this book, the authors frequently use flow charts and fishbone charts to allow systematic troubleshooting.

The authors added a substantial amount of new material to this third edition, including:

- Chapter 1: new section on collection and interpretation of extrusion process data
- Chapter 2: data acquisition systems section substantially expanded and updated with cloud-based DAS and systems that can automatically detect machine problems; new sections on rotational rheometry and the smartphone
- Chapter 3: new sections covering how screw design can affect extruder performance and melt temperature variation; additionally, barrel temperature profiles for many polymers from LDPE to PEEK
- Chapter 4: ten new case studies
- Appendix 3: new section with information on barrel temperature optimization for PP and HDPE for a 2.5-inch (63.5 mm) extruder and a description of recent research on automatic optimization of extruder barrel temperatures conducted at the department of Kunststofftechnik Paderborn, University of Paderborn, Germany by Verena Resonnek

- Appendix 4 (new): process signal analysis using Fast Fourier Transform

The authors welcome feedback from readers, along with additional material on extrusion troubleshooting. This will allow more information to be incorporated into future editions of this book.

# Contents

<b>Acknowledgments</b> .....	<b>V</b>
<b>Preface</b> .....	<b>VII</b>
<b>List of Acronyms</b> .....	<b>IX</b>
<b>1 Requirements for Efficient Troubleshooting</b> .....	<b>1</b>
1.1 Instrumentation .....	1
1.2 Understanding the Extrusion Process .....	2
1.3 Collection and Analysis of Historical Data (Time Line) .....	4
1.4 Team Building .....	5
1.5 Condition of the Equipment .....	6
1.6 Information about the Feed Stock .....	6
1.7 Problem-Solving Techniques .....	8
1.8 Collection and Interpretation of Extrusion Process Data .....	9
1.8.1 Introduction .....	9
1.8.2 Vital Signs of the Extrusion Process .....	9
1.8.2.1 Melt Pressure .....	10
1.8.2.2 Melt Temperature .....	16
1.8.2.3 Training .....	25
1.8.3 Conclusions .....	25
<b>2 Tools for Troubleshooting</b> .....	<b>27</b>
2.1 Temperature Measurement Devices .....	27
2.2 Data Acquisition Systems .....	28
2.2.1 Portable Data Collectors/Machine Analyzers .....	29
2.2.2 Fixed-Station Data Acquisition Systems .....	30
2.3 Light Microscopy .....	33

2.4	Thermochromic Materials .....	34
2.5	Thermal Analysis, IR Spectroscopy, and Rheometry .....	35
2.5.1	Differential Thermal Analysis and Differential Scanning Calorimetry .....	35
2.5.2	Thermogravimetric Analysis .....	37
2.5.3	Fourier Transform Infrared Spectroscopy .....	38
2.5.4	Thermomechanical Analysis .....	39
2.5.5	Torque Rheometry .....	40
2.5.6	High Pressure Capillary Rheometry .....	41
2.5.7	Rotational Rheometry .....	43
2.5.8	Other Thermal Characterization Techniques .....	46
2.6	Miscellaneous Tools .....	46
2.6.1	Infrared Thermography .....	47
2.6.2	The Smartphone .....	48
2.6.3	Power Measurements .....	49
<b>3</b>	<b>Systematic Troubleshooting .....</b>	<b>51</b>
3.1	Upsets versus Development Problems .....	51
3.2	Machine-Related Problems .....	51
3.2.1	The Drive System .....	52
3.2.2	The Feed System .....	53
3.2.3	The Heating and Cooling System .....	53
3.2.4	How Screw Design Can Affect Extruder Performance .....	54
3.2.5	Wear Problems .....	65
3.2.5.1	Wear Mechanisms .....	66
3.2.5.2	Test Methods for Wear .....	67
3.2.5.3	Causes of Wear .....	72
3.2.5.4	Solutions to Wear Problems .....	77
3.2.5.5	Rebuilding Worn Screws and Barrels .....	83
3.2.6	Screw Binding .....	87
3.2.6.1	Extrusion of Fluoropolymers .....	88
3.2.6.2	The Mechanics of Screw Binding .....	88
3.2.6.3	Changes in Clearance Due to Temperature Differences .....	88
3.2.6.4	Analysis of Temperature Distribution in Extruder Screws .....	91
3.2.6.5	Change in Clearance Due to Compressive Load .....	92
3.2.6.6	Results from Analysis .....	92
3.3	Polymer Degradation .....	93
3.3.1	Types of Degradation .....	93
3.3.1.1	Thermal Degradation .....	94

3.3.1.2	Mechanical Degradation .....	94
3.3.1.3	Chemical Degradation .....	96
3.3.2	Degradation in Extrusion .....	97
3.3.2.1	Residence Time Distribution .....	97
3.3.2.2	Temperature Distribution Simple Calculations .....	101
3.3.2.3	Temperature Distribution Numerical Calculations ....	107
3.3.2.4	Reducing Degradation .....	114
3.4	Extrusion Instabilities .....	115
3.4.1	Frequency of Instability .....	116
3.4.1.1	High-Frequency Instabilities .....	117
3.4.1.2	Screw Frequency Instabilities .....	120
3.4.1.3	Low-Frequency Instabilities .....	122
3.4.1.4	Very Slow Fluctuations .....	123
3.4.1.5	Random Fluctuations .....	123
3.4.2	Functional Instabilities .....	124
3.4.2.1	Solids-Conveying Instabilities .....	125
3.4.2.2	Plasticating Instabilities .....	125
3.4.2.3	Melt-Conveying Instabilities .....	126
3.4.2.4	Devolatilization Instabilities .....	126
3.4.2.5	Mixing Related Instabilities .....	127
3.4.2.6	Distributive Mixing Sections .....	127
3.4.2.7	Dispersive Mixing Sections .....	132
3.4.2.8	Solving Mixing Problems .....	139
3.4.2.9	Melt Temperature Variation .....	140
3.4.3	Solving Extrusion Instabilities .....	149
3.5	Air Entrapment .....	151
3.6	Gel Problems .....	153
3.6.1	Measuring Gels .....	153
3.6.2	Gels Created in the Extrusion Process .....	154
3.6.3	Removing Gels Produced in Polymerization .....	155
3.7	Die-Flow Problems .....	156
3.7.1	Melt Fracture .....	156
3.7.2	Die-Lip Buildup (“Die Drool”) .....	158
3.7.3	V- or W-Patterns .....	159
3.7.4	Specks and Discoloration .....	160
3.7.5	Lines in Extruded Product .....	161
3.7.5.1	Weld Lines .....	162
3.7.6	Optical and Appearance Properties .....	163

<b>4 Case Studies</b> .....	<b>165</b>
4.1 Film Coextrusion – Degradation in the Middle Layer .....	165
4.1.1 Description of the Problem .....	165
4.1.2 Analysis of the Problem .....	166
4.1.3 Solution .....	167
4.2 Film Coextrusion with Interfacial Problems .....	169
4.2.1 Description of the Problem .....	169
4.2.2 Analysis of the Problem .....	169
4.2.3 Solution .....	170
4.3 Lines in the Extruded Film .....	170
4.3.1 Description of the Problem .....	170
4.3.2 Analysis of the Problem .....	171
4.3.3 Solution .....	172
4.4 Color Variation in Polypropylene Carpet Fiber .....	172
4.4.1 Description of the Problem .....	172
4.4.2 Analysis of the Problem .....	173
4.4.3 Solution .....	174
4.5 Plastic Film with Poor Transparency .....	175
4.5.1 Description of the Problem .....	175
4.5.2 Analysis of the Problem .....	176
4.5.3 Solution .....	177
4.6 Wear Problem in Film Extrusion .....	178
4.6.1 Description of the Problem .....	178
4.6.2 Solution .....	178
4.7 Multilayer Film – Several Appearance Problems .....	179
4.7.1 Description of the Problem .....	179
4.7.2 Analysis of the Problem .....	179
4.7.3 Solution .....	180
4.8 Dispersion Problem in a High-Density Polyethylene Bottle .....	181
4.8.1 Description of the Problem .....	181
4.8.2 Analysis of the Problem .....	181
4.8.3 Solution .....	182
4.9 Polymer Degradation .....	184
4.9.1 Description of the Problem .....	184
4.9.2 Analysis of the Problem .....	184
4.9.3 Solution .....	185
4.10 Heat-Sealing Problems in a Coextruded Film .....	187
4.10.1 Description of the Problem .....	187
4.10.2 Analysis of the Problem .....	188
4.10.3 Solution .....	189

4.11	Output Problem in a Blown Film Line	190
4.11.1	Description of the Problem	190
4.11.2	Analysis of the Problem	190
4.11.3	Solution	192
4.12	Masterbatch Selection	193
4.12.1	Description of the Problem	193
4.12.2	Analysis of the Problem	194
4.12.3	Solution	195
4.13	Pipe Extrusion Problem	196
4.13.1	Description of the Problem	196
4.13.2	Analysis of the Problem	196
4.13.3	Solution	197
4.14	Gel Formation in a Coextruded Film	199
4.14.1	Description of the Problem	199
4.14.2	Analysis of the Problem	199
4.14.3	Solution	200
4.15	Agglomerates and Grammage Variation in a PP Sheet	200
4.15.1	Description of the Problem	200
4.15.2	Analysis of the Problem	201
4.15.3	Solution	203
4.16	Insufficient Melting and Mixing in a Plasticating Unit	204
4.16.1	Description of the Problem	204
4.16.2	Analysis of the Problem	205
4.16.3	Solution	207
4.17	High Melt Temperature and Insufficient Output in Coextrusion	208
4.17.1	Description of the Problem	208
4.17.2	Analysis of the Problem	209
4.17.3	Solution	210
4.18	Deficient Solids Conveying and Dispersion	213
4.18.1	Description of the Problem	213
4.18.2	Analysis of the Problem	213
4.18.3	Solution	215
4.19	Instability of Formation at the Die	216
4.19.1	Description of the Problem	216
4.19.2	Analysis of the Problem	217
4.19.3	Solution	219
4.20	Intermittent Pumping in a Vented Extruder	222
4.20.1	Description of the Problem	222
4.20.2	Analysis of the Problem	223
4.20.3	Solution	225



4.21 Melt Fracture or Sharkskin in m-PE .....	227
4.21.1 Description of the Problem .....	227
4.21.2 Analysis of the Problem .....	227
4.21.3 Solution .....	228
4.22 Scale-up of LLDPE Single Screw Extruder .....	229
4.22.1 Description of the Problem .....	229
4.22.2 Analysis of the Problem .....	229
4.22.3 Solution .....	230
4.23 Non-homogeneous Melt in Blow Molding .....	232
4.23.1 Description of the Problem .....	232
4.23.2 Analysis of the Problem .....	232
4.23.3 Solution .....	232
4.24 High Melt Temperature in Sheet Extrusion .....	234
4.25 Gear Pump Speed Variation in Sheet Extrusion .....	238
4.26 Melt Temperature Variation in Tubing Extrusion .....	244
4.27 Black Specks in Tubing Extrusion .....	247
4.28 Mechanical Degradation in TPE Extrusion .....	252
4.29 Degradation in a Long Adapter .....	255
4.30 Shrink Voids in Rod Extrusion .....	258
4.31 Improper Preheating of Extruders .....	268
<b>Appendix 1: Systematic Problem Solving .....</b>	<b>285</b>
<b>Appendix 2: Machine Troubleshooting and Maintenance .....</b>	<b>287</b>
A2.1 Check the Oil .....	287
A2.2 Unusual Noises .....	288
A2.3 Vibration Monitoring .....	288
A2.4 Drive Motors and Belts .....	289
A2.5 Spare Parts .....	290
A2.6 Screw and Barrel .....	290
A2.7 Extruder Maintenance Checklist .....	291
<b>Appendix 3: Extruder Barrel Temperatures .....</b>	<b>295</b>
A3.1 Setting Extruder Barrel Temperatures .....	295
A3.2 Extruder Barrel Temperature Profile Optimization .....	296
A3.2.1 Introduction .....	296
A3.2.2 Facts about Barrel Temperature Profile (BTP) .....	296

A3.2.3 Typical Process Temperatures for Different Plastics . . . . .	298
A3.2.4 Guidelines and Considerations for Setting Barrel Temperatures . . . . .	299
A3.2.5 BTP Optimization by Design of Experiments (DOE) . . . . .	304
A3.2.6 BTP Optimization by One-at-a-Time Experiments (OTE) . . . . .	305
A3.2.7 Dynamic BTP Optimization . . . . .	305
A3.2.8 Other Studies on Optimization of Extruder Barrel Temperature Profiles . . . . .	307
A3.2.9 Conclusions . . . . .	321
<b>Appendix 4: Process Signal Analysis Using Fast Fourier Transform . . . . .</b>	<b>323</b>
<b>References . . . . .</b>	<b>335</b>
<b>Index . . . . .</b>	<b>347</b>

# 3

## Systematic Troubleshooting

### ■ 3.1 Upsets versus Development Problems

This chapter will primarily focus on upsets, problems that occur in an existing extrusion line for an unknown reason. If the extrusion line had been running fine for a considerable period of time, then it is clear that there must be a solution to the problem. Thus, the objective of troubleshooting is to find the cause of the upset and eliminate it. On the other hand, there may be no solution to a development problem. Solving a development problem involves establishing a condition that has not been achieved before. If it is physically impossible to establish the desired condition, then, clearly, there is no solution to the problem. A functional analysis of the process should make it possible to determine the bounds of the conditions that can be realized in practice.

### ■ 3.2 Machine-Related Problems

In machine-related problems, mechanical changes in the extruder cause a change in extrusion behavior. These changes can affect the drive system, the heating and cooling system, the feed system, the forming system, or the actual geometry of the screw and the barrel. The main components of the drive are the motor, the reducer, and the thrust-bearing assembly. Drive problems manifest themselves as variations in rotational speed and/or the inability to generate the required torque. Problems in the reducer and thrust bearings are often associated with clear audible signals of mechanical failure. If the problem is suspected to be the drive, make sure that the load conditions do not exceed the drive capacity.

### 3.2.1 The Drive System

Older motor drive systems generally consist of a direct current (DC) brush motor, a power conversion unit (PCU), and operator controls. A frequent problem with the motor itself is worn brushes; these should be replaced at regular intervals as recommended by the manufacturer. The manufacturer's recommendations should also be followed in troubleshooting an extruder drive. A typical troubleshooting guide for a DC motor is shown in Table 3.1.

**Table 3.1** Troubleshooting Guide for DC Motor

Problem	Possible cause	Action
Motor will not start	Low armature voltage	Make sure motor is connected to proper voltage
	Weak field	Check for resistance in the shunt field circuit
	Open circuit in armature or field	Check for open circuit
	Short circuit in armature or field	Check for short circuit
Motor runs too slow	Low armature voltage	Check for resistance in armature circuit
	Overload	Reduce load or use larger motor
	Brushes ahead of neutral	Determine proper neutral position for brush location
Motor runs too fast	High armature voltage	Reduce armature voltage
	Weak field	Check for resistance in shunt field circuit
	Brushes behind neutral	Determine proper neutral position for brush location
Brushes sparking	Brushes worn	Replace
	Brushes not seated properly	Reseat brushes
	Incorrect brush pressure	Measure brush pressure and correct
	Brushes stuck in holder	Free brushes, make sure brushes are of proper size
	Commutator dirty	Clear commutator
	Commutator rough or eccentric	Resurface commutator
	Brushes off neutral	Determine proper neutral position for brush location
	Short circuit in commutator	Check for shorted commutator, and check for metallic particles between commutator segment
	Overload	Reduce load or use larger motor
Excessive vibration	Check driven machine for balance	
Brush chatter	Incorrect brush pressure	Measure and correct
	High mica	Undercut mica
	Incorrect brush size	Replace with proper size
Bearings hot	Belt too tight	Reduce belt tension
	Misaligned	Check alignment and correct
	Bent shaft	Straighten shaft
	Bearing damage	Inspect and replace

### 3.2.2 The Feed System

The most important component of the feed system in a flood-fed extruder is the feed hopper and its stirrer and/or discharge screw. A mechanical malfunction of this system can be determined by visual inspection. If the feed hopper is equipped with a discharge screw (crammer feed), the speed of the discharge screw should be checked for unusual variation. For proper functioning, the drive of a crammer feeder should have a torque feedback control to ensure constant feeding and to avoid overfeeding.

Many extruders have square feed hoppers with rapid compression in the converging region. Extruder manufacturers often choose this geometry because of the ease of manufacture, but this hopper geometry does not promote steady flow. When flow instabilities occur in a feed hopper, the extruder operator will often hit the hopper with a heavy object to get the flow going again. As a result, hoppers that cause flow problems often show signs of abuse such as surface damage, dents, scrapes. Such damage is a strong indication of poor feed hopper design.

### 3.2.3 The Heating and Cooling System

The heating and cooling system exercises a certain degree of control of the polymer melt temperature. However, stock temperature deviations do not necessarily indicate a heating or cooling problem because heat is transferred directly to (or removed from) the barrel and only indirectly to (or from) the polymer. It is actually the barrel temperature that is controlled. The local barrel temperature, as measured with a temperature sensor, determines the amount of barrel heating or cooling.

The stock temperature is generally controlled by changing the setpoint of the temperature zones along the extruder. However, due to the slow response of the melt temperature to changes in heat input, only very gradual stock temperature changes can be effectively controlled by setpoint changes. Rapid stock temperature fluctuations (cycle times less than about five minutes) usually cannot be reduced via a melt temperature control system. Such fluctuations are indicative of conveying instabilities in the extrusion process and can only be effectively reduced by eliminating the cause of the conveying instability.

The heating system can be checked by changing the setting to a much higher temperature, for instance 50 °C above the regular setting. The heater should turn on at 100% power, and the measured barrel temperature should begin rising in about one to two minutes. If the heater does not turn on at full power, the barrel temperature measurement is in error, or there is a problem with the electronic circuit of the temperature controller. If the heater turns on at full power but the temperature does not start to rise within two to four minutes, either the barrel temperature

measurement is incorrect, or there is poor contact between the heater and barrel. The cooling system can be checked similarly by changing the setting to a much lower temperature, for instance 50 °C below the regular setpoint. If the cooling does not turn on at full capacity, the barrel temperature measurement is in error, or there is a problem in the circuit of the temperature controller. If the cooling turns full on at full capacity but the temperature does not start to drop within two to four minutes, either the barrel temperature is incorrect or the cooling device is inoperable. This checkout procedure is summarized in Table 3.2.

**Table 3.2** Heating and Cooling System Check

<b>Heating system: Increase setpoint of temperature zone by 50 °C</b>	
Heater turns on full blast and the barrel temperature rises in about 2 minutes	Heating system normal
Heater turns on full blast but the barrel temperature does not change	Poor contact of heater to barrel, insufficient heating capacity, temperature sensor failure
Heater output does not change	Heater failure, controller bad
<b>Cooling system: Reduce setpoint of temperature zone by 50 °C</b>	
Cooling on full blast and the barrel temperature drops in about 2 minutes	Cooling system normal
Cooling on full blast but the barrel temperature does not change	Temperature sensor failure, insufficient cooling capacity, cooling system not functioning at all
Cooling output does not change	Cooling system bad, controller bad

If a substantial amount of cooling is required to maintain the desired stock temperature, this is generally a strong indication of excessive internal heat generation by frictional and viscous dissipation. Internal heat generation can be reduced by lowering the screw speed or by changing the screw design. The main screw design variable that affects viscous heating is the channel depth. Increasing the channel depth will reduce shear rates and viscous heating. Mechanical changes in the forming system are tied to the extrusion die and downstream equipment. These elements can be subjected to simple visual inspection to detect mechanical changes. Changes in the geometry of the screw and/or the barrel are often caused by wear. Because wear is a very important element in the performance of extrusion machinery, it will be discussed in detail in Section 3.2.5.

### 3.2.4 How Screw Design Can Affect Extruder Performance

One possible cause of a number of extrusion problems is poor screw design. It is helpful to have some rudimentary knowledge of screw design so that a problem caused by poor screw design can be recognized. Screw design is a very large topic and we will not go into the details of screw design. For a detailed discussion on


screw design, the reader is referred to the Polymer Extrusion book [176]. However, it is important to have an understanding of some of the main screw design issues.

The screw is the heart of the extruder. The screw performs the following functions:

- Feeding of the plastic particles (usually pellets)
- Conveying of the plastic
- Heating of the plastic
- Melting of the plastic
- Mixing of the plastic
- Degassing of the plastic (in vented extruders)
- Pressure development

### Functional Zones of the Extruder

The main functional zones of the extruder are feeding, solids conveying, melting, and melt conveying in the extruder and melt conveying in the die. These zones have to be in balance for the extruder to achieve stable extrusion conditions. The balancing of the functional zones occurs by the pressures that develop over the length of the extruder. For instance, if the solids-conveying rate is higher than the melting rate, the pressure at the end of the solids-conveying zone will increase as shown in Figure 3.1.

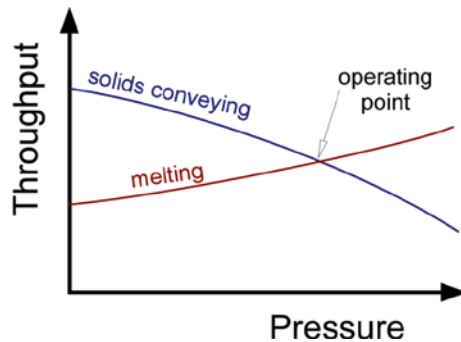

**Figure 3.1** Throughput versus pressure solids conveying and melting – stable conditions

The pressure shown in Figure 3.1 is the pressure at the end of the solids-conveying zone; this is also the pressure at the start of the melting zone. An increase in this pressure will reduce the solids-conveying rate and increase the melting rate. When the solids-conveying rate equals the melting rate, the two zones are balanced. This is where the solids-conveying characteristic curve intersects with the melting characteristic curve. This point is called the operating point.

We have unstable conditions when solids conveying cannot reduce to the point where the solids-conveying rate equals the melting rate; this situation is shown in

**Table 3.9** Comparison of Various Distributive Mixers

Mixers	Pressure drop	Dead spots	Barrel wiped	Operator-friendly	Machining cost	Splitting reorientation
Pins	Medium	Yes	Partial	Good	Low	Medium
Dulmage	Low	No	Partial	Good	Medium	Good
Saxton	Low	No	Fully	Good	Medium	Good
CTM	High	Yes	Partial	Poor	Very high	Good
TMR	High	Few	Fully	Medium	High	Good
CRD	Low	No	Fully	Good	Medium	Good
Axon	Low	No	Fully	Good	Low	Medium
Double-wave	Low	No	Fully	Good	High	Low
Pulsar	Low	No	Fully	Good	Medium	Low
Stratablend	Low	Few	Fully	Good	Medium	Low

### 3.4.2.7 Dispersive Mixing Sections

The following characteristics are desirable for dispersive mixing:


- The mixing section should have regions where the material is subjected to high stresses, preferably elongational stresses.
- The high stress regions should be designed in such a way that the exposure to high shear stresses occurs only for a short time, while exposure to elongational stresses is maximized.
- All fluid elements should pass through the high stress regions many times to achieve efficient dispersive mixing action.
- All fluid elements should pass through the high stress regions the same number of times for uniform mixing.

There are several types of dispersive mixing sections: blister rings, fluted mixing sections, and planetary gear extruders.

#### Blister Ring

The blister ring is simply a circumferential shoulder on the screw with a small clearance between the ring and the barrel (Figure 3.60). All material must flow through this small gap where it is exposed to high shear stresses. Since no forward drag flow occurs in the blister ring, relatively high pressure drops occur across the blister ring. The stress level in the gap is not uniform; therefore, the mixing action is not uniform.




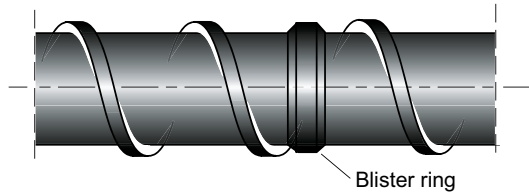

**Figure 3.60** Blister ring

### Fluted Mixing Sections


These mixers have inlet and outlet flutes separated by barrier flights. The material must pass through the narrow gap of the barrier flights to exit from the mixer, and this is where the mixing action takes place. One of the earliest fluted mixers was the Egan mixing section developed by Gregory and Street in which the flutes have a helical orientation (Figure 3.61).

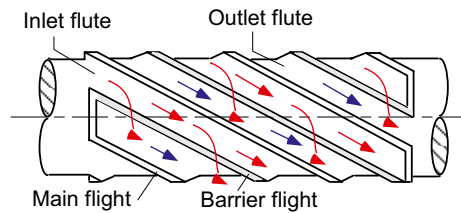


**Figure 3.61** Egan mixing section

Another fluted mixer is the Union Carbide mixer (UC mixer) developed by LeRoy and popularized by Maddock, which has straight flutes (Figure 3.62). Because of the straight flutes, the LeRoy mixer has no forward pumping capability and thus, tends to have a high pressure drop. It is typically machined with a ball mill, and as a result, the flutes have a semicircular cross section. This tends to result in inefficient streamlining at the entry and exit of the flutes. Despite these shortcomings, the LeRoy mixer is probably the most commonly used mixer in single-screw extruders.


It is important to design mixing sections with a low pressure drop. This is particularly true for dispersive mixers. A high pressure drop reduces output, increases melt temperatures, increases residence time, and increases the chance of degradation. Higher melt temperatures reduce melt viscosity and the stresses in the melt in the mixing section, and therefore reduce dispersive mixing. Because a high pressure drop causes high temperatures, a high pressure drop should be avoided.

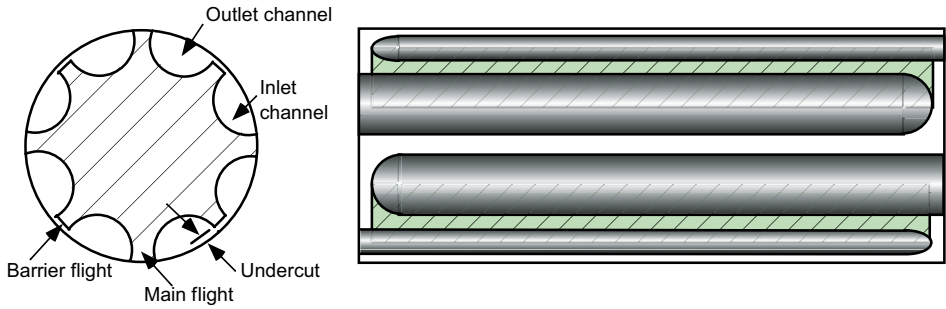

**Figure 3.62** LeRoy mixing section

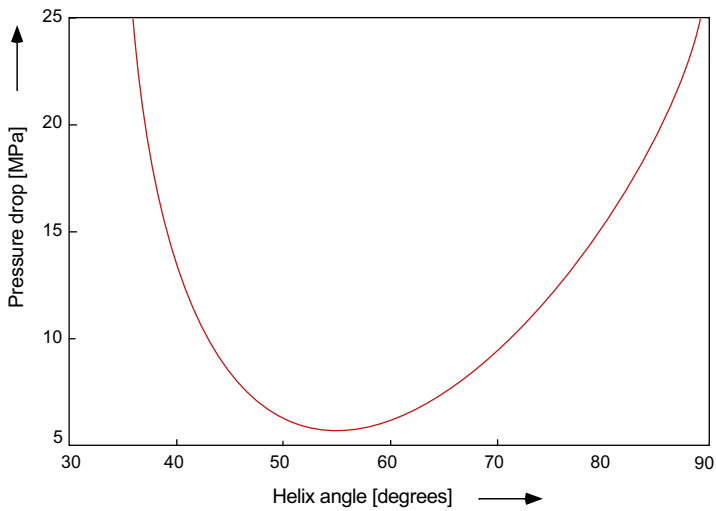

**Figure 3.63** Pressure drop versus helix angle for a Newtonian fluid

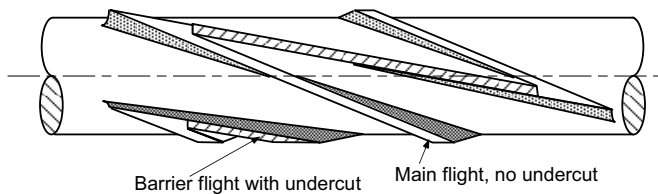

**Figure 3.64** Zorro mixing section

The strong influence of helix angle on pressure drop is illustrated graphically in Figure 3.63. Clearly, a 90° helix angle (as in the LeRoy or Maddock mixer) is not a good choice in terms of pressure drop. Likewise, a 30° helix angle (as in the Egan mixer) is not a good choice either. The optimum helix angle is approx. 50°, and less than 50° for non-Newtonian fluids. The optimum helix angle depends on the


degree of non-Newtonian behavior, and for typical plastics, the optimum angle is approx.  $45^\circ$ .

To promote good streamlining, the helix angle of the barrier flight can be made larger than the main flight, as shown in Figure 3.64. This makes the entry channel wide at the entrance and the exit channel wide at the exit. To minimize hangup, the channels should taper to zero depth at the end of the entry channels and at the beginning of the exit channels. The geometry of this Zorro mixing section is shown in Figure 3.64.

### Planetary Gear Mixers

Planetary gear mixers have six or more planetary screws that revolve around the circumference of the main screw. The planetary barrel section must have helical grooves corresponding to the helical flights on the planetary screws. The planetary barrel section is generally separate, with a flange-type connection to the other barrel section (Figure 3.65). These machines are commonly used in Europe, but not commonly used in the United States. Some of the benefits of planetary gear mixers are:

- Good homogeneity of the melt at low temperature level
- Uniform shear exposure
- High output per screw revolution
- Low production cost per unit throughput
- Self-cleaning action for easy material change
- Good dispersive and distributive mixing of various additives

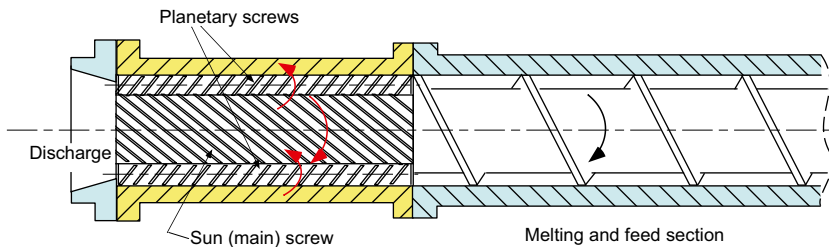


**Figure 3.65** Schematic of planetary gear mixer

These characteristics make the planetary gear extruders well suited for foam extrusion and processing of heat-sensitive materials, such as rigid and flexible PVC. They are also used to process blends (e. g., PVC and ABS), powder coatings, epoxy, polyester, acrylic, polyurethane, and chlorinated polyethylene.

### The Chris Rauwendaal Dispersive (CRD) Mixer

Current dispersive mixers have two important drawbacks. First, they rely mostly on shear stresses to disperse materials rather than on elongational stresses; and second, the material passes over the high stress region only once. New mixing technology developed by Rauwendaal eliminates the disadvantages of existing dispersive mixers [133–139]. The CRD mixer uses a slanted pushing flight flank to create a wedge-shaped lobal region (Figure 3.66).

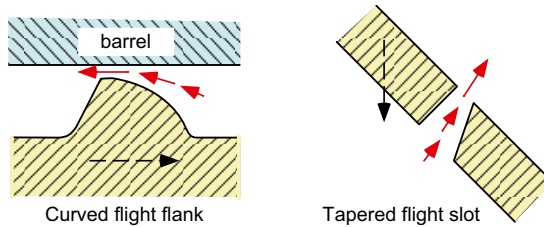

**Figure 3.66** Wedge-shaped regions in CRD mixer

The flights in the CRD mixer are slotted to improve the distributive mixing capability; the slots are not straight but tapered. As a result, the fluid accelerates as it passes through the slots and thus is exposed to elongational flow. Therefore, the fluid is exposed to elongational stress as it flows over the mixing flights, and again when it passes through the slots in the flights. It is important to incorporate good distributive mixing in a dispersive mixing element to randomize the fluid. This ensures that all fluid elements are exposed to the mixing action several times.

The wedge shape creates strong elongational flow. The CRD mixer uses multiple mixing flights with a relatively large flight clearance to ensure that all fluid elements pass through the high stress region several times. Figure 3.67 shows a CRD5 mixer which has four flights with tapered slots. One out of four flight segments is a wiping flight section. The wiping flight sections are staggered in such a way that the mixer completely wipes the barrel.

Because of the large clearances of the mixing flights, wiping flights are used to avoid a stagnant film at the barrel surface and improve pumping. The wiping flights can be continuous flights, as in the CRD8 mixer, or wiping flight segments, as in the CRD5. The CRD8 mixer (Figure 3.68) has eight flights, six mixing flights and two wiping flights. All the flights are slotted to provide the best possible mixing action. Mixers with separate wiping flights are easier to manufacture than mixers that have wiping segments along the mixing flights. Good wiping action is important in maintaining good heat transfer characteristics in the mixing section.

in the extrudate or in the final product. In this case, two dispersive mixers could be used without problems because of the low melt viscosity (high melt index) of the polymer. Low melt viscosity raises little concern regarding an increase in temperature due to viscous dissipation.

**Table 4.7** Data of New Mixing Screw

Diameter, mm	60
Total length, $L/D$	30
<i>Feed zone:</i>	
Channel depth, mm	12
$L/D$	10
<i>Barrier melting zone:</i>	
$L/D$	14
<i>Dispersive mixing zone:</i>	
Channel depth, mm	8
$L/D$	4
<i>Distributive mixing zone:</i>	
Channel depth, mm	8
$L/D$	2

## ■ 4.5 Plastic Film with Poor Transparency

### 4.5.1 Description of the Problem

This case involved a PP film manufactured in a cast film line. The mono-layer was made of homopolymer PP (natural). The film was extruded on a 120-mm single-screw extruder with  $L/D = 28$ . The polymer stream flowed into a feed block, and from there to a cast film die. The extrusion line was fully instrumented.

The film exhibited a serious appearance problem, in this case poor transparency. The film looked opaque throughout the entire roll. The extruder operating conditions are shown in Table 4.8. The extrusion line had a melt temperature probe at the discharge end of the extruder barrel, just before the screen pack. Melt temperature, measured only at this one location, was 225 °C. The screw design was also checked and its geometry is shown in Table 4.9. The screw geometry indicates a screw design intended for processing polyolefins. The screw compression ratio of 4 is relatively high for polypropylene.

**Table 4.8** Operating Conditions of 120-mm Extruder

Screw rotation speed, rpm	170
Extruder back pressure, bar	200
Barrel temperature profile, °C	225 (= feed zone), 225, 215, 215, 215, 215, 215 (= screw tip)
Temperature of polymer granules, °C	30
Melt temperature, °C	225
Output, kg/h	650

**Table 4.9** Screw Geometry

Diameter, mm	120
Total length, $L/D$	28
<i>Feed zone:</i>	
Channel depth, mm	21.3
$L/D$	7
<i>Compression zone:</i>	
$L/D$	8
<i>Metering zone:</i>	
Channel depth, mm	5.3
$L/D$	11
<i>Mixing zone:</i>	
Channel depth, mm	20
$L/D$	2


The first issue was to take into account all the variables related to film transparency in a semi-crystalline material such as PP.

#### 4.5.2 Analysis of the Problem


The problem was visualized based on the fishbone diagram in Figure 4.8, and the variables were checked one by one. Crystallization is a major concern in this case. Therefore, optical microscopy was used to examine the type of crystals occurring in the film under different operating conditions for the extruder and with different cooling rates.

Film manufactured under one specific set of operating conditions was cut to allow examination of the film cross section. A micrograph was taken at  $500\times$  magnification with transmitted and polarized light as illumination (see Figure 4.9). A Leica optical microscope, Laborlux 12 Pol S, equipped with polishing and microtome

capability was used for the examination. Transmitted, reflected, and polarized light can be used with this microscope.

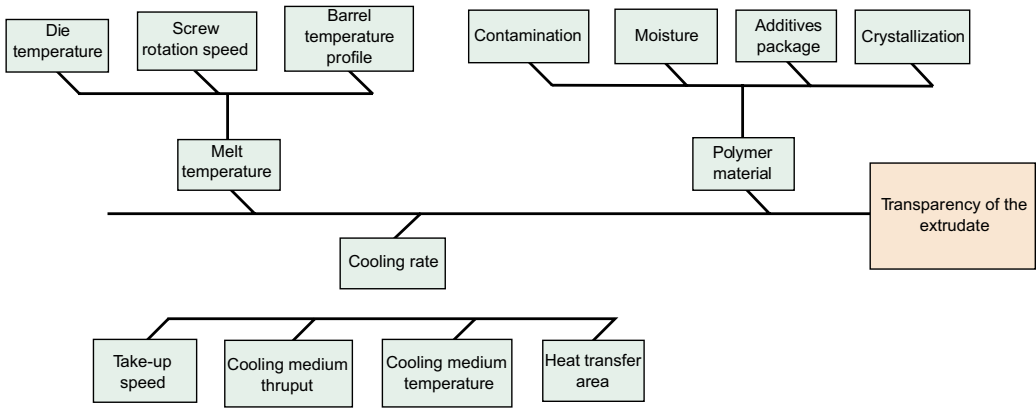

**Figure 4.8** Fishbone chart of transparency problem

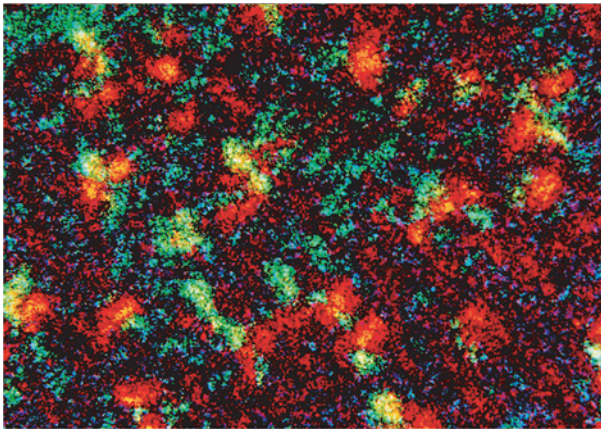

**Figure 4.9** Optical micrograph of spherulites in a polypropylene film

The micrograph shows the type of crystals or spherulites in the film. It is possible to observe both amorphous and crystalline regions. Several micrographs of film manufactured at different operating conditions were obtained.

### 4.5.3 Solution

Crystallization was confirmed as the key variable affecting film transparency based on the micrographs at different line operating conditions. Transparency was better at higher cooling rates and lower chill roll temperatures. The lower limit for



**Figure 4.53**  
Maillefer type dispersive mixer

The melt homogeneity of the polymer blend and the film color were verified by means of optical microscopy and color spectrometer. Agglomerates and striations disappeared and the expected output was obtained for the required production program.

## ■ 4.19 Instability of Formation at the Die

### 4.19.1 Description of the Problem

This problem concerned the single-screw extrusion of a PP blend comprised of recycled post-consumer PP and virgin PP material for industrial strapping and banding. The extruder operated with a smooth barrel surface in the feed section. The extrusion line manufactured heavy duty strapping tapes from PP blends in different compositions and colors. The recycled post-consumer PP content in the blend varied between approximately 40 and 60%, depending on product requirements.

The problem presented the following characteristics:

- the extrusion process was unstable,
- instability of formation at the die was noticeable,
- presence of inhomogeneities, e. g., agglomerates visible for several blend compositions, especially at higher amounts of recycled PP, and
- variations in mechanical resistance of the tapes.

These tapes were produced in 0.5 mm and 0.8 mm thickness and 13 mm width. A simultaneous extrusion of two tapes was required (e.g., two-cavity die). A subsequent drawing process was necessary to achieve the desired mechanical strength and stiffness of the tapes.



A minimum extruder output of 60 kg/h was considered. A melt temperature below 220 °C was a condition for a successful subsequent drawing process (e. g., drawing ratio 10:1).


The performance of an extrusion line is strongly dependent on the interaction between extruder and extrusion die, in particular when using a conventional extruder with a smooth barrel. With regard to the design of an extrusion die, following key criteria should be taken into account [172]:

- The pressure drop is an important parameter, because it is related directly to output and melt temperature difference.
- Ensuring that the melt emerges from the die at the same average rate all across the outlet cross section.
- The surface of the extrudate and/or the interfaces of the melt layers should remain smooth at operating conditions (e. g., within the processing window). Flow anomalies and/or stagnations should be avoided along the die length.

#### 4.19.2 Analysis of the Problem


This tape extrusion case presented an interaction of extruder and extrusion die, where the operation of the main components, screw and die, suffered from a deficient design. In addition, there was a source of visible inhomogeneities of various types caused by recycled post-consumer PP.

The solution was visualized based on the problem tree showed in Figure 4.54, considering each one of the potential causes. A problem tree is a problem analysis tool that illustrates the cause and effect relationship of problem(s) using a hierarchical tree diagram.

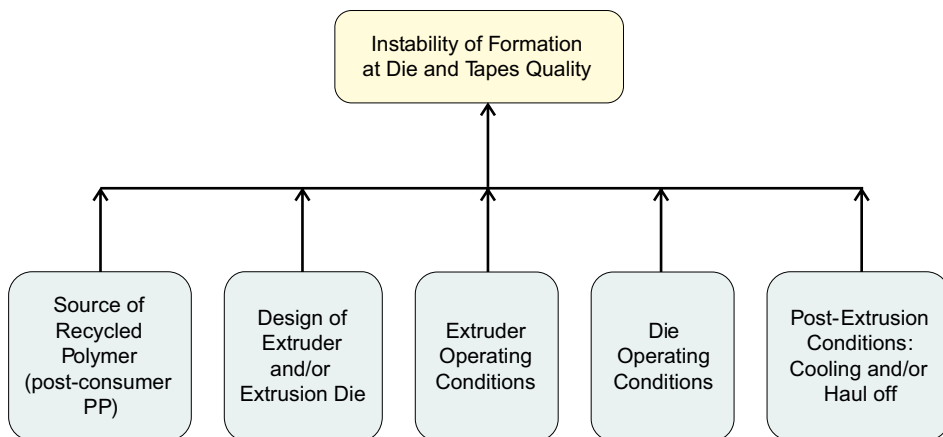


**Figure 4.54** Problem tree for instability of formation at die

Setup and operating conditions were checked; it was discovered that the melt temperatures were too high (above 240 °C), affecting extrudate cooling and other post-extrusion processes. The original screw ( $D = 63.5$  mm,  $L/D = 30.9$ ) was a conventional screw with square pitch and a compression ratio of 2.8:1. This screw had an inefficient mixer for dispersion of agglomerates located at the end of the compression zone. Figure 4.55 shows the geometry of the original screw.

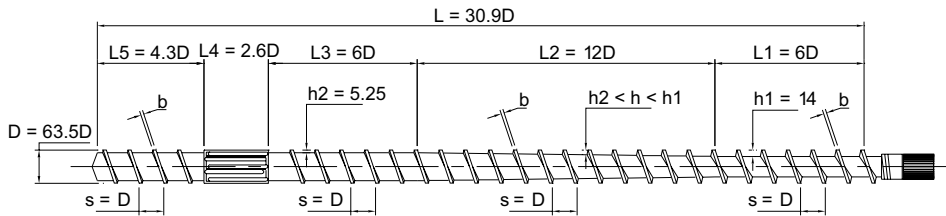

**Figure 4.55** Original 63.5-mm screw

A capillary rheometer was used to obtain complete viscosity curves at three temperatures. Measurements for a polymer blend comprising recycled post-consumer PP were carried out at 200, 220, and 240 °C. Figure 4.56 presents the corrected viscosity curves at three temperatures for a specific PP blend composition. These viscosity curves were strongly affected by the content of recycled PP.

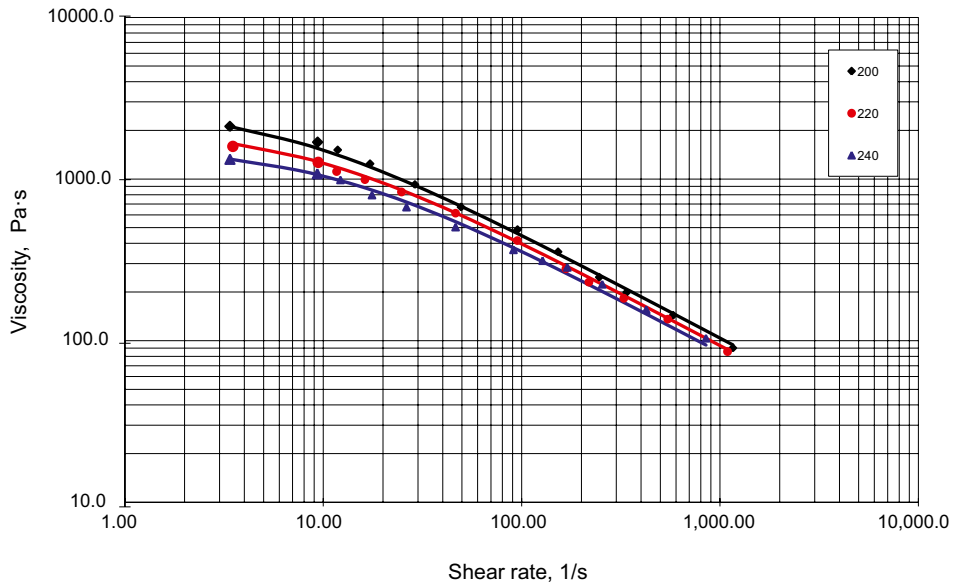


**Figure 4.56** Viscosity curves of blend with recycled PP content

### 4.19.3 Solution


The solution was visualized based on previous information, computer simulations, extrusion line trials, IR thermography, and the problem tree shown in Figure 4.54. Each of the causes was analyzed, focusing on a new screw design suitable for a new two-cavity die.

The newly designed single-screw needed to achieve 60 kg/h output and sufficient mixing to avoid the presence of inhomogeneities or agglomerates caused by recycled PP. Therefore, a variable pitch screw was designed ( $D = 63.5$  mm,  $L/D = 30.9$ ), including a  $4D$  dispersive mixer of Maillifer type and a  $2D$  distributive mixer of Saxton type. Figure 4.57 shows the new optimized design delivering, both in simulations and final trials, a higher output of 60 kg/h at 112 rpm. A uniform rate of molten material could be conveyed to the extrusion die.

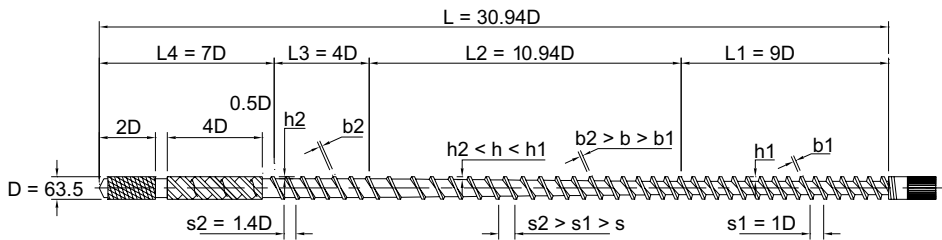


**Figure 4.57** New 63.5-mm variable pitch screw

The new two-cavity die was designed to achieve the same 60 kg/h output with a 2.3 mm die gap for manufacturing both tape sizes (0.5 mm and 0.8 mm thickness and 13 mm width). Figure 4.58 shows the calculated pressure drop along the die length. A pressure drop of approx. 65 bar was predicted and obtained in final trials with small deviations. A low melt temperature increase (less than 5 °C) was observed because of low viscous dissipation.

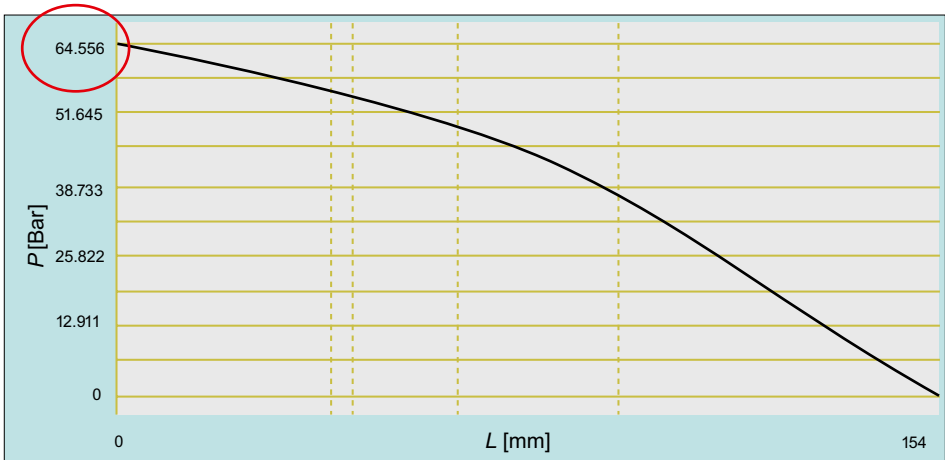

**Figure 4.58** Calculated pressure drop along the die length

Figure 4.59 provides important information with regard to flow front velocity at the die exit. It shows that the melt front velocity was the same for the two die cavities. The simultaneous and uniform tape extrusion was a requirement in this case. The final trials showed a successful uniform extrusion of tapes.

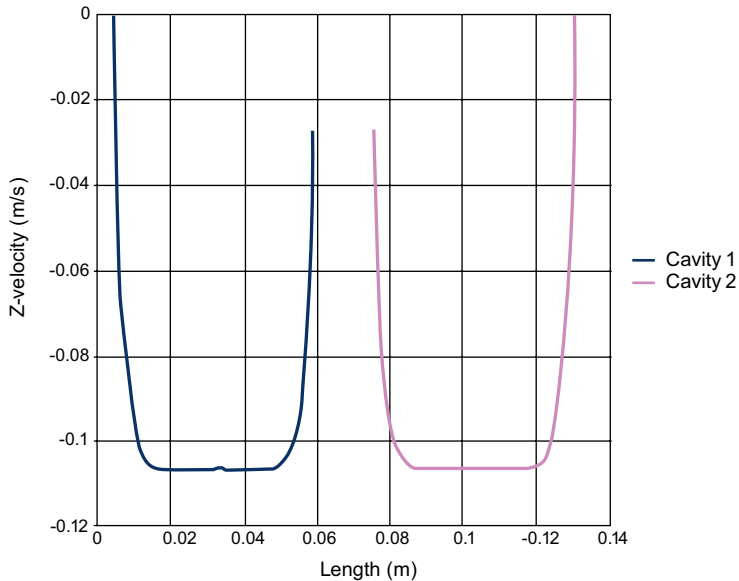

**Figure 4.59** Flow front velocity for two-cavity die

# Index

## A

abrasion and corrosion 72  
adjustable melt temperature probe 17  
agglomerates 196  
agglomerates and grammage variation in  
a PP sheet, case study 200  
air entrapment 151

## B

backpressure 202, 203, 209, 213, 224  
barrel temperature profile (BTP) 296  
black speck *see* black speck, case study  
black speck, case study 247  
breaker plate 12  
BTP optimization  
– DOE 304  
– dynamic 305  
– OTE 305

## C

case studies *see* under each case study  
– agglomerates and grammage variation  
in a PP sheet 201  
– black speck 247  
– color variation in polypropylene carpet  
fiber 172  
– deficient solids conveying and disper-  
sion 213  
– degradation in a long adapter 255  
– dispersion problem in a high-density  
polyethylene bottle 181

– film coextrusion, degradation in the  
middle layer 165  
– film coextrusion with interfacial  
problems 169  
– gear pump speed variation in sheet  
extrusion 238  
– gel formation in a coextruded film  
199  
– heat-sealing problems in a coextruded  
film 187  
– high melt temperature and insufficient  
output in a coextrusion 208  
– high melt temperature in sheet  
extrusion 234  
– improper preheating of extruder 268  
– instability of formation at die 216  
– insufficient melting and mixing in a  
plasticating unit 204  
– lines in the extruded film 170  
– masterbatch selection 194  
– mechanical degradation 252  
– melt fracture or sharkskin in m-PE  
227  
– melt temperature variation 244  
– multilayer film, several appearance  
problems 179  
– non-homogeneous melt in blow  
molding 232  
– output problem in a blown film line  
190  
– pipe extrusion problem 196  
– plastic film with poor transparency  
175

- polymer degradation 184
- scale-up of LLDPE single-screw extruder 229
- shrink voids 258
- unstable pumping in a vented extruder 222
- wear problem in film extrusion 178
- cloud-based
  - server 28
  - system 28
- color contour plot 19
- colorimetry 33, 34, 180
- color variation in polypropylene carpet fiber, case study 172
- contiguous solids melting (CSM) 16
- cooling process 140
- cooling simulation 143
- CSM 16

## D

- data acquisition
  - system (DAS) 9
- data acquisition systems (DASs) 28
  - capabilities of 30
  - comparison among 32
  - features of 31
  - fixed-station data acquisition systems 30
  - portable data collectors (PDCs) 28
  - portable machine analyzers (PMAs) 30
- data analysis
  - window 324
- data collection rate 9, 24
- DC motor 52
  - troubleshooting guide 52
- deficient solids conveying and dispersion, case study 213
- degradation in a long adapter, case study 255
- degradation *see* polymer degradation
  - devolatilization 126
- diaphragm 11
- die-flow problems 156

- mixing, improvement in 160
- polymer degradation 184
- die inlet pressure 10
- die-lip buildup *see* die-flow problems
  - differential scanning calorimetry (DSC) 35
- differential scanning calorimetry (DSC)
  - application field 36
- differential thermal analysis (DTA) 35
- dispersion problem in a high-density polyethylene bottle, case study 181
- dispersive mixers *see* mixers 119
- distributive mixers *see* mixers 119
- draw resonance 119

## E

- energy efficiency 10
- enthalpy 10
- equipment
  - condition of 1
- extruder barrel temperature
  - other studies on optimization 307
  - profile optimization 296
  - setting 295
- extruder performance 54
- extruder temperatures, setting of 34
- extrusion instabilities
  - causes 115
  - devolatilization 126
  - draw resonance 119
  - fluctuations, random 123
  - fluctuations, slow 123
  - frequency of 116
  - functional instabilities 124
  - low-frequency instabilities 122
  - melt-conveying 126
  - melt fracture 117
  - mixing related 127
  - plasticating 125
  - screw frequency instabilities 120
  - shark skin 117
  - solids-conveying 125
  - solving of 149

- extrusion process 1
- extrusion process, understanding of 1
  - time line, construction of 4

## F

- Fast Fourier Transform 24, 323
- feed stock
  - and performance problems 6
  - importance of 6
- feed system, and trouble with feed hopper 53
- FFT 24
- film coextrusion, degradation in the middle layer, case study 165
- film coextrusion with interfacial problems, case study 169
- fishbone diagram 8, 152, 167
- Fourier analysis 324
- Fourier transform infrared spectroscopy 38
  - application field 39
  - equipment, characteristics of 38
- functional zone of the extruder 55

## G

- gear pump speed *see* gear pump speed variation in sheet extrusion, case study
- gear pump speed variation in sheet extrusion, case study 238
- gel formation in a coextruded film, case study 199
- gel problems 153, 155
  - avoid creation of 154
  - cause of 160
  - degradation, reduction of 160
  - die design, changing of 158
  - die-lip buildup, reduction of 158
  - for voids 152
  - gel formation 153
  - incompatible component, removal of 158
  - measuring gels 153
  - melt fracture 156

- patterns, V-and W- 159
- process, changing of 158
- reduction of 156
- removing gels 155
- shear stress, reduction of 156
- specks and discoloration 160
- grammage variation 200
- grooved feed extruder 213

## H

- hard-facing materials
  - application of 84
- hard-facing techniques 84
  - comparison among 84
  - laser hard-facing 87
  - metal inert-gas welding 87
  - oxyacetylene welding 85
  - plasma transfer arc (PTA) welding 86
- heating and cooling system 53
  - checklist 54
  - for heating and cooling systems 54
- heat-sealing problems in a coextruded film, case study 187
- helical solid ribbon 16
- high melt temperature *see* high melt temperature in sheet extrusion, case study
- high melt temperature and insufficient output in a coextrusion, case study 208
- high melt temperature in sheet extrusion, case study 234
- hot spot 20

## I

- ID waviness 24
- immersion melt temperature probe 16
- improper preheating *see* improper preheating of extruder, case study
- improper preheating of extruder, case study 268
- infrared radiation 17

infrared thermography 47  
 infrared thermometer 17, 27  
 inhomogeneities 206, 216, 222, 225  
 instability of formation at die 124  
 instability of formation at die, case study 216  
 instrumentation 1  
 insufficient melting and mixing 115, 204  
 – case study 204  
 intermittent pumping in extruder, case study 222  
 IR temperature measurement 19

## L

laser hard-facing 87  
 light microscope 33  
 light microscopy 33  
 lines in the extruded film, case study 170  
 lines in the extruded product 158  
 low-frequency instabilities 122

## M

machine-related problems 51  
 – feed system 53  
 – heating and cooling system 53  
 – mechanisms 66  
 – solutions to problems 77  
 – testing for 67  
 – troubleshooting guide 52  
 – wear 54  
 machine troubleshooting and maintenance 287  
 – drive motors and belts 289  
 – extruder maintenance checklist 291  
 – noises, unusual 288  
 – oil, checking of 287  
 – screw and barrel 290  
 – spare parts 290  
 – vibrations, monitoring of 288  
 masterbatch selection, case study 193

mechanical degradation *see* mechanical degradation, case study  
 mechanical degradation, case study 252  
 melt-conveying functional instabilities 126  
 melt fracture or sharkskin in m-PE, case study 227  
 melt pool 16  
 melt pressure 9, 10  
 melt temperature 9, 16  
 – distribution 19, 140  
 – in extruder 142  
 – non-uniform 141  
 – variation 19, 140  
 melt temperature variation *see* melt temperature variation, case study  
 melt temperature variation, case study 244  
 mercury 12  
 metal-to-metal wear 74  
 – and flight geometry 75  
 mixers 127  
 – blister ring 132  
 – cavity 127  
 – Chris Rauwendaal Dispersive (CRD) mixer 136  
 – comparison among dispersive 138  
 – comparison among distributive 132  
 – dispersive 131  
 – distributive 127  
 – elongational mixer 138  
 – fluted; CRD-Z; dispersive; blockhead 63  
 – pin 129  
 – planetary gear 135  
 – slotted flight 129  
 – variable depth 130  
 mixing problems, solving of 139  
 – and functional instabilities 127  
 Mohs scale 72  
 motor  
 – load 9  
 multilayer film, several appearance problems, case study 179



**N**

- non-homogeneous melt in blow molding, case study 232
- non-isothermal analysis 19
- non-Newtonian
  - polymer 19

**O**

- optical and appearance properties 163
- output problem in a blown film line, case study 190
- overpressure shutdown 13
- oxyacetylene welding 85

**P**

- pipe extrusion problem, case study 196
- plasma transfer arc (PTA) welding 86
- plasticating 125
- plastic film with poor transparency 175
- polymer degradation
  - chemical 93
  - in extrusion 97
  - mechanical 93
  - residence time distribution (RTD) 97
  - temperature distribution, numerical calculations of 107
  - temperature distribution, simple calculation of 101
  - thermal 93
  - types of 93
- polymer degradation, case study 184
- portable data collectors (PDCs) 29
- portable machine analyzers (PMAs) 29
- power measurements 49
- pressure
  - drop 133, 217
  - feedback control 12
  - transducer 11
- problem tree 8
- process signal 323
- process signal analysis 323

- process temperature 298
- pushing flight flank 20
- pyrometer 27

**R**

- residence time 23
- rheometer
  - capillary 44
  - Couette 43
  - rotational 43
- rheometry 35
  - high pressure capillary rheometry 41
  - torque rheometry 40
- rod extrusion 258
- rupture disk 13

**S**

- sapphire window 18
- scale-up *see* scale-up of LLDPE single-screw extruder, case study
- scale-up of LLDPE single-screw extruder, case study 229
- screen
  - pack 12
- screw speed 23
- screw binding 87
  - and compressive load 92
  - and temperature 88
  - materials, thermal conductivity of 88
  - mechanics of 88
  - temperature distribution, analysis of 91
- screw design 54
  - consideration 58
  - features 61
  - variables 59
- screw flight materials 79
- screw frequency instabilities 120, 121
- screws and barrels
  - hard-facing materials, and properties of 80
  - rebuilding of 83

SEC 10  
 setting barrel temperature 299  
 shark skin 117  
 shear rate 41, 102, 221  
 shear stress 41, 118, 156, 221  
 short-term melt temperature variations 23  
 short-term pressure variations 13  
 shrink void *see* shrink voids, case study  
 shrink voids, case study 258  
 smartphone 48  
 solid bed 16  
 solid bed width profile (SBP) 202  
 solids-conveying functional instabilities 125  
 specific energy  
 – consumption (SEC) 10  
 strain gage capillary pressure 12

## T

teams for repair, building of 5  
 temperature 17  
 – measurement devices 2  
 thermal analysis 35  
 – application field 33, 36, 38, 39  
 – differential scanning calorimetry (DSC) 35  
 – differential thermal analysis (DTA) 35  
 – equipment, characteristics of 38  
 – thermal optical analysis (TOA) 46  
 – thermogravimetric analysis 37  
 – thermomechanical analysis (TMA) 39  
 – tools, miscellaneous 46  
 – torque rheometer 40  
 – torsion braid analysis (TBA) 46  
 thermally sensitive materials 17  
 thermal optical analysis (TOA) 46  
 thermochromic materials, and temperature-related problems 34  
 thermocouple  
 – mesh 20  
 thermographic camera 47

ToolPak add-in 325  
 tools, miscellaneous 46  
 torque rheometer 40  
 – application field 40  
 TPE extrusion 252  
 trailing flank 20  
 training 25  
 transparent window 18  
 troubleshooting guides and checklists  
 – for extrusion instabilities 151  
 – for wear problems 78  
 – tungsten inert-gas welding 85  
 tubing extrusion 244, 247  
 tungsten inert-gas welding 85

## V

vented extruder 222  
 vital signs 9

## W

wall thickness variation 141  
 waviness 23  
 wear 65  
 – abrasion and corrosion 72  
 – abrasive wear 66  
 – adhesive wear 66  
 – Bauer and coworkers 69  
 – Broszeit 71  
 – Calloway and coworkers 71  
 – causes of 72  
 – corrosive 66  
 – Deutsches Kunststoff Institut 69  
 – factors affecting 72  
 – fillers, surface treatment of 73  
 – laminar wear 66  
 – Maelhammar 71  
 – mechanisms 66  
 – Mehdorn 68  
 – Mennig and Volz 68  
 – metal-to-metal wear 74  
 – Mohs scale 72  
 – Moslé 71  
 – Plumb and Glaeser 70

- screw binding 87
- screw flight materials 78
- solutions 77
- surface-fatigue 67
- testing, types of 68
- troubleshooting flow chart 78
- universal disk tribometer 70
- wear problem in film extrusion 178