


HANSER

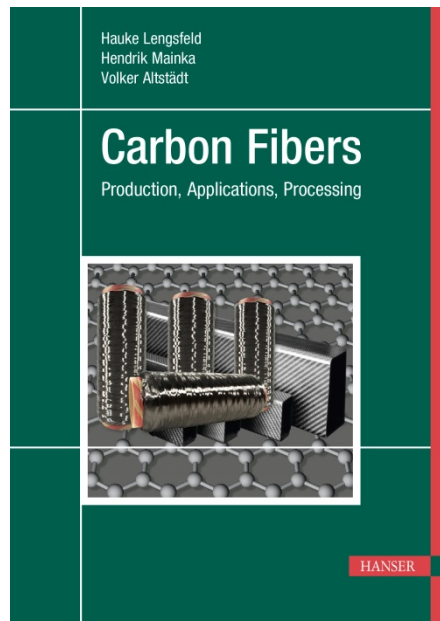

Sample Pages

Carbon Fibers

Hauke Lengsfeld et al.

ISBN (Book): 978-1-56990-828-0

ISBN (E-Book): 978-1-56990-829-7

For further information and order see

www.hanserpublications.com (in the Americas)

www.hanser-fachbuch.de (outside the Americas)

© Carl Hanser Verlag, München

The Authors

Dr.-Ing. Hauke Lengsfeld

After completing his studies in Chemistry and his Ph.D. at the Department of Polymeric Materials at the University of Bayreuth (Germany) (Adviser: Prof. Dr.-Ing. Altstädt), Dr.-Ing. Hauke Lengsfeld was responsible for the production of large CFRP components at Airbus Operations GmbH as a materials and process expert. He was project manager for the development of CFRP components for the Airbus A350XWB. Subsequently, he was Head of Technical Marketing and Sales at Saertex Stade GmbH. At Hexcel Composites GmbH he worked as Technical Support Manager Aerospace for Central Europe. In close cooperation with other coauthors, he wrote his first book on prepreg processing, *Composite Technology*. Since 2018 he has been working as head of development of reactive polymers, epoxy products, and flame retardants at Schill+Seilacher “Struktol” GmbH. Since 2007, Dr.-Ing. Hauke Lengsfeld is also an adjunct professor, teaching courses on fiber reinforced materials and chemistry at several universities.



Dr.-Ing. Hendrik Mainka

After completing his studies in chemical engineering with a focus on molecular and structural product design at the Otto-von-Guericke University Magdeburg (Germany), Dr.-Ing. Hendrik Mainka received his Ph.D. in production engineering (Prof. Dr. Prof. Dr. Axel Herrmann – Faserinstitut Bremen e.V. (FIBRE))

Since 2011 Dr.-Ing. Mainka has been working for Volkswagen in the Group Research – Materials and Manufacturing Processes department. The focus here was on alternative fiber reinforcements and automotive lightweight construction. In 2015 he moved to Volkswagen Group of America, where he has been leading the Product Innovation since 2016. His work here focuses on lightweight automotive construction using fiber composites, electromobility, and additive manufacturing.

In January 2020 Dr.-Ing. Mainka took over the responsibility for the Volkswagen Group Innovation Hub Knoxville. With focus on material research and innovations for electric vehicles, the Knoxville Innovation Hub is an important location of the global Volkswagen Group Innovation network.

Dr.-Ing. Mainka also worked for a year at the Oak Ridge National Laboratory, where he was involved in the development of cost-effective automotive carbon fibers.

**Prof. Dr.-Ing. Volker Altstädt**

Volker Altstädt undertook university studies in physics and received a Dr.-Ing. in 1987 with Prof. Dr.-Ing. Ehrenstein at the Department of Mechanical Engineering at the University of Kassel (Germany). For eight years he was working at the Department for Polymer Composites and later for Polymer Physics at BASF AG in Ludwigshafen. Since 1995 he has been professor for Plastics in Mechanical Engineering and Head of the Department of Polymers and Plastics Composites at the Technical University of Hamburg-Harburg. Since October 2000 he has been full professor and Director of the Department of Polymer Engineering at the University of Bayreuth. In summer 2009 he became in addition the CEO of the Bavarian Research Company NMB GmbH in Bayreuth.



Preface

According to the composite market report of CCEV and AVK, a global carbon fiber market of about 70.5 thousand tons was identified for 2017 [1]. Mordor Intelligence expects an annual growth rate of 13.45% for carbon fibers for the period 2018 to 2023. Compared to other fibers such as glass fibers with several million production tons/year at a growth rate of approx. 7.4% [3], the consumption of carbon fibers worldwide is very low but the volume growth is very high. On the other hand, the applications are highly innovative and mostly driven by the goal of weight reduction. Demand is highest in the aerospace industry (36%) and the automotive industry (24%). But also the wind energy and sports industries with 13% each and the construction industry (5%) are important sales markets [2].

Against this background, the aim of this technical book is to present for the first time a book on fiber composite technology with a focus on modern carbon fibers. The focus is on the individual characteristics of carbon fibers, from the precursor for the fiber, the stabilization and carbonization process, to the resulting atomic structure and the properties. The various paths from the fiber to the roving to the composite material and its properties are discussed using many current examples from various branches of industry.

After a brief introduction to the historical development of carbon fibers, the *second chapter* of the book first explains the atomic model for carbon compounds in order to make the various carbon modifications (diamond, C-nanofiber, fullerenes ...) comprehensible to the reader.

The *third chapter* describes in great detail the process steps of precursor production, oxidative stabilization, and carbonization/graphitization. The discussion of surface treatment and the correct sizing of the fibers is also important for the reader. Very instructive are the many graphic representations, e. g. of C-fibers with and without sizing, as well as the ideas about the interphase.

This chapter is logically followed in *Chapter 4* with the analysis of carbon fibers and rovings made from them. In addition to a presentation of the relevant standards, current test procedures for characterization and classification of the processing behavior of carbon fiber yarns and filaments are addressed. Test apparatuses are

clearly illustrated in pictures and, for example, drapery faults caused by forming are clearly explained by means of photos.

A particular strength of the book is the presentation of the applications of carbon fibers in *Chapter 5*. Due to the excellent and diverse properties of PAN-based fibers, they are used in a wide variety of applications. The book gives application examples of the different fiber types (PREOX and carbon fibers) and explains with examples the different presentations (continuous, cut, ground) from a practical perspective and with rich illustration, to a degree that can hardly be found in other sources. The presentation is subdivided according to the different fiber types and covers the broad spectrum of production methods for applications in the aerospace industry, from automotive structures made of CFRP based on multiaxial fabrics to PrimeTex fabrics for winter sports skis, carbon short fibers for screed concrete or in a 3D-printed fan housing, to name just a few examples.

Since C-fiber production is very energy-intensive, it is no longer possible to talk about materials today without addressing their recycling and carbon footprint in the lifecycle analysis. *Chapter 6* is therefore devoted to a current review of C-fiber recycling and sustainability. Here, too, a distinction is made between the different presentations (continuous, cut, ground) in the description of the various recycling paths. In addition to the actual recycling cycle for C-fibers, the challenges of waste treatment are also addressed and ways are shown of moving from a material mix of different residual materials as an input variable to an energetic or better recyclate semi-finished product (flour, balls, or granulate) by thermal, chemical, or mechanical processes, which lead to sustainable secondary use in a variety of applications shown in the book. The authors come to the conclusion that the recycling of all types of carbon-containing waste and the associated recovery of high-quality carbon fibers (rCF) has been solved on an industrial scale and is increasingly applied.

Nevertheless, there are still challenges to be met in order to be able to expand the use of carbon fibers. These are mainly driven by the high price of the fiber. In *Chapter 7*, precursor costs, energy costs, and investment costs for plants are subdivided into future improvement potentials.

In summary, this technical book can be used both as a manual and as a textbook or reference book for practitioners. The physical basics of carbon fibers, the manufacturing processes, their material, and process engineering basics are taught with a strong practical orientation. The book also aims to make a contribution at the interfaces between carbon fiber technology and semi-finished products and components made from them, and to build the necessary bridges between structure/production and properties. Looking to the future, the book presents important developments in the field of recycling and energy efficiency of modern carbon fiber composite technology.

Bayreuth, February 2019

Volker Altstädt

References for the Preface

- [1] Der globale CF- und CC-Markt – Michael Sauer, Michael Kühnel (CCeV) Der GFK-Markt Europa – Dr. Elmar Witten (AVK)
- [2] Study of the Carbon Global Fiber Market – <https://www.mordorintelligence.com/industry-reports/global-carbon-fiber-market-industry>
- [3] <https://www.reportlinker.com/p05176097/Global-Glass-Fiber-Market.html>

Contents

The Authors	V
Dr.-Ing. Hauke Lengsfeld	V
Dr.-Ing. Hendrik Mainka	VI
Prof.Dr.-Ing. Volker Altstädt	VI
Preface	VII
Acknowledgements	XI
Abbreviations	XIII
1 Introduction	1
2 Carbon and Its Properties	5
2.1 Structure of the Carbon Atom and Atomic Model of Carbon	6
2.1.1 Rutherford's and Bohr's Atomic Models	6
2.1.2 Atomic Orbitals and Hybridization	8
2.2 Modifications of Carbon	9
2.3 Structural Forms of Carbon	12
2.3.1 Diamond - The Diamond Structure (sp^3)	13
2.3.2 Graphite - The Graphite Structure (sp^2)	13
2.3.3 Triple Bonding (sp^1)	14

2.3.4	Other Forms of Carbon	14
2.3.4.1	Fullerenes	14
2.3.4.2	Carbon Nanotubes	14
2.3.4.3	Carbon Black	15
2.3.4.4	Activated Carbon	15
2.3.4.5	Carbon Fibers	15
3	Carbon Fibers	17
3.1	Precursor Manufacturing	18
3.1.1	Wet Spinning	19
3.1.2	Melt Spinning	21
3.1.3	Precursors	22
3.1.3.1	Polyacrylonitrile (PAN)	22
3.1.3.2	Mesophase Pitch	24
3.1.3.3	Further Precursors	25
3.2	Production of Carbon Fibers	25
3.2.1	Precursor Stabilization/Stabilization Process	27
3.2.2	Carbonization and Graphitization	30
3.3	Surface Treatment and Fiber Sizing	32
3.3.1	Sizing (Preparation)	34
3.3.2	Sizing Levels and Sizing Types	38
3.4	Properties and Types	40
3.4.1	Properties of Carbon Fibers	41
3.4.2	Carbon Fiber Types	49
3.5	Manufacturers and Costs	53
3.5.1	Manufacturers of Precursors and Carbon Fibers	54
3.5.2	Manufacturing Costs	56
3.5.3	Manufacturing Capacities	60
3.5.4	Suppliers of Process Technologies	63
4	Characterization of Carbon Fibers	75
4.1	Test Methods on Dry Yarn	76
4.1.1	Density Determination	77
4.1.2	Determination of Linear Density	78

4.1.3	Determination of the Filament Diameter	80
4.1.4	Determination of the Preparation Mass Fraction	80
4.1.5	Determination of Mechanical Parameters on Dry Yarn	81
4.1.6	Roving Test	82
4.1.7	Drape Test	83
4.1.8	Surface Activity and Impregnability	85
4.2	Test Method on Impregnated Yarn	86
4.2.1	Determination of Tensile Strength	86
4.2.2	Fiber-Matrix Interphase	88
4.2.2.1	Testing by Pull-Out Test	89
4.2.2.2	Testing by Push-Out Test	91
4.2.2.3	Fragmentation Test	91
4.2.2.4	Broutman Test	92
4.2.2.5	Testing in a Scanning Electron Microscope	93
4.3	Spectroscopic Test Methods for Carbon Fibers	94
4.3.1	Chemical Characterization of Carbon Fibers and Their Precursors	94
4.3.1.1	Elemental Analysis	94
4.3.1.2	Mass Spectroscopy	95
4.3.1.3	Nuclear Magnetic Resonance Spectroscopy – NMR	96
4.3.1.4	Fourier Transform Infrared Spectroscopy – IR Spectroscopy	97
4.3.2	Chemical Structure Elucidation of Carbon Fibers	98
4.3.2.1	Raman Spectroscopy	98
4.3.2.2	X-ray Photoelectron Spectroscopy, XPS	101
5	Applications of Carbon Fibers	105
5.1	Introductory Remarks	105
5.2	Dry Semi-Finished Fiber Products	106
5.2.1	PREOX Fibers	106
5.2.2	Carbon Fibers	109
5.2.2.1	Carbon Fibers, Continuous	109
5.2.2.2	Carbon Fibers, Cut or Ground	125

5.3	Pre-Impregnated Semi-Finished Fiber Products	133
5.3.1	Applications: UD Prepreg (Thermoset)	134
5.3.2	Applications: Fabric and Scrim Prepreg (Thermoset)	135
5.3.3	Applications: C-SMC/C-BMC	138
5.3.4	Applications: Organotapes	140
5.3.5	Applications: Organosheet	142
6	Recycling and Sustainability	145
6.1	Introductory Remarks	145
6.2	Recycling Cycle and Challenges	149
6.2.1	Process and Plant Challenges	151
6.2.2	The Challenge of Fiber Quality	152
6.3	The Challenge of Waste Treatment	157
6.4	Recycling Processes for Carbon Fibers and CFRP	159
6.4.1	Mechanical Shredding	160
6.4.2	Pyrolysis Process	161
6.4.3	Fluidized Bed Process	163
6.4.4	Solvolysis	164
6.4.5	Chemical Direct Use	165
6.4.6	Electrodynamic Fragmentation	166
6.4.7	New Processes	167
6.4.8	Overview and Comparison of Procedures	168
6.4.9	Hazards and Health Aspects	169
6.5	rCF Products and Applications	170
6.6	Producers	175
6.7	Challenges and Trends	176
7	New Developments	179
7.1	Alternative Precursors	181
7.1.1	Polyethylene	181
7.1.2	Cellulose	182
7.1.3	Lignin	183
7.1.4	Textile PAN	186

7.1.5	Lignin/PAN Blends	187
7.1.6	Nanofibers and Carbon Nanotubes	188
7.2	Alternative Processes	188
7.2.1	Plasma Oxidation	188
7.2.2	Use of Additives	189
7.2.3	Natural Gas Burner	190
7.3	Outlook	190
Index	193

1

Introduction

Uniqueness

The uniqueness of carbon fibers is defined by their excellent properties. Their strength is comparable to that of high-performance steel and their stiffness is higher than that of all known metals, ceramics, or polymers. Even their thermal and electrical conductivity exceeds that of comparable materials (see Chapter 3). The uniqueness of the properties of carbon fibers becomes apparent when the strength or stiffness is divided by the material density to obtain the specific properties. No other known material can currently compete with this result [1-1].

History

Carbon fibers are a synthetic product. The history of carbon fiber began in 1879 with the invention of the first filament lamp by *Thomas Edison*. Edison experimented with fine cotton and bamboo fibers in order to improve the already known arc lamp. He pyrolyzed (carbonized) the fibers at high temperatures. The resulting carbon filaments showed good electrical conductivity and stability for use in incandescent lamps. Unfortunately this application for carbon fiber was soon replaced by tungsten filaments for this application due to their easier and more cost effective manufacturing process. As the result of this development, the initially interest in carbon fiber slowed down again [1-2].

The modern era of carbon fibers did not begin until the 1950s and 1960s. Fundamental development work was done on characterizing the first carbon fibers based on polyacrylonitrile (PAN), pitch, viscose, and rayon in the development laboratories of *Union Carbide* and *DuPont*. It was discovered that pyrolysis of carbon-rich materials resulted in an oriented graphite structure, with a very high modulus of elasticity and strength values. This discovery could be demonstrated in practical tests on so-called graphite whiskers. Whiskers are thread-shaped single crystals with an anisotropic lattice structure [1-3]. Soon several researchers independently recognized the necessity of stretching the fiber at high temperatures ($> 2800\text{ }^{\circ}\text{C}$) in order to further improve the properties, especially the modulus of elasticity. This allowed up to 10 times higher stiffnesses to be achieved than without the stretch-

ing process. One of the first commercial fibers from Union Carbide was the “Thornel-25”. This trade name derives from the Nordic deity *Thor* (“strength”).

At the beginning of the 1960s, Japanese scientists were able to successfully demonstrate in a study the production of high modulus or high stiffness fibers based on polyacrylonitrile (PAN) as a precursor. Earlier attempts of US-American scientists had failed here. The secret of this development was improved PAN precursors. The chemical structure (the so-called backbone) after carbonization was the reason for their excellent properties. At the same time, British scientists also succeeded in developing high-modulus PAN-based fibers, which were soon commercialized. All these developments created the basis for the carbon fibers used today. Through increasing application and further development, production costs have been drastically reduced in the past 35 years through new processes and new raw materials [1–4].

Since around 2010, research and subsequent commercialization have focused on new precursors such as lignin and textile PAN on the one hand, as well as measures for energy efficiency on the other (plasma oxidation, microwave oven) [1–5]. The commercialization of these new technologies is driven by innovative start-ups such as *LeMond Composites*, *RMX*, and *4M* [1–6] [1–7] [1–8].

Current Applications

Due to their outstanding properties, carbon fibers are used in a wide variety of industrial sectors. Examples range from silicon carbide brake disks for aircraft and sports cars, tanks for solid-fuel rockets for space travel, hydrogen tanks and structural components for automobiles, to applications in the construction industry and sporting goods. These and other examples are discussed in detail in Chapter 5.

Recycling

Waste containing carbon fibers occurs in various stages during the production, processing, and use of carbon fibers and carbon fiber reinforced polymer (CFRP) components made from them. Recycling processes include pyrolysis, fluidized bed, solvolysis, and direct chemical use. The challenges that arise and the benefits that can be achieved are described in detail in Chapter 6.

Future Trends

Future applications of carbon fibers will be in the area of additive manufacturing (e. g., Big Area Additive Manufacturing), but also widespread applications in automotive and consumer-oriented areas seem possible if the prices for carbon fibers continue to fall as predicted. The most important requirement for this will be the successful commercialization of new precursors and conversion technologies for the production of carbon fibers.

References for Chapter 1

- [1-1] *Handbook of Composites*, 2nd ed., edited by S. T. Peters, Chapman & Hall, 1998, ISBN 0-412-54020-7
- [1-2] T. Edison; US 470925 1880-03-15
- [1-3] *Faserverbundbauweisen*, M. Flemming, G. Ziegmann, S. Roth, Springer Verlag, 1995, ISBN3-540-58645-8
- [1-4] *High Performance Carbon Fibers*, National Historic Chemical Landmarks of American Chemical Society, September 2003, <https://www.acs.org/content/acs/en/education/whatischemistry/landmarks/carbonfibers.html>
- [1-5] H. Mainka, O. Täger, E. Körner, L. Hilfert, S. Busse, F. T. Edelmann, A. S. Herrmann, *Lignin - an alternative precursor for sustainable and cost-effective automotive carbon fiber*; *Journal of Materials Research and Technology*; Volume 4, Issue 3, July-September 2015, pp. 283–296
- [1-6] LeMond: <https://lemondcarbon.com/>, accessed February 2019
- [1-7] RMX Technologies: <http://www.rmstechnologies.net/>, accessed February 2019
- [1-8] 4M: <http://4mio.com/>, accessed February 2019

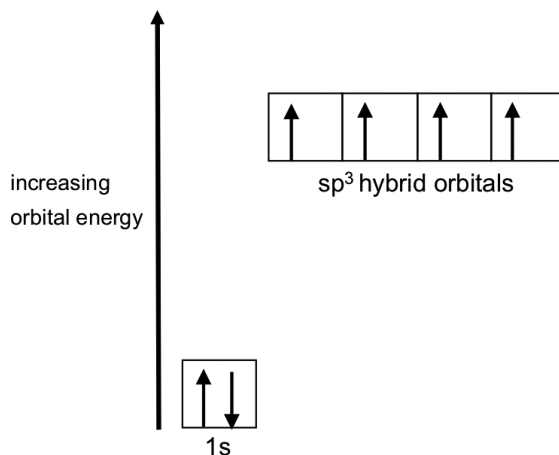


Figure 2.5 sp^3 -hybrid orbitals of the carbon atom [2-2]

These orbitals are called hybrid orbitals and are responsible for the different modifications and structural forms of carbon, which are explained below.

■ 2.3 Structural Forms of Carbon

Diamond and graphite are the two main elemental structural forms (allotropes) of carbon as infinite solid carbon molecules.

In diamond, each carbon atom is sp^3 -hybridized and surrounded by four more carbon atoms. All bonds in the diamond are covalent bonds and have a bond length of 0.154 nm. Due to the sp^3 -hybridization, the basic shape of the diamond structure is a tetrahedron in which the carbon atoms are arranged.

In graphite, the carbon is sp^2 -hybridized, resulting in a planar structure in which each carbon atom is connected to three other carbon atoms. The three covalent bonds have a bond length of 0.1415 nm. The individual layers of graphite are relatively weakly bound to each other. This attraction is called *van der Waals* forces.

In 1985 a new form of carbon was discovered with the fullerenes, which contain just sp^2 -hybridized carbon. The relationship between the individual structural forms of carbon is summarized in Figure 2.6 [2-14].

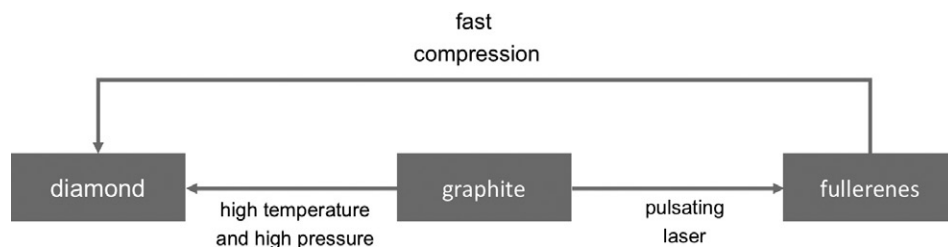


Figure 2.6 Allotropes of carbon and their interconversion

2.3.1 Diamond – The Diamond Structure (sp^3)

In diamonds, the carbon atoms are linked three-dimensionally by covalent bonds. Each carbon atom is tetrahedrally surrounded by four neighboring carbon atoms. It is bound to its neighbors by four σ bonds. The C–C single bonds (length: 1.5445 Å) are formed by overlapping tetrahedrally aligned sp^3 -hybrid orbitals; see Figure 2.7.

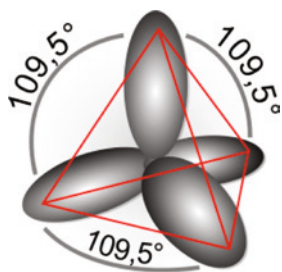


Figure 2.7
Four sp^3 -orbitals – tetrahedral at equal angles [2-12]

2.3.2 Graphite – The Graphite Structure (sp^2)

Graphite is composed of flat carbon layers stacked on top of each other.

Within the layers, each carbon atom is surrounded by three carbon atoms in the form of an equilateral triangle. Each carbon atom is sp^2 -hybridized and with three of its four outer electrons forms three localized σ bonds to its three atomic neighbors. The fourth valence electrons of the carbon atoms are located in delocalized π molecular orbitals, which result from a combination of the p atomic orbitals of the carbon atoms, which are not involved in hybridization and are perpendicular to the sp^2 -hybrid orbitals. Thus, the carbon atoms of graphite are linked by σ bonds as well as by π bonds. In graphite, all C–C bonds have the same length.

3

Carbon Fibers

A carbon fiber is an endlessly long, very thin material strand with a diameter of approximately 5 to 10 μm , essentially consisting of pure carbon. The carbon atoms are arranged in a graphite structure largely parallel to the fiber axis, which makes for the high stability of the fiber [3-1]. Taken together, many thousands of these carbon filaments form a fiber bundle, also known as roving or tow.

The base and thus the starting material of each carbon fiber is its precursor. Since the early work of *Thomas Edison* and the use of cellulose-based carbon fibers in light bulbs, a variety of precursors for the production of carbon fibers have been tested [3-2]. Today there are two commercially available precursors: *polyacrylonitrile (PAN)* and *pitch*.

- PAN-based carbon fibers dominate the market and represent more than 90% of the world market. This is mainly due to the good availability of the precursor PAN and its constant quality.
- The remaining approximately 10% of the world market is occupied by pitch-based carbon fibers. In addition to the classical PAN- and pitch-based precursors, there are some promising new approaches to obtain suitable starting compounds on a different chemical basis (see Chapter 7).

Heat treatment is the conventional process by which carbon fibers are produced today. Figure 3.1 schematically shows the multi-stage production process for carbon fibers based on polyacrylonitrile – a process that contains both chemical and mechanical (stretching of the fibers) components. Three characteristic process steps are performed:

1. Precursor manufacturing
2. Oxidative stabilization
3. Carbonization/graphitization

The scheme gives an idea of how complex and cost-intensive the production of carbon fibers is, especially through energy-intensive heat treatment. This is a quasi-continuous process with several weeks of production time for one production lot.

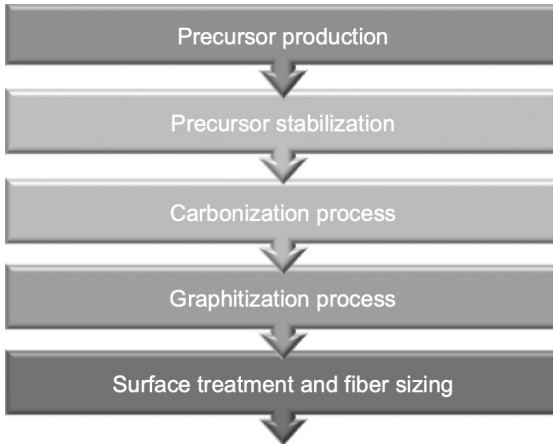


Figure 3.1
Schematic diagram of the manufacturing process for carbon fibers

After the first carbonization, so-called standard fibers or high-strength fibers (HS and HT types) are obtained. For high modulus fibers (IM, HM, UHM types) another step follows, graphitization. At the end of the production process, the carbon fiber obtained consists of > 95% pure carbon.

■ 3.1 Precursor Manufacturing

Suitable precursors are a fundamental prerequisite for the production of carbon fibers. These are long-chain, organic polymers with characteristic properties that significantly determine the later properties of the carbon fiber obtained from them. The exact chemical composition of precursors varies from manufacturer to manufacturer and is usually a strictly guarded secret, as the development of a new fiber type can take 10 years and more to develop. Most carbon fiber manufacturers also produce their own precursors or several different ones, depending on the product range. Typical variable influencing parameters in precursor manufacture are the solvents used, types and quantities of co-monomers used, degree of precursor yarn shrinkage, and yarn stretching in the process.

A precursor should be as economic and ecologically friendly as possible, since on the way to carbon fiber about 50% of the precursor's initial mass is lost as gaseous by-products as a result of the chemical conversion processes. An ideal precursor for carbon fibers already has a high carbon content and can be spun into a thin precursor yarn, mechanically stretched, and then converted into a carbon fiber. The fineness of the yarn is further increased by the mechanical stretching, i. e. the fiber diameter is reduced. The stretching also ensures an advantageous alignment

of the molecular chains along the fiber axis, which is important for the mechanical properties of the later carbon fiber.

There are two main processes for the production of a precursor filament: *wet spinning* and *melt spinning*. Wet spinning is the most commonly used commercial process for the production of PAN precursors [3-3][3-26]. This is due to the fact that the decomposition temperature of PAN is below its melting temperature. Although the melt spinning process was also developed for PAN, it has not yet been implemented on an industrial scale [3-4].

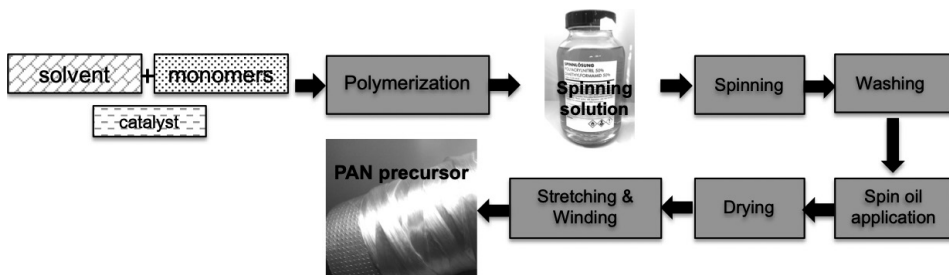


Figure 3.2 Process for precursor production

3.1.1 Wet Spinning

Figure 3.3 shows the typical process flow of a continuous solvent polymerization with subsequent wet spinning. This comprises the two essential steps of the so-called dope preparation (polymerization to polyacrylonitrile) and coagulation (spinning of the PAN). Dope is a general description for a polymer solution in an organic solvent ready for the spinning process (coagulation).

Dope Preparation

To produce dope, powdered acrylonitrile is reacted with other co-monomers, such as methyl acrylate and methyl methacrylate, using a catalyst dissolved in solvents such as dimethyl formamide (DMF) or dimethyl sulfoxide (DMSO) to form polyacrylonitrile. Instead of a solvent-supported reaction, it is also possible to convert the starting materials into a suspension. In order to prevent solidification of the mixture as a result of the polymerization reaction, the temperature of the polymerization reaction must be between 25 and 120 °C. The dope concentration is about 15 to 20% and is pumped directly into the spinning bath (coagulation) [3-5].

3.5.3 Manufacturing Capacities

Figure 3.34 provides an overview of the theoretical global production capacities for carbon fibers. These add up to around 151,000 tons, whereby the figures may vary depending on the source. Compared to the theoretical quantities of approximately 14,000 t [3–19] available in the year 2000, this means an over tenfold increase in capacities [3–20] [3–24].

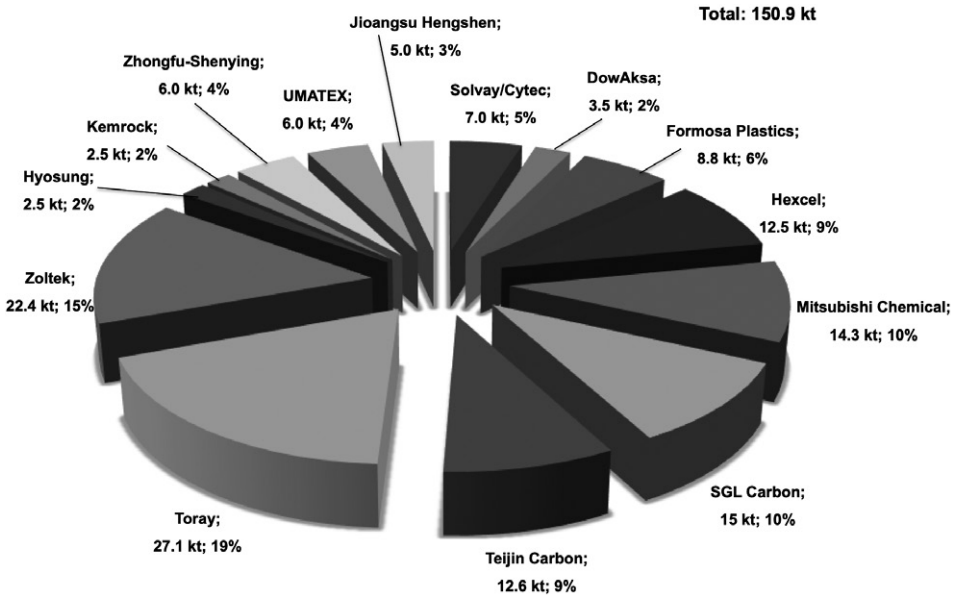


Figure 3.34 Annual theoretical production capacity for carbon fiber, as of 09/2019 (according to [3–20] [3–24])

These figures, based on manufacturer data, express only the theoretically producible quantity, not the actual world market demand for carbon fibers. No distinction is made between different fiber types, K number, or application areas (aerospace or industrial fibers). In Table 3.11 the absolute and percentage capacities per manufacturer are listed. Figure 3.35 illustrates the global distribution of capacity in a country comparison.

The chart in Figure 3.35 shows the theoretical production capacity broken down by country of manufacture. Three major regions account for more than 60% of capacity: North and Central America (38%), Japan (18%), and China (11%).

Table 3.11 Manufacturer, Brand Name, and Theoretical Manufacturing Capacities, as at 09/2019

Manufacturer	Type Designation	Capacity in kt	Capacity in %
<i>Solvay (Cytec)</i>	Thornel®	7.0	4.6
<i>DowAksa</i>	not specified	3.5	2.3
<i>Formosa Plastics</i>	Tairyfil	8.8	5.8
<i>Hexcel</i>	Magnamite, HexTow®	12.5	8.3
<i>Mitsubishi Chemical</i>	DIALED®, Pyrofil, Grafil	14.3	9.5
<i>SGL Carbon</i>	SIGRAFIL®	15.0	9.9
<i>Tejin Carbon</i>	Tenax®-E, Tenax®-J	12.6	8.3
<i>TORAY</i>	TORAYCA®	27.1	18.0
<i>Zoltek</i>	PANEX®	22.4	14.8
<i>Hyosung</i>	TANSOME®	2.5	1.7
<i>Kemrock</i>	JAITEC®	2.5	1.7
<i>Zhongfu Shenying</i>	SYT45	6.0	4.0
<i>UMATEX</i>	UMT®	6.0	4.0
<i>Jiangsu Hengshen</i>	not specified	5.0	3.3
<i>LeMond Composites</i>	GRAIL™	–	0.0
<i>Other</i>	not specified	5.7	3.8
	Total	150.9	100

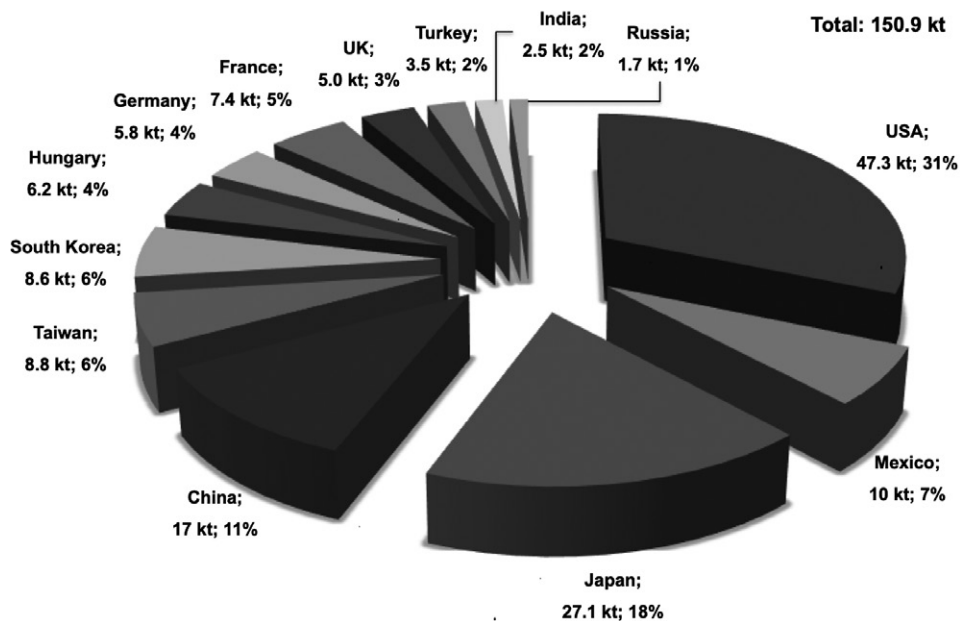


Figure 3.35 Theoretical production capacity by country of manufacture, as at 09/2019 (according to [3–20])

Method C (Density Gradient Column)

This method is based on the principle that a sample is immersed in a liquid column with a linear density gradient and does not sink or rise further within the liquid column according to the sample density. *Density gradient columns* are columns whose density increases uniformly from top to bottom. Thus, method C is basically based on the same principle as method B. First, a gradient column (height 1 m, ϕ 40 to 50 mm) is produced from two liquids of different density. The density distribution in the column is determined using several calibrated reference bodies in the range of the expected carbon fiber sample density and plotted as a calibration curve. A quantity of 1 to 10 mg of the carbon fiber is dipped into the mixture from above in the form of a knot or bundle. The sample slowly sinks down in the column until an equilibrium is reached at the same density of fiber sample and liquid mixture and the fiber sample floats in the liquid. The density ρ of the sample in g/cm^3 results from the previously determined calibration curve of the gradient column.

Normative References:

- ISO 10119:2002: Carbon fibre – Determination of density
- ISO 10548:2002: Carbon fibre – Determination of size content
- ISO 291: Plastics – Standard atmospheres for conditioning and testing

4.1.2 Determination of Linear Density

Gravimetric Determination

The principle for determining the linear density is based on the gravimetric determination of a fiber bundle sample of defined and known length. The measurement can be carried out on carbon fiber yarn with or without preparation application (sizing). The sample is conditioned or dried under a standard climate before measurement. The sizing can be removed by solvent extraction, pyrolysis or chemical digestion. In this case, drying of the sample is not required.

At first the empty weight of a suitable bobbin is measured. Then it is wound with a damage-free fiber sample of defined length. According to Table 4.3 sample length depends on the nominal linear density of the fiber.

Table 4.3 Overview Sample Lengths vs. Nominal Linear Density for Carbon Fibers

Nominal Linear Density T_f in tex	Sample Length in m
$T_f < 50$	Select length so that mass ≥ 0.25 g
$50 < T_f < 125$	5
$125 < T_f < 250$	2
$250 < T_f$	1

The mass m of the fiber sample is calculated from the difference between the two weighs (weight of empty spool or wound spool).

The linear density T_f in g/km of the fiber is obtained from the following equation and is expressed in tex:

$$T_f = \frac{1000 * m}{L}$$

m = mass of the sample in g

L = sample length in m

Vibration Method

Another method for determining linear density is based on the principle of vibroscopic measurement (ISO 1973). Figure 4.1 shows a machine developed by *Textechno GmbH* which largely automates the measurement [4-3]. For this purpose, a filament from a bundle of yarns is inserted into the measuring apparatus and vibrated by a sinusoidal frequency sweep via a loudspeaker. The linear density can be calculated from the resonant frequency f of the filament measured at a constant measuring length L and a known preload F_V according to Equation 4.2:

$$T_f = \frac{F_V}{4 * f^2 * L^2} \quad (4.2)$$

T_f = linear density

F_V = preload force

f = resonant frequency

L = free sample length

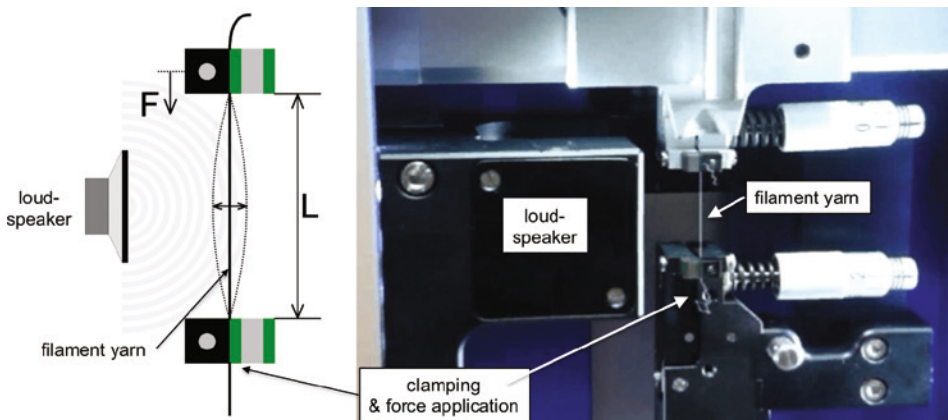


Figure 4.1 Measuring arrangement for vibroscopic determination of linear density [*Textechno GmbH*]

5

Applications of Carbon Fibers

■ 5.1 Introductory Remarks

Due to their excellent and versatile properties, PAN-based fibers are used in a wide variety of applications. Application examples of different fiber types (PREOX and carbon fibers) and different fiber format (continuous, cut, and ground) will be explained in this chapter.

The diagram in Figure 5.1 shows a variety of dry and pre-impregnated fiber semi-finished products, starting with PAN fiber as precursor followed by PREOX fiber and carbon fiber. Furthermore, different possible processing technologies producing different end-products are presented.

Starting from a continuous PAN precursor fiber whose *K number* can be varied depending on the end application (see also Chapter 3), a so-called PREOX fiber (oxidatively stabilized PAN fiber) is produced as the first step in the carbon fiber production process. This PREOX fiber can either be directly converted into carbon fiber, or can be used in textile processing steps in the form of continuous or short cut fiber or fiber flour. The respective K number of the precursor depends mainly on the application of the fiber. It influences the property level and thus also the fiber price considerably. For example, while only low K numbers of 3 to 24 K are used for aerospace applications, yarn counts of 50 to 400 K are common for industrial and automotive applications.

Depending on the application, the fibers are further processed either as dry textiles (with subsequent matrix addition) or as semi-finished products pre-impregnated with matrix (e.g. thermoplastics). The diagram in Figure 5.1 shows how the wide range of semi-finished products can be processed into a finished component in a wide variety of ways.

The following examples show applications of carbon fibers and their processing into components and end-products.

textile production		further processing							
		layup, handling, cutting			matrix addition	curing / consolidation			
dry textile production	pre-impregnated with TS / TP matrix	dry semi-finished products	semi-finished product with matrix		dry semi-finished products	semi-finished product with matrix			
			TS matrix	TP matrix		TS matrix	TP matrix		
PAN precursor Pre-OX fiber	carbon fiber roving	continuous fabric	precutting, (partly)automated layup						
		cut chopped fiber ca. 60-100 mm	(partly) automated layup		CFC, CSiC	hot press			
		UD roving	winding, pultrusion			resin infusion process	ACL, hot press, oven, RT		
			UD prepreg	ATL, AFP		ACL, hot press, oven			
			thermoplastic UD tape			ATL, AFP	ACL, hot press		
			DFP material	ATL, AFP		resin infusion process	ACL, oven		
		continuous fabric	precutting, (partly)automated layup			infusion process (TS or TP), hand laminating	ACL, hot press, oven, RT		
			fabric prepreg	precutting, (partly)automated layup		ACL, hot press, oven, RT			
			fabric organosheets			precutting, (partly)automated layup	ACL, hot press		
			NCF	precutting, (partly)automated layup			infusion process (TS or TP), hand laminating	ACL, hot press, oven, RT	
				NCF prepreg	precutting, (partly)automated layup		ACL, hot press, oven, RT		
				NCF organosheets			precutting, (partly)automated layup	ACL, hot press	
		cut chopped fiber ca. 1-100 mm	SMC / BMC molding compound	precutting, (partly)automated layup		hot pressing, extrusion			
			TP granulates			injection molding, extrusion			
		milled milled fiber ca. 30-150 µm	TP granulates			extrusion of FFF filaments and production of SLS powders	injection molding, extrusion, ALM laser sintering		

Figure 5.1 From precursor to application

5.2 Dry Semi-Finished Fiber Products

5.2.1 PREOX Fibers

As described in Chapter 3, PREOX fibers or yarns are a thermally stabilized intermediate product in the carbon fiber production process. These can either be further processed into carbon fibers or used directly as continuous fibers or as crimped staple fibers. PREOX fiber types commonly offered on the market are summarized in Table 5.1.

Index

Symbols

3D printing technology 128

A

activated carbon 15
airlaid process 171
alternative precursors. *see* precursors
angel hair 151
applications 105
– 3D printing technology 128
– aircraft spoiler 122
– automotive structure 125
– body light construction 137
– CFC transport chain 115
– CFRP flywheel 112
– CFRP lamella 114
– civil engineering, mesh fabric 123
– connection clip 139
– C-SMC & C-BMC 138
– DFP tapes 117
– dry fiber placement tapes 116
– fuselage connection fitting 136
– hybrid B-pillars 137
– injection molding 127, 128
– organosheet 142
– organotape 140
– pressure bulkhead 122
– pull-winding profile 113
– pultrusion profile 112
– screed concrete 131
– side impact beam 113
– skis und snowboards 136

– surface heating 132
– tanks for solid-fuel rockets 110
– vertical stabilizer 135
– wave earthing 115

B

BMC press mass 172
Broutman test. *see* test methods

C

carbon and its properties
– activated carbon 15
– atomic model 6
– atomic orbitals 8
– carbon black 15
– carbon fibers 15
– carbon nanotubes 14
– chemical 5
– diamond structure 13
– fullerenes 14
– graphite structure 13
– hybridization 8
– modifications 9
– physical 5
– sp¹-hybridization 14
– sp²-hybridization 13
– sp³-hybridization 13
– triple bonding 14
carbon black 15
carbon fiber 17
carbon fiber fleece 132

carbon fiber production
 – plasma oxidation 188
 carbon fibers 15
 – applications 105
 – continuous 109
 – cut 126
 – ground 126
 – UD rovings 109
 carbon fiber types 49
 – AM fibers 50
 – HM fibers 50
 – HMS fibers 50
 – HT/HS fibers 50
 – IM fibers 50
 – tabular overview 66, 68, 70, 72
 – UHM fibers 50
 – UHT/UTS fibers 50
 – UMS fibers 50
 carbonization 180. *see* manufacturing
 of carbon fibers
 carbon nanotubes 14, 188
 carbon paper 171. *see also* random non-
 wovens
 C-BMC 138
 cellulose 181, 182
 chemical direct use 165
 classification 147
 “closed-loop” concept 150
 contact angle measurement. *see* test
 methods
 costs 53
 – cost allocation 56
 – energy 179
 – fiber price and fiber strength 59
 – fiber price and titer 59
 – investment 179
 – manufacturing of carbon fibers 56
 – precursor 179
 C-SMC 138
 cut remnants 170

D

denier. *see* titer
 density determination. *see* test methods

developments
 – new precursors 179
 – new processes 179
 – new raw materials 179
 dope. *see* precursor manufacturing
 drapability. *see* test methods
 drape test. *see* test methods
 dry fiber waste
 – recycling 159
 dry semi-finished fiber products 106

E

ecological footprint 147
 electrodynamic fragmentation 166, 169
 electropolymerization. *see* surface
 treatment
 elemental analysis. *see* test methods
 end-of-life (EoL) components 145, 147

F

fabric
 – civil engineering, mesh fabric 123
 – preform 124
 – prepreg 134
 false wire. *see* test methods:roving test
 faser-matrix interphase. *see* test
 methods
 fiber ball 151, 154
 fiber basis weight. *see* properties of
 carbon fibers
 fiber breakage. *see* test methods
 fiber length determination 153
 fiber matrix adhesion 31
 fiber measurement 153
 fiber purity 155
 fiber quality 152
 – 95% level 153
 – defect-free fiber surface 153
 – matrix impurity 153
 fiber sizing 32
 fiber surface 153
 filament diameter. *see* test methods
 filaments. *see* properties of carbon fibers

fluidized bed process 163, 169
Fourier transform infrared spectroscopy.
 see test methods
fragmentation test. *see* test methods
fullerenes 14

G

graphitization. *see* manufacturing of
 carbon fibers

H

hazard
 – electrical 170
 – inhalation 169
health aspects 169
hybrid yarn 172

I

impregnability. *see* test methods
impurities
 – aramid fibers 159
 – fine particles 151
 – foreign fibers 151
 – matrix residues 151
 – metal 159
 – paper 159
 – plastic films 159
 – polyester threads 159
 – pyrolysis coke 151
 – webs 159
 – wood 159
injection molding technology 127

K

K number 105, 119. *see* properties of
 carbon fibers

L

landfilling 147
LFT granules 127

lignin 181, 183
lignin/PAN blends 181, 187
linear density, determination. *see* test
 methods

M

manufacturers 53
 – brand names 61
 – carbon fibers 54
 – global carbon fiber demand 62
 – precursors 54
 – suppliers of process technologies
 63
 – tabular overview of fiber types 66, 68,
 70, 72
 – theoretical production capacities 60
manufacturing of carbon fibers
 – alternative processes 188
 – carbonization 17, 25, 30, 180
 – energy usage 180
 – graphitization 17, 25, 30
 – natural gas burner 190
 – oxidative stabilization 17, 25
 – precursor manufacturing 17
 – precursor stabilization 27
 – stabilization 180
 – use of additives 189
mass spectroscopy. *see* test methods
material mix 157, 158
matrix impurity 153
mechanical separation 168
mesophase pitch. *see* precursors
milled fibers 170
modifications of carbon 9
multiaxial fabric 118
multiaxial fabrics 120
multiple use 149

N

nanofibers 188
natural gas burner 190
non-oxidative processes. *see* surface
 treatment

nuclear magnetic resonance spectroscopy. *see* test methods

O

organosheet 134, 142

organotape 140

oxidation furnace. *see* precursor stabilization

oxidative cyclization. *see* precursor stabilization

oxidative processes. *see* surface treatment

oxidative stabilization. *see* manufacturing of carbon fibers

P

PAN precursor 105

paracrystallinity. *see* properties of carbon fibers

plasma oxidation 188

polyacrylonitrile. *see* precursors

polyethylene 181

precursor

– lignin 183

precursor manufacturing 18. *see also* manufacturing of carbon fibers

– coagulation 20

– dope preparation 19

– spinneret 20

– spinning bath 20

– wet spinning 19

precursors 22

– alternative 179

– carbon nanotubes 188

– cellulose 181, 182

– further precursors 25

– lignin 181

– lignin/PAN blends 181, 187

– manufacturers 53

– mesophase pitch 24

– nanofibers 188

– polyacrylonitrile 22

– polyethylene 181

– textile PAN 181, 186

precursor stabilization. *see* manufacturing of carbon fibers

– oxidation furnace 27

– oxidative cyclization 29

pre-impregnated semi-finished fiber products 133. *see also* prepreg

PREOX fiber 30, 106

– CFC 108

– PANOX 107

– PYROMEX 107

– ZOLTEK OX 107

preparation. *see* sizing

preparation mass fraction. *see* test methods

prepreg 133

– fabric prepreg 136

– NCF prepreg 136

– slit tape 134

– towpreg 134

printing filament 128

processes

– airlaid process 171

– chemical direct use 165

– comparison and overview 168

– electrodynamic fragmentation 166

– fluidized bed 163

– mechanical shredding 160

– new processes 167

– pyrolysis 161

– solvolysis 164

– wet process 171

producers

– recycling processes 175

– recycling products 175

production of carbon fibers 25

products

– staple fiber yarn 172

properties of carbon fibers 41

– carbon fiber types 45

– carbon monocrystal 42

– chemical and physical 45

– comparison of commercial carbon fibers 52

- comparison of mechanical properties 50
- electrical 45
- electromagnetic 45
- fiber basis weight 48
- fiber price and titer 59
- filaments 47
- general 45
- K number 47
- layered structure 41
- mechanical 45
- paracrystallinity 42
- roving 47
- theoretical modulus 41
- thermal 45
- titer 46
- tow 47
- yarn fineness 46
- pull-out test. *see* test methods
- push-out test. *see* test methods
- pyrocarbon. *see* surface treatment
- pyrolysis 168
 - hot air 161
 - inductive heating 167
 - microwave 161
- pyrolysis process 161
- pyrolysis temperature 161

R

- Raman spectroscopy. *see* test methods
- random non-wovens 171
- rCF flour 171
- rCF products 170
 - carbon paper 171
 - hybrid yarn 172
 - random non-wovens 171
 - rCF fiber balls 171
 - rCF flour 171
 - rCF semi-finished products 170
 - rCP short cut 171
 - rC staple fiber tape 173
 - short cut fibers 170
 - SMC mass 172
- rCF, recycled carbon fiber 147

- rCF semi-finished products 170
- rCF short cut 171
- rCP short cut 171
- rC staple fiber tape 173
- recycled fibers 152
- recycling 145
 - pyrolytic 157
- recycling companies 175
- recycling cycle 149
- recycling processes
 - chemical 159
 - mechanical 159
 - thermal 159
- resource conservation 145
- roving. *see* properties of carbon fibers
- roving test. *see* test methods

S

- scanning electron microscope. *see* test methods
- screed concrete 131
- shredding
 - mechanical 160
- sizing 34, 165
 - functional sizing 40
 - non-permanent processing sizing 39
 - permanent processing sizing 39
 - preparation 34
 - sizing level 38
- slit tape 134
- SMC mass 172
- solvolysis 149, 168
 - alcoholysis 164
 - ammonolysis 164
 - hydrolysis 164
- spectroscopic test methods. *see* test methods
- spinneret. *see* precursor manufacturing
- spinning bath. *see* precursor manufacturing
- stabilization 180
- staple fiber yarn 172
- structural forms of carbon 12
- supercritical fluids 165

suppliers of process technologies 63
 suppliers of rCF 175
 surface activity. *see* test methods
 surface damage 155
 surface treatment 32
 – anodic oxidation 33
 – electropolymerization 33
 – non-oxidative processes 32
 – oxidative processes 33
 – pyrocarbon 33
 – thermal oxidation 33
 – wet oxidation 33
 – whisker formation 32
 sustainability 145

T

test methods
 – Broutman test 92
 – chemical characterization 94
 – contact angle measurement 85
 – density determination 77
 – density gradient column 78
 – displacement method 77
 – drape test 83
 – elemental analysis 94
 – fiber breakage 82
 – fiber-matrix interphase 88
 – filament diameter 80
 – Fourier transform infrared spectroscopy 97
 – fragmentation test 91
 – gravimetric determination 78
 – impregnability 85
 – linear density, determination 78
 – mass spectroscopy 95
 – nuclear magnetic resonance spectroscopy 96
 – preparation mass fraction 80
 – pull-out test 89
 – push-out test 91
 – Raman spectroscopy 98

– roving test 82
 – scanning electron microscope 93
 – spectroscopic 94
 – surface activity 85
 – swim-sink method 77
 – tensile strength, determination 86
 – vibration method 79
 – vibroscopic measurement 82
 – X-ray photoelectron spectroscopy 101
 tex. *see* titer
 textile PAN 181, 186
 thermal utilization 147
 titer. *see* properties of carbon fibers
 tow. *see* properties of carbon fibers
 towpreg 134
 turners in the yarn bundle. *see* test methods

U

UD organotape 134

V

vibration method. *see* test methods

W

waste
 – avoidance or reduction 147
 – offcuts 145
 – prepreg scrap 145
 – residual spools 145
 – treatment 157
 weave 118
 – crimp factor 119
 – plain weave 119
 – undulation 118
 wet spinning. *see* precursor manufacturing
 whisker formation. *see* surface treatment

X

X-ray photoelectron spectroscopy. *see*
test methods

Y

yarn fineness. *see* properties of carbon
fibers

yarn spreading. *see* test methods