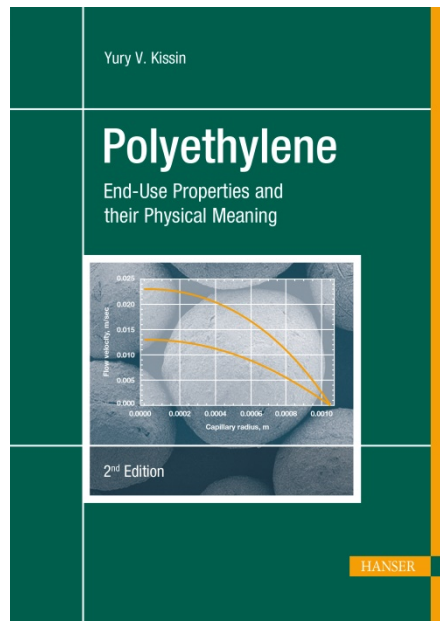


HANSER



Sample Pages

Polyethylene

Yury V. Kissin

ISBN: 978-1-56990-831-0

E-Book ISBN: 978-1-56990-832-7

For further information and order see

www.hanserpublications.com (in the Americas)

www.hanser-fachbuch.de (outside the Americas)

© Carl Hanser Verlag, München

Preface

Every commercial information sheet describing a polyethylene resin, every professional discussion of the application range for a resin, every issue of the resin pricing – they all involve the same short list of resins’ end-use properties. Although the items in the list may vary depending on application, these end-use properties are universally understood throughout the “insider” world without any need for an explanation.

In the case of commercial film-grade LLDPE resins, these parameters usually include the resin’s density, the melt index, the melt flow ratio, the melting point, the dart impact strength, the tear strength in two directions of the film, film haze, and extractables. In the case of blow-molding HDPE resins, the standard parameters are the density, the high-load melt index, environmental stress cracking resistance, the top-load strength, and so on. Tables P.1, P.2, and P.3 show three representative examples of these parameters taken from commercial product data-sheets.

These engineering terms and these values have become “the lingua franca” of all product engineers, plant operators, and catalyst chemists throughout the world involved in the production and testing of polyethylene resins. Test procedures for these parameters are minutely described in standardized documents, ASTM methods in the US and ISO methods in Europe.

On the other hand, the polymer science has developed a different universally understood set of parameters that characterize the same polymers: the average molecular weight, the molecular weight distribution, the content of an α -olefin in an ethylene/ α -olefin copolymer, compositional uniformity of the copolymers, stress-strain characteristics of semi-crystalline polymers, etc.

Table P.1 ExxonMobil LLDPE Resin, LL 1001 Series (Ziegler-Natta Catalyst)

	SI units	English units	Measurement method
Density	0.918 g/cm ³	0.0332 lb/in ³	ASTM D1505
Melt index (190 °C, 2.16 kg)	1.0 g/10 min	1.0 g/10 min	ASTM D1238
Peak melting temperature	121 °C	250 °F	
Tensile strength at yield, MD	9.4 MPa	1,400 psi	ASTM D882
Tensile strength at yield, TD	9.5 MPa	1,400 psi	ASTM D882
Tensile strength at break, MD	50 MPa	7,700 psi	ASTM D882
Tensile strength at break, TD	35 MPa	5,100 psi	ASTM D882
Elongation at break, MD	580%	580%	ASTM D882
Elongation at break, TD	850%	850%	ASTM D882
Secant modulus, MD, at 1%	190 MPa	28,000 psi	ASTM D882
Secant modulus, TD, at 1%	220 MPa	32,000 psi	ASTM D882
Dart drop impact strength	100 g	100 g	ASTM D1709A
Elmendorf tear strength, MD	80 g	80 g	ASTM D1922
Elmendorf tear strength, TD	400 g	400 g	ASTM D1922
Haze	14%	14%	ASTM D1003

Table P.2 ExxonMobil LLDPE Resin Exceed 1018KA Series (Metallocene Catalyst)

	SI units	English units	Measurement method
Density	0.918 g/cm ³	0.0332 lb/in ³	
Melt index (190 °C, 2.16 kg)	1.0 g/10 min	1.0 g/10 min	ASTM D1238
Peak melting temperature	<119 °C	<247 °F	
Tensile strength at yield, MD	9.65 MPa	1,400 psi	ASTM D882
Tensile strength at yield, TD	9.65 MPa	1,400 psi	ASTM D882
Tensile strength at break, MD	54.5 MPa	7,900 psi	ASTM D882
Tensile strength at break, TD	42.7 MPa	6,200 psi	ASTM D882
Elongation at break, MD	500%	600%	ASTM D882
Elongation at break, TD	600%	600%	ASTM D882
Secant modulus, MD, at 1%	186 MPa	27,000 psi	ASTM D882
Secant modulus, TD, at 1%	193 MPa	28,000 psi	ASTM D882
Dart drop impact strength	590 g	1.3 lb	ASTM D1709A
Elmendorf tear strength, MD	250 g	250 g	ASTM D1922
Elmendorf tear strength, TD	470 g	470 g	ASTM D1922
Haze	18%	18%	ASTM D1003

Table P.3 Braskem Blow Molding HDPE Resin GM7746C

	SI units	English units
Density	0.944 g/cm ³	0.0341 lb/in ³
Melt index (190 °C, 21.6 kg)	4.5 g/10 min	4.5 g/10 min
Vicat softening point	126 °C	259 °F
Tensile strength at yield	23 MPa	3,340 psi
Tensile strength at break	42 MPa	6,090 psi
Elongation at yield	13%	13%
Elongation at break	880%	880%
Flexural (secant) modulus at 1%	890 MPa	129,000 psi
Secant modulus, TD, at 1%	220 MPa	32,000 psi
Environmental stress-cracking resistance (100% Igepal)	≥ 1,000 h	≥ 1,000 h

This book provides a necessary bridge between the meaning of the engineering end-use parameters of polyethylene resins and molecular and structural characteristics of the same materials used in the polymer science. The main goal is to translate such commonly used parameters as the melt index of a resin or the dart impact strength of a film sample into the universal language of the polymer science. After this translation is completed, many facets of the resin engineering properties became transparent and easily explainable. For example:

- What happens with the melt flow ratio of a resin after the catalyst used to produce it is modified to increase its sensitivity to an α -olefin?
- What happens with the dart impact strength or the tear strength of LLDPE film when butene is replaced with hexene or octene in an ethylene/ α -olefin copolymerization reaction employing the same catalyst and why does it happen?
- Why are the melting points of metallocene LLDPE resins so much lower compared to the melting points of LLDPE resins of the same density and melt index prepared with Ziegler-Natta catalysts?
- Why are hexane extractables of metallocene LLDPE resins lower compared to extractables of LLDPE resins of the same density produced with Ziegler-Natta catalysts?

These are the types of questions this book provides answers to. Detailed analysis of many such links between end-use engineering properties of polyethylene resins and molecular characteristics of the polymers turn out to be quite complex. For this reason, the description of each such linkage is accompanied by numerous examples of practical significance and by explicit data for commodity polyethylene resins.

This book is written with three audiences in mind. The first, the most populous audience, includes product engineers, the specialists who evaluate properties of polyethylene resins and judge their usefulness (as well as pricing) for a particular application. These specialists are very adept at measuring and evaluating end-use engineering properties of the resins they are working with. However, they are usually less confident when asked which of the molecular characteristics of the polymers should be changed, and in what direction, to improve a particular end-use property of a resin.

The members of the second audience are plant and pilot plant operators in the polyethylene industry. These individuals deal with large-scale continuous production processes and need to know which of the process variables they control are crucial for achieving and maintaining the desired end-use parameters of the resins.

The members of the third audience are catalyst chemists, specialists in designing new polymerization catalysts and modifying the existing ones. These professionals often judge a success or a failure of a catalyst they develop based on properties of a small amount of polymer prepared in the laboratory, from ~ 10 to ~ 200 g. Their principal interest is to know which parameters of a polymer prepared in bench-type tests have the highest predictive power and how to translate the changes they make in a catalyst recipe into the changes in the end-use properties of the resins manufactured with the catalyst on the commercial scale. One has to take into account that measurements of some end-use properties require large quantities of resins far exceeding what can be prepared in laboratory.

This book is intended to improve communication bridges between these three groups of specialists and to aid them in understanding each other better and faster.

The second edition of the book contains updated information on many aspects of the relationships between scientific and engineering characterization of various polyethylene resins, as well as new information on polyethylene recycling (a rapidly expanding field of resin applications with a different set of technical requirements) and on polyethylene resins prepared with post-metallocene catalysts. It also contains a new chapter describing several important commercial characteristics of polyethylene film, the content of extractable and soluble material in LLDPE film, blocking of LLDPE film, and film haze.

Yury V. Kissin

Rutgers, The State University of New Jersey
New Jersey, USA

Contents

Preface	VII
1 Educational Minimum: Synthesis, Structure, and Properties of Polyethylene Resins	1
1.1 Classification and Applications of Polyethylene Resins	1
1.2 Catalysts for Synthesis of Polyethylene Resins	4
1.3 Industrial Processes for the Manufacture of Polyethylene Resins	7
1.4 Chemistry of Ethylene Polymerization Reactions	9
1.5 Molecular Weight Distribution of Polyethylene and Methods of Its Analysis	13
1.6 Examples of Molecular Weight Distribution of Polyethylene Resins	18
1.6.1 Polyethylene Resins Produced with Metallocene Catalysts	18
1.6.2 Polyethylene Resins Produced with Supported Ziegler-Natta Catalysts	19
1.6.3 Polyethylene Resins Produced with Chromium Oxide Catalysts	21
1.6.4 Polyethylene Resins with Bimodal Molecular Weight Distribution	22
1.7 Copolymer Statistics and Its Application to Description of LLDPE and VLDPE Resins	25
1.8 Compositional Uniformity of Polyethylene Resins	27
1.9 Morphology of Polyethylene Resins	31
1.10 Mechanical Properties of Polyethylene Resins	34
1.11 Recycling of Polyethylene Resins	37

2	Melt Index and Melt Flow Ratio of Polyethylene Resin	43
2.1	Introduction	43
2.1.1	Measurement Method of Melt Index	43
2.1.2	Empirical Correlations between Melt Index and Molecular Weight	44
2.2	Basics of Polymer Rheology. Melt Flow through a Capillary	46
2.2.1	Flow of Polymer Melt through a Cylindrical Capillary . .	48
2.2.2	Melt Index of Newtonian Melt	50
2.3	Melt Flow of Monodisperse Polyethylene Resins	51
2.4	Additivity Rules for Melt Viscosity. Calculation of Melt Indexes and Melt Flow Ratios from Molecular Weight Distribution Data .	53
2.4.1	Additivity Rules for Zero-Shear Viscosity	53
2.4.2	Additivity Rules for Effective Viscosity and General Expressions for Flow of Multi-Component Non-Newtonian Melts	55
2.5	Examples of Melt Flow Behavior of Commercial Polyethylene Resins	58
2.5.1	Polyethylene Resins Produced with Single-Site Metallocene Catalysts	59
2.5.2	LLDPE Resins Produced with Supported Metallocene Catalysts	61
2.5.3	LLDPE Resins Produced with Supported Ziegler-Natta Catalysts	62
2.5.4	HDPE Resins with Bimodal Molecular Weight Distribution	65
2.5.5	Effect of Long-Chain Branching	68
3	Melting Point of Polyethylene Resin	71
3.1	Introduction	71
3.2	Melting Point of HDPE Resin	72
3.3	DSC Melting Curves and Melting Points of LLDPE and VLDPE Resins Produced with Single-Site Catalysts	76
3.3.1	Effect of Crystallization Conditions	76
3.3.2	Effect of Copolymer Composition	77
3.3.3	Crystallization Process of Compositionally Uniform Ethylene/ α -Olefin Copolymers. Model for Primary Crystallization	80
3.3.4	Model for Secondary Crystallization	81
3.3.5	Combined DSC Model for Compositionally Uniform LLDPE and VLDPE Resins	82

3.4	DSC Melting Curves and Melting Points of LLDPE Resins Produced with Multi-Site Catalysts	84
3.5	DSC Melting Curves of LLDPE Resins Produced with Post-Metallocene Catalysts	88
4	Crystallinity Degree and Density of Polyethylene Resin	91
4.1	Crystallinity Degree	91
4.1.1	Measurement Methods	91
4.1.2	Definition of Crystallinity Degree of LLDPE and VLDPE Resins Based on Copolymer Statistics	93
4.2	Density	95
4.2.1	Measurement Methods	95
4.2.2	Physical Meaning of Polyethylene Density	95
5	End-Use Mechanical Properties of Polyethylene Film	101
5.1	Mechanical Properties of Polyethylene Resins	101
5.1.1	Effect of Stretching Speed on Mechanical Properties ...	102
5.1.2	Orientation in Polyethylene Film	103
5.2	Dart Impact Strength of LLDPE Film	105
5.2.1	Description of Dart Impact Test	105
5.2.2	Model of Dart Impact Test	108
5.2.3	Effect of Mechanical Properties of LLDPE Resins on Dart Impact Strength	111
5.2.4	Comparison of Film Made from Ethylene/1-Butene and Ethylene/1-Hexene Copolymers	113
5.2.5	Effect of Copolymer Composition	114
5.2.6	Effect of Compositional Uniformity	115
5.3	Tear Strength of LLDPE and LDPE Film	116
5.3.1	Description of Tear Test	116
5.3.2	Physical Details of Tear Test	117
5.3.3	Model of Tear Test	122
5.3.4	Effect of Pendulum Speed	127
5.3.5	Effect of Resin Mechanical Properties	127
5.3.6	Effect of Film Orientation	128
5.3.7	Comparison of Tear Strength of Ethylene/1-Butene and Ethylene/1-Hexene Copolymers	130
5.3.8	Low Density Polyethylene	130
5.4	Comparison of Factors Determining Tear Strength and Dart Impact Strength of LLDPE Film	131

6	End-Use Testing of High Molecular Weight HDPE and MDPE Resins	135
6.1	Top Load Test of HDPE Containers	135
6.1.1	Mechanics of Top Load Test	136
6.2	Dynamic Burst Test of HDPE Pipes and Tubing	139
6.3	Static Burst Test and Long-Term Fatigue in Polyethylene Pipes and Tubes	140
6.3.1	Principal Equation and Theory of Low-Stress Failure ...	140
6.3.2	Physical Mechanism of Polymer Failure under Low Stress	142
6.4	Environmental Stress-Cracking Resistance	145
6.4.1	Description of ESCR Test	146
6.4.2	Physics of Environmental Stress Cracking	147
6.4.3	Structural Parameters of HDPE Resins Affecting ESCR .	148
6.4.4	Relationship between ESCR and Long-Term Fatigue in Polyethylene	150
6.4.5	Mechanism of Environmental Stress Cracking	153
7	End-Use Testing of LLDPE Film; Extractables, Solubles, Blocking, and Haze	159
7.1	Introduction	159
7.2	Extractables and Solubles in LLDPE Resins	161
7.2.1	Measurement Methods	161
7.2.2	Control of Extractables in LLDPE Resins	163
7.3	Blocking of LLDPE Film	164
7.3.1	Measurement Method	164
7.3.2	Control of Film Blocking	165
7.4	Haze of Polyethylene Film	166
	Index	169

1

Educational Minimum: Synthesis, Structure, and Properties of Polyethylene Resins

■ 1.1 Classification and Applications of Polyethylene Resins

The term “polyethylene resins” describes catalytically produced semi-crystalline homopolymers and copolymers derived mostly from ethylene [1-4], as well as ethylene polymers produced in radical polymerization reactions under high pressure [4-6]. Polyethylene resins of different types are widely used as commodity plastics.

Some polyethylene resins contain strictly linear polymer chains; their chemical formula is $-(\text{CH}_2-\text{CH}_2)_n-$, where n is a very large number, from $\sim 1,000$ to $\sim 100,000$. Other polyethylene resins contain branches in their chains. Most such resins are produced in ethylene/ α -olefin copolymerization reactions. The molecular structure of ethylene/ α -olefin copolymers with a low α -olefin content can be approximately represented by the formula:



where the $-\text{CH}_2-\text{CH}_2-$ units come from ethylene and the $-\text{CH}_2-\text{CH}(\text{Branch})-$ units come from the α -olefin molecule. The x , y , and z values in these chains can vary from small (4 to 5) to a very large number.

All the branches in catalytically produced polyethylene resins are of the same size; they are the alkyl substituents in the α -olefin molecules: the ethyl group if the α -olefin is 1-butene, the butyl group if the α -olefin is 1-hexene, the hexyl group if the α -olefin is 1-octene, or the isobutyl group if the α -olefin is 4-methyl-1-pentene. When ethylene is polymerized at a high pressure via the radical mechanism, they have essentially the same chain structure. In this case, branches of several different types are formed spontaneously due to peculiarities of the radical polymerization reactions. These branches are linear or branched alkyl groups [7, 8]. Their lengths vary widely within each polymer molecule. Two types of such branches are distinguished: short-chain branches, from the methyl to the isoctyl group, and

Table 1.1 Commercial Classification of Polyethylene Resins

Resin type	Symbol	α -Olefin content, mol %	Crystallinity degree, %	Density, g/cm ³
Resins of high density	HDPE	0	65 to 70	>0.960
Resins of high density	HDPE	0.2 to 0.5	60 to 65	0.941 to 0.959
Resins of ultrahigh molecular weight	UHMW HDPE	0	30 to 40	0.930 to 0.935
Resins of medium density	MDPE	1 to 2	45 to 55	0.926 to 0.940
Resins of low density	LLDPE	2.5 to 3.5	30 to 45	0.915 to 0.925
Resins of very low density	VLDPE	>4	<25	<0.915
Low density polyethylene produced in radical reactions	LDPE	Branching degree 20 to 30 CH ₃ /1,000C	45 to 55	0.910 to 0.940

The content of an α -olefin in commercially manufactured ethylene/ α -olefin copolymers varies in a wide range, from <0.5 up to 20 mol %. These copolymers, depending on the content of α -olefin, are called *medium density polyethylene resins* (MDPE), *linear low density polyethylene resins* (LLDPE), or *very low density polyethylene resins* (VLDPE). The group of the VLDPE resins is further divided into two subgroups, polyethylene *plastomers* with a crystallinity degree of 10 to 20% and density from 0.915 to 0.900 g/cm³, and completely amorphous ethylene *elastomers* with density as low as 0.86 g/cm³. By definition, all the catalytically produced resins contain only short-chain branches derived from α -olefins. However, polymerization reactions utilizing some metallocene catalysts and chromium oxide catalysts can also introduce long-chain branches in the polyethylene chains (Section 1.4).

Some metallocene catalysts can copolymerize ethylene with cycloolefins, such as cyclopentene, cyclooctene, or norbornene. In this case, the branches in polyethylene chains are either small cycles containing from 5 to 10 carbon atoms, or two fused cycles. These materials form an additional resin type called *cycloolefin copolymers* (COC).

The five categories of polyethylene resins are specified according to their melt index measured according to ASTM D1238-10:

Category:	1	2	3	4	5
Melt index, g/10 min:	>25	10 to 25	1 to 10	0.4 to 1.0	below 0.4

Other characteristics of polyethylene resins, predominantly color, are specified by class. The three classes of polyethylene resins are designated as A, B, and C. The classes indicate color, amounts, and types of antioxidants, and other additives.

Class A refers to naturally colored polyethylene resins, Class B includes white and black-colored resins, and Class C covers weather-resistant black resins containing more than 2% carbon black.

The classification of polyethylene resins in its present form affords a basic distinction between different resin types. However, the classification is often poorly suited to delineate fine differences between structures and properties of various resins that play an important role in the sophisticated modern resin market. After all, the market grades different resins mostly according to their end-use properties rather than by their general classification.

Taken together, polyethylene resins account for the largest fraction, ~35%, of the worldwide plastic production. The volume of HDPE resins manufactured worldwide in 2019 was over 50 million metric tons and the combined volume of LLDPE and LDPE resins over 60 million metric tons. In the US alone, the total production volume of all polyethylene grades in 2019 amounted to ~23 million metric tons.

Applications of polyethylene resins vary greatly by the grade. The applications of the two most important grades are:

HDPE resins	Blow molding (containers and bottles)	~31%
	Film (biaxially oriented)	~28%
	Injection molding	~22%
	Other applications	~19%
LLDPE resins	Film (blown and cast)	~80%
	Injection molding	~7%
	Wire and cable coating/insulation	~4%
	Other applications	~9%

■ 1.2 Catalysts for Synthesis of Polyethylene Resins

Polyethylene resins are produced commercially with transition metal catalysts of different types [1–4, 9, 10] or in high-pressure radical polymerization reactions [4, 5]. This section provides merely a brief sketch of the catalyst chemistry; a much more detailed discussion of catalyst preparation techniques is presented in reviews [3, 4, 9, 10].

Several groups of polymerization catalysts are especially important.

Titanium-based Ziegler-Natta catalysts: All these catalysts consist of two components. The first component is called a *catalyst*, it is a liquid or a solid powder that

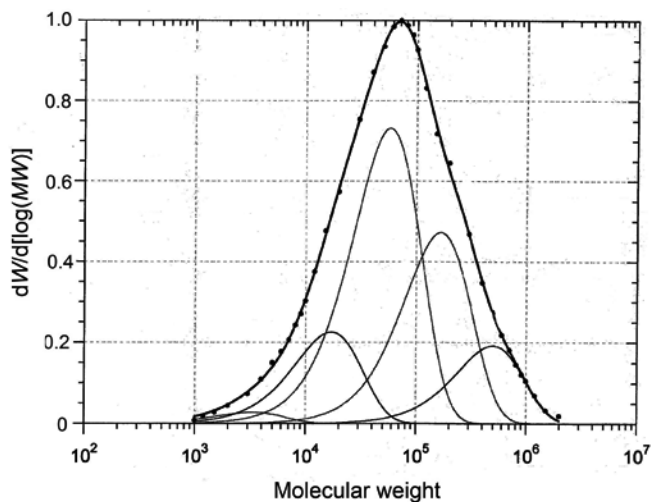


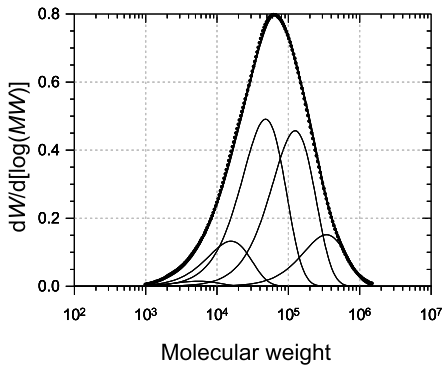
Figure 1.5 Experimental GPC curve of HDPE resin produced with supported Ziegler-Natta catalyst at 80 °C (points) and its resolution into Flory components

Table 1.2 gives parameters M_w and FR_j of each Flory component in this resin. The numbering of Flory components used in the table, from I to IV in the order of increasing molecular weight, as well as numbering of Flory components in all the following tables, is arbitrary.

Table 1.2 Flory Components in HDPE Resin Produced with Supported Ziegler-Natta Catalyst

Flory component (j)	Molecular weight ($M_{w,j}$)	Content (FR_j), %
I	15,700	14
II	47,900	45
III	124,400	29
IV	342,900	12
Total resin	133,000	100

Figure 1.6 shows the GPC curve of an LLDPE resin (ethylene/1-hexene copolymer with $C_M^{\text{copol}} = 3.5$ mol) produced with a supported Ziegler-Natta catalyst at 85 °C. The product is also a mixture of four Flory components [49]. The distribution of copolymer molecules with respect to their molecular weight in these LLDPE resins is also quite broad, similarly to HDPE resins produced with catalysts of the same type (Figure 1.5) [42, 50]. The width of the molecular weight distribution $(M_w/M_n)^{\text{av}}$ of the copolymer is 4.0.

**Figure 1.6**

Experimental GPC curve of LLDPE resin (ethylene/1-hexene copolymer with $C_M^{\text{copol}} = 3.5$ mol %) produced with supported Ziegler-Natta catalyst and its resolution into Flory components

Table 1.3 gives parameters of each Flory component in the copolymer mixture. Detailed kinetic analysis of ethylene/1-hexene copolymerization reactions with supported Ziegler-Natta catalysts showed [50–52] that Flory components in the copolymers differ not only in the average molecular weight but also in the 1-hexene content. As Table 1.3 shows, the components with the lowest molecular weight (components I and II) have the highest 1-hexene content whereas the components with the highest molecular weight (components III and IV) have the lowest 1-hexene content. The existence of the differences in the copolymer composition was confirmed with several crystallization fractionation studies described in Section 1.8 (see Table 1.7).

Table 1.3 Flory Components in LLDPE Resin Produced with Supported Ziegler-Natta Catalyst

Flory component (j)	Molecular weight ($M_{w,j}$)	Content (FR_j), %	C_M^{copol} , mol %
I	15,700	11	8 to 10
II	47,900	39	~4
III	124,400	37	0.6 to 0.8
IV	342,900	12	0.3 to 0.4
Total resin	109,000	100	3.5

1.6.3 Polyethylene Resins Produced with Chromium Oxide Catalysts

Figure 1.7 shows the GPC curve of a typical HDPE resin prepared with a chromium oxide catalyst. The molecular weight distribution of such resins is always very broad; seven Flory components are needed to represent this GPC curve. Table 1.4 lists molecular weights of Flory components in an HDPE resin produced at 90 °C.

2

Melt Index and Melt Flow Ratio of Polyethylene Resin

■ 2.1 Introduction

The melt index of a polyethylene resin is universally accepted in the industry as an indicator of the resin's average molecular weight. Melt indexes are routinely measured both in the industrial environment and in laboratory using simple automated equipment and simple standard procedures (Section 2.1.1). The polymer science operates with a different set of parameters describing molecular weight characteristics of ethylene polymers. The three most often used parameters are the weight-average molecular weight M_w , the number-average molecular weight M_n , and the width of the molecular weight distribution, the M_w/M_n ratio. Measurement methods and the statistical meaning of these parameters are described in Section 1.5 of Chapter 1.

This chapter describes correlations between these two sets of molecular weight characteristics.

2.1.1 Measurement Method of Melt Index

Melt indexes of polyethylene resins are measured using the instrument called an *extrusion plastometer*. The measurement procedures are specified in the American Society for Testing and Materials (ASTM) method D1238-10, Conditions E and F, and in the International Organization for Standardization (ISO) Method 1133. Figure 2.1(a) shows the schematics of the melt index measurement. A small amount of resin (~6 gram) is placed inside the heated cylindrical barrel (9.55 mm diameter) with a metal die at its bottom. The die has a round capillary opening, 2.095 mm in diameter and 8 mm in length. Some procedures use a shorter die (a half-die) 4 mm long with a 1.0475 mm capillary opening. A metal plunger with a long narrow stem is placed on the top of the resin sample. The resin is kept at 190 °C for 6 minutes to achieve complete melting. After that, the melt is pressurized by placing a cylindrical metal weight on the upper tip of the stem. The pressure of the plunger

forces the melt through the capillary opening. By definition, the melt index of a polyethylene resin is the weight of the melt extruded through the capillary over a period of 10 minutes, that is, the melt index is a measure of the melt flow rate (g/10 min). Depending on the type of polyethylene resin, four different standard weights (the total of the cylindrical metal weight, the plunger, and the rod) are used to measure melt indexes, 2.16, 5.16, 10.16, and 21.6 kg. The melt indexes are respectively designated as I_2 , I_5 , I_{10} , and I_{21} . If no indication of the weight is given, the I_2 value is traditionally reported. In the earlier designs of extrusion plastometers, the polymer extrudate was collected, cooled, and its amount was determined by weighing. Modern extrusion plastometers use an automated procedure; they measure the speed of the downward movement of the plunger under a given weight.

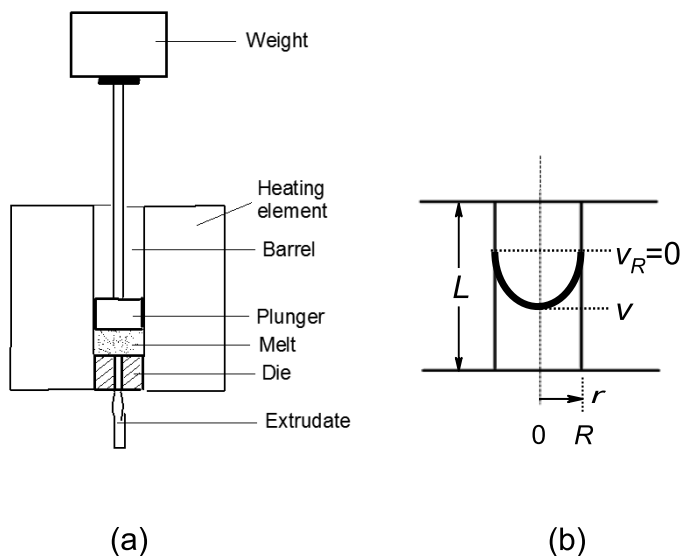


Figure 2.1 (a) Schematics of melt index measurement; (b) flow of viscous liquid through capillary

2.1.2 Empirical Correlations between Melt Index and Molecular Weight

If one is dealing with polyethylene resins of a single particular type (for example, resins produced with the same catalyst under different reactor conditions), the melt index is a precise relative measure of the resin's weight-average molecular weight M_w . Several empirical correlations between M_w values and melt indexes of various polyethylene resins were developed. Figure 2.2 shows one such example

■ 3.3 DSC Melting Curves and Melting Points of LLDPE and VLDPE Resins Produced with Single-Site Catalysts

3.3.1 Effect of Crystallization Conditions

Compositionally uniform ethylene/ α -olefin copolymers prepared with single-site metallocene catalysts represent a convenient model to examine the effect of crystallization conditions on the shape of DSC melting curves. Figure 3.3 demonstrates this effect using as an example two ethylene/1-hexene copolymers prepared with different metallocene catalysts in toluene slurry at 70 °C [25]. The copolymers have a different composition: the sample in Figure 3.3(A) contains 0.8 mol % of 1-hexene and the sample in Figure 3.3(B) 2.4 mol %. Their crystallinity degree is also different, 63% and 42%, respectively. Ethylene copolymerization reactions in toluene slurry are accompanied by orderly crystallization of polymer molecules. DSC peaks of both nascent copolymers (materials recovered from polymerization reactors without any additional thermal treatment) are relatively narrow (Figure 3.3(A) and Figure 3.3(B)). When the mixture of the two copolymers is slowly crystallized from toluene solution, each component forms separate crystals (Figure 3.3(C)).

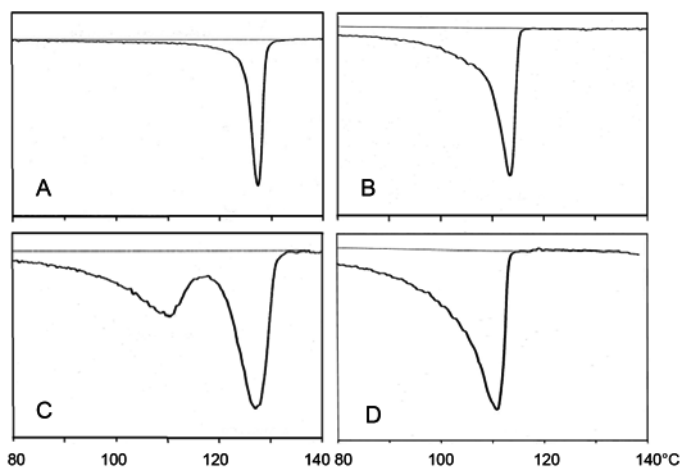


Figure 3.3 DSC melting curves in the narrow temperature range 80 – 140 °C: A and B – nascent copolymers with $C_M^{\text{copol}} = 0.8$ and 2.4 mol %, respectively, produced with two metallocene catalysts; C – mixture of the two copolymers crystallized from solution; D – re-melted copolymer B

When these compositionally uniform copolymers are crystallized from the melt, the lamella-formation process is much faster and less orderly than during crystallization from solution or during a polymerization reaction. The DSC peak of a thermally pretreated copolymer (Figure 3.3(D)) is broader than the DSC peak of the solution-crystallized copolymer (Figure 3.3(B)), and its melting peak is positioned at a lower temperature. This comparison emphasized the need for a thoroughly followed protocol in the preparation of resin samples for the DSC analysis. Analytical laboratories often examine polymer samples with unknown or poorly defined thermal history. A standardized procedure, for example, pre-melting of a resin specimen in a hot press, is a desired step for a DSC sample preparation.

3.3.2 Effect of Copolymer Composition

Figure 3.4 shows melting points of compositionally uniform ethylene/1-hexene copolymers produced with single-site metallocene catalysts as a function of their composition. The copolymers contain from 0.5 to 3.5 mol % of 1-hexene. All the materials were thoroughly homogenized before the DSC analysis by hot-pressing polymer powders into thick film. The melting points were measured during the second melting step; each corresponds to the maximum on the DSC melting curve. The results show that the melting point decreases with an increase in the 1-hexene content in the copolymers. This section describes a DSC model which provides an explanation for the steep dependence between T_m and C_M^{copol} values evident from Figure 3.4.

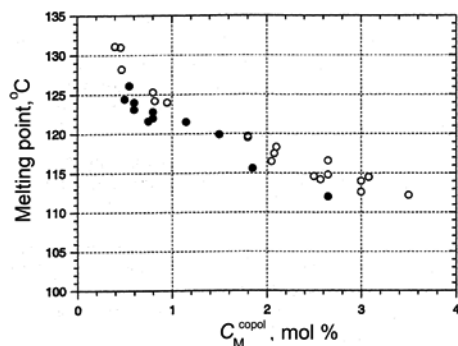


Figure 3.4

Melting temperatures of ethylene/1-hexene copolymers of different composition produced with single-site metallocene catalyst; heating rates are 10 °C/min (●) and 2 °C/min (○)

Basic statistical expressions used for modeling the melting behavior of compositionally uniform ethylene/ α -olefin copolymers are given in Section 1.7 of Chapter 1. For the goal of the DSC modeling, a copolymer chain can be viewed as consisting of a set of monomer sequences; blocks of ethylene units, $M-(E)_n-M$, and blocks of α -olefin units, $E-(M)_m-E$. All commercial LLDPE and VLDPE resins contain rela-

curve are the yield point, the end-of-necking point, and the breaking point. These points are characterized by six parameters:

1. The yield stress, σ_y , and the yield strain, ε_y ;
2. The necking stress, σ_n , and the end-of-necking strain, ε_n ;
3. The breaking (tensile) stress, σ_{br} , and the breaking strain, ε_{br} .

The ε values in Figure 1.18 are the length ratios in the strained and the original sample: $\varepsilon = \text{elongation} + 1$; the minimum ε value for a polymer sample before stretching is 1.

Mechanical changes shown in Figure 1.18 are accompanied by irreversible structural changes in the polymers; they are schematically shown in Figure 1.19. After the yield point of a polymer sample is passed, an area consisting of a highly oriented material (the neck) develops in the strained sample. As the stretching proceeds further, the two principal morphological features of a semi-crystalline resin, the spherulites and the microfibrils (see Figure 1.16 and Figure 1.17), are gradually disassembled until all the material in the tested sample becomes highly oriented. This transformation occurs at a nearly constant necking stress σ_n . The last stage of the sample stretching is called strain hardening; it involves a simultaneous further increase in the strain and the stress in the oriented sample. At some point during this stage the material finally breaks. The length of the strain-hardening range, $\varepsilon_{br} - \varepsilon_n$, depends on the grade of the resin. HDPE resins break soon after the onset of strain hardening; their σ_y and σ_{br} values are relatively close. On the other hand, LLDPE resins have a relatively large strain-hardening range and their σ_{br} value is always much higher than the σ_y and the σ_n values.

Two more mechanical parameters are used to characterize polyethylene resins. The first parameter, the Young's modulus (M_{Young}), characterizes stiffness of a resin sample, the slope of the stress/strain curve at very low strain. By definition, $M_{\text{Young}} = d(\sigma)/d(\varepsilon - 1)$ at low ε . In practice, two similar parameters, the secant modulus, are often used, the stress at 1% elongation or at 2% elongation. The second mechanical parameter, the strain-hardening modulus ($M_{\text{str-hard}}$), characterizes stiffness of a fully stretched and oriented resin sample: $M_{\text{str-hard}} = (\sigma_{br} - \sigma_n)/(\varepsilon_{br} - \varepsilon_n)$.

5.1.1 Effect of Stretching Speed on Mechanical Properties

Both end-use mechanical tests of polyethylene film, the dart impact test and the tear test, are carried out at a high deformation speed (Section 5.2 and Section 5.3). Relaxation phenomena in polyethylene are relatively slow, and most mechanical parameters of the resins depend on the deformation speed [8, 9]. These dependencies were measured experimentally in a broad range of deformation speeds V from 0.5 to 150 cm/min (0.2 to ~60 in/min) for several ethylene/1-hexene LLDPE res-

ins, both compositionally uniform resins produced with metallocene catalysts and compositionally nonuniform resins produced with Ziegler-Natta catalysts. In most cases, the dependencies between the tested parameters, σ or ε , and the deformation speed can be represented by simple empirical relationships using as a standard a particular σ or ε value at the standard deformation speed V_{stand} of 50.8 cm/min (20 in/min):

$$\sigma_y(V) = \sigma_y^{\text{stand}} + k(\sigma_y) \cdot \log(V/V_{\text{stand}}), \quad \text{the slope } k(\sigma_y) \approx 0.14 \quad (5.1)$$

$$\sigma_n(V) = \sigma_n^{\text{stand}} + k(\sigma_n) \cdot \log(V/V_{\text{stand}}), \quad \text{the slope } k(\sigma_n) \approx 0.11 \quad (5.2)$$

$$\varepsilon_n(V) - \varepsilon_y(V) = \varepsilon_n^{\text{stand}} - \varepsilon_y^{\text{stand}} + k(\varepsilon_n - \varepsilon_y) \cdot \log(V/V_{\text{stand}}) \quad (5.3)$$

The slope $k(\varepsilon_n - \varepsilon_y)$ in the last expression varies from 0.5 to 0.6 depending on the LLDPE grade. Three other parameters of the stress/strain curve, ε_y , ε_{br} , and σ_{br} , practically do not depend on the deformation speed.

5.1.2 Orientation in Polyethylene Film

Figure 5.1 shows the orientation pattern, orientation of the c axis in crystallites (the direction of molecular chains) in two types of articles manufactured from polyethylene, a blow-molded item and film.

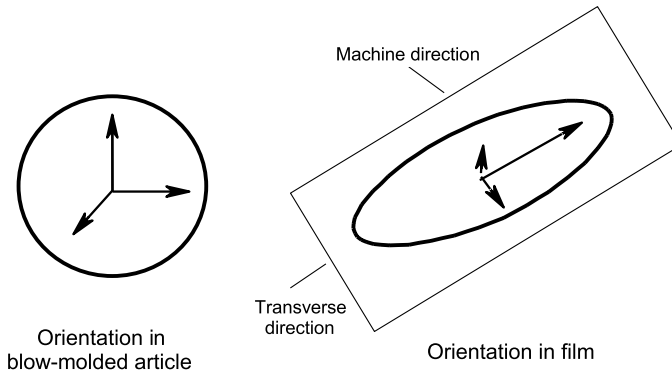


Figure 5.1 Orientation distribution in blow-molded article and in film

Thick-walled, blow-molded articles are practically isotropic in terms of chain orientation. On the other hand, polymer chains in polyethylene film are preferably oriented in the machine direction of film manufacture. The level of orientation depends on the resin type; it is the highest in HDPE film but significantly lower in

6.4.5 Mechanism of Environmental Stress Cracking

The mechanism of the polyethylene failure under the environmental stress cracking conditions represents a special case of the general mechanism describing the mechanical failure of polymers under low stress, which is discussed in Section 6.3.2. Similar to the process of failure under low stress, the environmental stress cracking mechanism includes four distinct stages [59, 60]:

craze nucleation (the longest stage) → craze growth → craze failure (crack initiation) → crack propagation.

The overall behavior of polyethylene articles under the conditions of environmental stress cracking is similar to that of their failure under low stress. Both processes are dominated by the molecular entanglement network, which is formed in the polymer melt prior to crystallization [38] (Section 6.3.2). Crystallization of most polyethylene resins from the melt leads to a spontaneous fractionation of their components. The low molecular weight and branched macromolecules crystallize at the latest stage of crystallization and concentrate in interlamellar and inter-spherulite regions. These short polymer chains cannot serve as good ties between lamellae and between spherulites. The principal feature responsible for the ESCR is the presence of tie molecules of a high molecular weight, which reinforce mechanically weak areas between and within spherulites and mitigate the effects of polymer fractionation [18, 38, 45–49]. The content of tie molecules in an HDPE resin can be artificially increased, for example, by co-blending a small amount of a semi-crystalline ethylene block copolymer with the resin [61] or by co-blending an HDPE resin with a high molecular weight LLDPE resin, especially if the LLDPE resin contains a small amount of long-chain branches [62].

Two subjects are important for the discussion of the mechanism of environmental stress cracking: the role of the detergent and the role of the solvent for the detergent. A detailed analysis of the liquid environment and its effect on the ESCR of LDPE and HDPE resins showed several important effects [17, 27, 30, 41, 52, 60].

Figure 6.12 compares schematically the crack propagation phenomena in an HDPE resin in three different environments: air, water, and 10% water solution of Igepal CO-630 [27]. The dependence between the stress and the speed of crack propagation measured in the air test shows the complex fatigue behavior typical for HDPE resins in general (Section 6.3.2). The cracks start to grow at a certain finite stress level. Initially, even a small increase of the stress leads to a rapid increase of the crack propagation rate but the acceleration of the crack propagation becomes less pronounced at high stresses. The behavior of the same HDPE resin in the water environment is mostly the same as in air, that is, water is not an effective sensitizing agent. An introduction of the detergent changes several features of the dependence between the stress and the crack growth rate:

1. The minimum stress required for the crack to start growing decreases about twofold.
2. A new stage in the crack propagation process becomes apparent: when the stress reaches a certain level, the speed of the crack growth does not depend on the stress.
3. The environmental stress cracking phenomena manifest themselves at relatively low stresses. The specific effect of a detergent disappears in the high-stress range of the curve in Figure 6.12 but this range (the range of a very short time-to-failure) is of little concern under the real-life conditions.
4. A very large difference exists in the speed of crack propagation between solutions of Igepal CO-630 in different solvents (Figure 6.13).

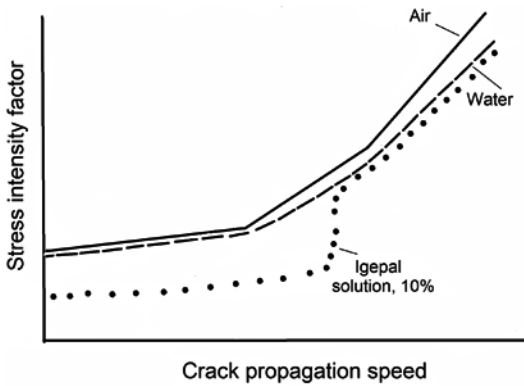


Figure 6.12

Crack propagation speed in HDPE sample in three environments; data from [30]

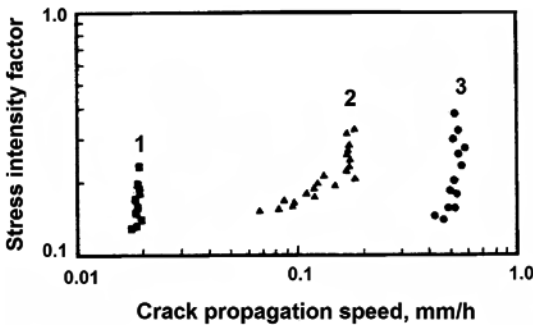


Figure 6.13

Environment effect on crack propagation speed in HDPE resin; data from [30]. Solvents for Igepal CO-630: (1) ethanol, (2) ethylene glycol, and (3)

water

The ESCR of polyethylene resins strongly depends on the concentration of a detergent in water (Igepal CO-630 in this case) [63, 64]. The largest reduction in the time-to-failure occurs at a low detergent concentration of $\leq 0.1\%$. An additional increase of the detergent concentration up to ~ 20 to 25% leads to a relatively small incremental reduction of the time-to-failure; the effect is minimal when the detergent concentration reaches 50% , and a further increase of the detergent concentration from 50 to 100% does not produce any effect at all.

Index

A

- Active center *9–11, 13*
- Additivity rules, for viscosity *53, 57*

B

- Bimetallic catalysts *6, 22, 65*
- Bimodal resin *10, 22, 24*
- Bimodal resins *65*
- Blocks, in copolymers *25, 77, 93*
- Branches
 - long-chain *2, 13, 46, 68, 69*
 - short-chain *1*
- Branching degree *2*
- Breaking point, stress and strain *36, 102*
- Burst test, dynamic, for pipes and tubing *136*

C

- Capillary, melt flow through *46*
- Catalysts, effects on resin properties
 - bimetallic *6, 23, 65*
 - chromium oxide *5, 7, 21, 22, 29*
 - metallocene *6, 8, 18, 31*
 - Ziegler-Natta *4, 6, 20, 21, 28, 62, 65*
- Chain orientation *103, 104, 128*
- Chain propagation reactions *10*
- Chain transfer (termination) reactions *11*
- Chromium-containing catalysts *5*
- Classification, of polyethylene resins *4*
- Compositional uniformity *27, 28*
- Copolymer chain statistics *25*
- Copolymerization reactions *12*

CRYSTAF *27–30*

- Crystal forms of polyethylene *32, 95*
- Crystallinity degree
 - definition *93*
 - effect of copolymer composition *94*
 - measurement methods *91*

D

- Dart impact strength of LLDPE film
 - definition *105*
 - measurement *105*
 - model *108, 110*
 - of ethylene copolymers *115*
- Density-gradient columns *95*
- Density of polyethylene resins
 - effect of copolymer composition *97*
 - measurement methods *95*
 - use in classification *2, 4*
- Differential scanning calorimetry (DSC)
 - 71, 91*
- Distribution of monomer units in copolymers *25*

E

- Effective viscosity, additivity rules *53, 55*
- Environmental stress cracking resistance (ESCR)
 - definition *147, 152*
 - effect of density *150*
 - effect of molecular weight *148*
 - measurement methods *146*
 - mechanism *150, 152, 153, 156*

F

- Failure, low-stress 140, 142–144
- Flory-Schulz molecular weight distribution 16, 18

G

- Gas-phase polymerization technology 8
- Gel permeation chromatography (GPC) 15

H

- Haze 166
- Hazemeter 166
- Heat of fusion of polyethylene 92
- Hydrogen, chain transfer agent 11

I

- Infrared spectroscopy 32, 93, 104, 107

L

- Lamella 32, 33
- LLDPE film
 - blocking 164
 - end-use testing 159
- LLDPE resins
 - extractables and solubles 161
- Long-chain branching 2, 13, 46
- Low density polyethylene (LDPE) 3, 9
- Low-stress failure 140

M

- Melt flow rate 44, 50
- Melt flow ratio, definition 46
- Melt index 2, 44
 - definition 43, 44
 - of Newtonian liquid 50
 - of non-Newtonian liquid 51
 - of polyethylene resins 58, 64, 66, 68
 - polyethylene resins 46, 59

Melt Index 43

Melting curve, model

- HDPE 72–74
 - LLDPE 76, 77, 79, 81–83
- Melting points
- of ethylene copolymers 77
 - of linear polyethylene (HDPE) 72–74

Metallocene catalysts 6, 18, 19

- GPC analysis 18

Methylalumoxane (MAO) 6

Modeling

- dart impact test 107–109
- Elmendorf tear test 123, 124, 126
- top load test 136

Modelling

- Elmendorf tear test 122

Molecular weight distributions

- GPC analysis 16
- theory 14

Molecular weights of polyethylene resins 12, 13

- control with hydrogen 11
- measurement methods 15

Monodisperse polyethylene 45, 51, 52

Morphology, of polyethylene resins 31

N

- Necking stage, stress and strain 36, 102
- Newtonian liquid 46, 50, 52
- Nomenclature, of polyethylene resins 3
- Non-Newtonian liquid 46, 48, 51, 55
- Nuclear magnetic resonance (NMR) 91

O

Orthorhombic cell 31, 96

P

- PEX 139
- Pipes, testing 140
- Plastomers 3, 83
- Polyethylene film
 - haze 166

Polyethylene resins

- applications 4
- bimodal 22, 65, 68
- branching degree 2
- classification 2, 4
- compositionally nonuniform 30, 113-115
- compositionally uniform 27, 28
- definition 1
- morphology 31
- multi-Flory 17, 19, 21, 23, 57, 58
- nomenclature 3
- single-Flory 18, 59, 60

Polymerization degree 15

Polymerization rate 11

Polymerization reactors

- gas-phase 7, 8
- slurry (particle-type) 7
- solution 8, 9

Polymorphism of polyethylene 32, 96

Pseudo-monoclinic cell 32, 96

R

Radical reactions

- cross-linking 139
- polymerization 7, 9

S

Secant modulus 35, 139

Shear strain, definition 49

Shear stress, definition 49

Slurry polymerization technology 7, 9

Spherulite 33-35

Statistics of copolymer chains 25

Stress-strain curve 35

T

Tear strength of LLDPE film

- model 122, 124, 126, 127

Top load test, for containers

- measurement 135
- model 137

TREF 27, 28

U

Uniformity, compositional 27, 30

V

Viscosity

- definition 49
- effective 55
- zero-shear 47

X

X-ray spectroscopy 32, 91

Y

Yield stress and strain 35, 102

Young's modulus 35, 112, 137, 138

Z

Zero-shear viscosity

- additivity rules 53, 55
- definition 47