


# HANSER

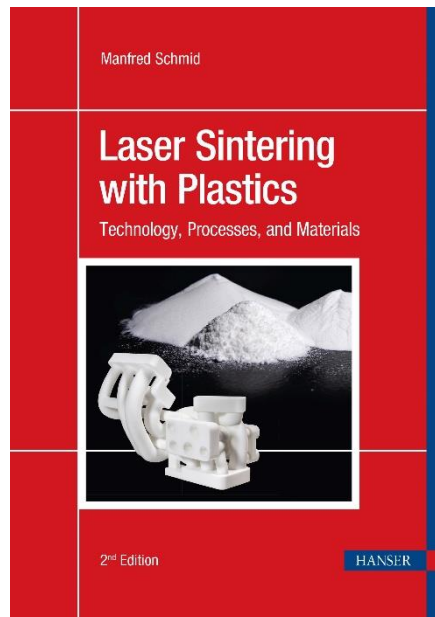

## Sample Pages

### Laser Sintering with Plastics

Manfred Schmid

Print-ISBN: 978-1-56990-921-8

E-Book-ISBN: 978-1-56990-929-4

E-Pub-ISBN: 978-1-56990-337-7

**For further information and order see**

[www.hanserpublications.com](http://www.hanserpublications.com) (in the Americas)

[www.hanser-fachbuch.de](http://www.hanser-fachbuch.de) (outside the Americas)

© Carl Hanser Verlag, München

# The Author



Dr. Manfred Schmid began his professional career as an apprentice laboratory assistant at Metzeler Kautschuk AG in Munich. After graduation, his education continued through his studies in chemistry at the University of Bayreuth, resulting in a Ph.D. in Macromolecular Chemistry, during which he worked with liquid-crystalline polyurethanes under the guidance of Prof. Dr. C. D. Eisenbach.

After graduation, he moved to Switzerland, where he continued for 17 years through different positions in industry in the areas of polymer research and production, as well as material testing and polymer analysis. Polyamides and biopolymers were the focus of a variety of different activities carried out during that time.

Since then, for more than 15 years, he has led the research in laser sintering (LS) at Inspire AG, the Swiss Competence Center for Manufacturing Techniques. This acts as a transfer institute between universities and the Swiss machine-, electro-, and metal (MEM) industries.

The focus of his current activities is on new polymer systems for the LS process, the analytical evaluation of LS powders with regard to their specific property profiles, and LS process development. He supervises several collaborators and has led a wide variety of research projects in this environment. A number of frequently cited original publications have resulted.

As a guest lecturer, Dr. Schmid has given alternating lectures on the Material Science of Plastics, the Processing of Polymers, and 3D-Printing at two Swiss institutions – the Interstate University of Applied Sciences Buchs and the University of Applied Sciences St. Gallen.

The idea for this book arose from several training courses held at Inspire AG on behalf of large industrial companies on the subject of “Additive Manufacturing”.

*Acknowledgement:* The author would like to express his sincere thanks to Ms. Gabriele Fruhmann for preparing individual sections of the book, especially on the main topics of industrial integration of LS technology (Section 3.2) and polyamide 11 (PA 11) (Section 6.1.2), as well as for her many valuable comments on the revision of the entire text. Without her support and highly valued contributions, this second edition of the book on laser sintering of plastics in its present form would not have been achieved.

### **Gabriele Fruhmann**



Gabriele Fruhmann studied mechatronics at the Technical University of Graz after a technical baccalaureate in Computer Science. After graduating, she joined the industry at Magna Steyr Fahrzeugtechnik in Graz in the area of multi-body dynamics simulation. She then moved to ZF Friedrichshafen AG to work in pre-development with a focus on fiber-reinforced polymer materials.

In 2013, she moved to the materials department at BMW AG, where she was responsible for pre-development projects. As part of her work, she began to focus more on additive manufacturing in 2014, and in 2017 she started to work in greater depth on material specifications for the feedstock materials used in laser sintering (LS), and the properties of the part following processing.

After an internal move in 2022 to the area of simulation, her current focus is on material model selection, material characterization, and material card generation for polymer materials in structural simulation, as well as on mapping the results from different process simulations to structural simulation in terms of material properties in the part.

The collaboration on the book came about because of Ms. Fruhmann's collaboration with Dr. Schmid on a joint project, and because of her appreciation to him for the first edition of this book, which helped her to gain an understanding of laser sintering in a short time-frame.



# Foreword

## Foreword to the first edition

The history of additive manufacturing seems to be very short on a first view, but in reality the technology is more than a hundred years old. The first patent application was in 1882 by J. E. Blather, who registered a method for producing topographical contour maps by cutting wax sheets, which were then stacked.

This is an amazing fact: layer-by-layer work processes are currently experiencing a huge amount of hype, which was not triggered by the development of new basic technologies. The background is rather that essential patents have expired, making it possible to recreate for example a melt deposition method using the simplest means, which can be used for the generation of three-dimensional bodies. This hype was created in a very short time, and it developed due to considerable inherent dynamics. The decentralization of users and the new degrees of freedom offered by the technologies coincide with the present boom of DIY (do it yourself) culture, so it is not surprising that “Fabber” and “3D printing selfies” are highly demanded.

Conversely, various new technologies were developed over the entire process chain as well. During my studies in the early 2000s, when I dealt with the topic for the first time, the importance of layer manufacturing was high only in the area of prototyping. The technologies have not changed radically since then, but nowadays the market for custom products and small production runs in many industries has increased massively. Consequently, both established machine manufacturers and many innovative startups have grown in this field. The additive manufacturing process has found immeasurable use today, from the production of individual toys to high-power components for powertrains. In the future, different scenarios for production are possible, and decentralized production “on demand” is tangible. This generates a field of high technological expectations with risks and potentials. A realistic estimation should be independent of the enthusiasm that is noticeable after seeing the first additive manu-

facturing process and having the generated part in one's hand. Independent research on the topic is therefore essential.

BMW AG ordered the first SLA system in 1989. Thus, BMW AG was the first customer of a today world recognized and leading company for laser sintering systems. Over the years, Research and Innovation Center (FIZ) formed a model for a Competency Center in which various practical and basic research is carried out today. In addition to high quality prototypes for testing and validation of transportation vehicles, materials and processes are being developed, making it possible to realize the potential of layer-by-layer construction. For example, employees working in the automotive production are individually equipped with personalized assembly aids to increase ergonomics and performance in assembly lines.

In this case, the focus of the discussion will be less on the 3D printing processes mentioned in the media, but rather on the highly complex manufacturing machines on which the production is to take place in the future. One such technology is selective laser sintering (SLS), a laser-based unpressurized manufacturing process. However, the coincidence with a "real" sintering process, is solely that the generated part cross-section will be held near its melting temperature for a long residence time. This is the core process of laser sintering, which is already examined in diverse ways and is still subject of intensive further research.

When I dealt with my own Ph.D. thesis about the time and temperature dependence of the two-phase region, in which melt and solid are present synchronous, I had the chance to enter into one of the many interdisciplinary fields of research on additive manufacturing, and I am still excited about this topic. Anyone who intends to work with laser sintering will not be able to find a lot about such specialized topics in most of the general books for 3D printing and additive manufacturing. Because powder bed based technologies are established as one of the major additive manufacturing processes, it is essential also to present the results of basic research and transfer it to practical use in order to create, for example, as a service provider, viable high quality parts. The purpose of this book by Manfred Schmid, one of the recognized specialists in laser sintering, is precisely to give this depth of field without losing the benefits to the user.

May 2015

*Dr.-Ing. Dominik Rietzel*

### Foreword to the second edition

In the last decade, laser sintering has gained a leading role among processes for additive manufacturing or (as it is often more figuratively expressed) 3D printing. This applies to both metals and plastics, which are the focus of this book.

On the one hand, laser sintering produces components whose properties are closest to those of “classic” thermoplastic processing. On the other hand, as a process without any kind of support structures, it offers the ideal conditions for almost limitless free component design, and thus supports the turn from tool-bound design to function-driven design of a component. This freedom of design is increasingly finding its way into industrial production for specialized components with a high degree of functional integration or a high degree of customization, right down to the individual piece.

One example of function integration is the production of gripper systems, where up to 100 individual parts such as valves, springs, hoses, and the gripper tools can be integrated into a single laser-sintered component. As well as eliminating assembly, the tool manufactured in this way weighs only a fraction of the conventional tool, and thus enables a significant reduction in costs in the life cycle of the component, because the gripper can move faster and simultaneously use less energy. The high degree of customization that is possible is also put to use, in particular for applications involving people, be it the production of customized orthoses and prostheses, or drilling templates for operations. But it doesn't always have to be high-tech medicine; the production of laser-sintered insoles is already a reality today.

The first edition of the book *Laser Sintering with Plastics: Technology, Processes, and Materials* has become the standard volume for system and material manufacturers, users, and researchers. This is because even a newcomer to the field of additive manufacturing will find it easy to get started, and because of the depth of detail and technical precision with which Manfred Schmid manages to explain the highly complex interplay of materials and processes, which take place on completely different timescales than any other process used in the plastics industry. These long timescales also result in particular strains on the materials, and this challenge is one of the reasons why the choice of different plastics is still limited, even after 30 years of laser sintering. To overcome this problem, the chemical industry is working hard on adapted plastics, and system manufacturers are accelerating processes, for example by using many laser sources simultaneously.

May this second edition be as helpful, educational, and exciting a read as the first edition to a new generation of technicians working in the field of laser sintering of plastics, and give new impetus to veterans of this technology such as myself.

August 2022

*Dipl.-Phys. Peter Keller*



# Contents

<b>The Author</b> .....	<b>V</b>
<b>Foreword</b> .....	<b>VII</b>
<b>1 Introduction</b> .....	<b>1</b>
1.1 Manufacturing Technology .....	1
1.2 Additive Manufacturing .....	2
1.2.1 Application Areas and Technology Drivers .....	3
1.2.2 Main Groups of Additive Manufacturing .....	5
1.3 Additive Manufacturing with Plastics .....	7
1.3.1 Vat Photopolymerization (VPP) .....	7
1.3.2 Material Extrusion (MEX) .....	9
1.3.3 Material Jetting Technology (MJT) .....	12
1.3.4 Powder Bed Fusion (PBF) .....	13
1.3.5 Comparison of AM Processes for Plastics .....	17
1.4 Laser Sintering (LS) with Plastics .....	19
<b>2 Laser Sintering Technology</b> .....	<b>23</b>
2.1 Machine Technology .....	25
2.1.1 Machine Configuration .....	25
2.1.2 Temperature Control .....	28
2.1.2.1 Heat Sources .....	29
2.1.2.2 Surface Temperature at the Build Area .....	30
2.1.2.3 Laser Energy Input, Andrew Number ( $A_N$ ) .....	31



2.1.3	Powder Supply and Powder Application . . . . .	33
2.1.3.1	Internal and External Powder Supply . . . . .	33
2.1.3.2	Powder State (Conditioning) . . . . .	34
2.1.4	Powder Application . . . . .	34
2.1.4.1	Blade and Powder Cartridge . . . . .	35
2.1.4.2	Roll Coater . . . . .	37
2.1.4.3	Combined Coating Systems . . . . .	38
2.1.5	Optical Components . . . . .	39
2.1.5.1	Laser Beam Positioning . . . . .	39
2.1.5.2	Focus Correction . . . . .	40
2.2	Machine Market . . . . .	41
2.2.1	Industrial Laser Sintering Equipment . . . . .	41
2.2.1.1	Company: Electro Optical Systems, EOS (Germany) . . . . .	43
2.2.1.2	Company: 3D Systems (USA) . . . . .	44
2.2.1.3	Company: Farsoon Technologies (China) . . . . .	44
2.2.1.4	Other Manufacturers of LS Equipment . . . . .	45
2.2.2	Pilot Plant and Research & Development Facilities . . . . .	48
2.2.2.1	R&D Plants with CO <sub>2</sub> Lasers . . . . .	49
2.2.2.2	R&D Systems with Laser Diodes . . . . .	49
<b>3</b>	<b>The Laser Sintering Process . . . . .</b>	<b>53</b>
3.1	Process Chain . . . . .	54
3.1.1	Powder Supply . . . . .	54
3.1.2	Data Preparation and Build Job . . . . .	56
3.1.3	Build Process . . . . .	58
3.1.3.1	Heating Up . . . . .	58
3.1.3.2	Process Flow . . . . .	59
3.1.3.3	Parts and Building Chamber Parameters . . . . .	63
3.1.3.4	Exposure Strategy . . . . .	63
3.1.3.5	Cooling and Unpacking . . . . .	65
3.1.4	Process Error . . . . .	66
3.1.4.1	Deformation of the Parts . . . . .	67
3.1.4.2	Surface Defects: Orange Peel . . . . .	68
3.1.4.3	Other Process Errors . . . . .	69

3.2	Qualification for Industrial Series Production.....	71
3.2.1	Product-Related Processes.....	74
3.2.1.1	Pre-Process.....	76
3.2.1.2	In-Process.....	81
3.2.1.3	Post-Process.....	83
3.2.1.4	Process Validation.....	84
3.2.2	Functional Processes.....	85
3.2.2.1	Feedstock Management.....	85
3.2.2.2	Qualification of the Laser Sintering Machine.....	89
3.2.2.3	Qualification of the Laser Sintering Process.....	93
3.2.3	Status of Standardization.....	94
<b>4</b>	<b>Laser Sintering Materials: Polymer Properties.....</b>	<b>103</b>
4.1	Polymers.....	103
4.1.1	Polymerization.....	104
4.1.2	Chemical Structure (Morphology).....	106
4.1.3	Thermal Behavior.....	107
4.1.4	Polymer Processing.....	108
4.1.5	Viscosity and Molecular Weight.....	109
4.2	Key Properties of LS Polymers.....	111
4.2.1	Thermal Properties.....	112
4.2.1.1	Crystallization and Melting (Sintering Window).....	113
4.2.1.2	Heat Capacity ( $c_p$ ) and Enthalpy ( $\Delta H_c$ , $\Delta H_m$ ).....	118
4.2.1.3	Thermal Conductivity and Thermal Radiation.....	118
4.2.1.4	Modeling of the Processes in the Sintering Window.....	120
4.2.2	Rheology of the Polymer Melt.....	122
4.2.2.1	Melt Viscosity.....	122
4.2.2.2	Surface Tension.....	127
4.2.3	Optical Properties.....	129
4.2.3.1	Absorption.....	130
4.2.3.2	Transmission and (Diffuse) Reflection.....	131
<b>5</b>	<b>Laser Sintering Materials: Polymer Powder.....</b>	<b>135</b>
5.1	Powder Production for Laser Sintering.....	136
5.1.1	Emulsion, Suspension, and Solution Polymerization.....	136

5.1.2	Precipitation from Solutions	137
5.1.3	Grinding and Mechanical Comminution	138
5.1.4	Melt Emulsification	139
5.1.5	Laser Sintering Powder Production at a Glance	139
5.1.6	Other Powder Manufacturing Processes	141
5.2	Powder Properties for Laser Sintering	143
5.2.1	Powder Density	144
5.2.1.1	Particle Shape and Surface	146
5.2.1.2	Particle Size Distribution (Number and Volume Distribution)	149
5.2.2	Powder Rheology	152
5.2.3	Measurement of Powder Flowability	154
5.2.3.1	Hausner Ratio ( $H_R$ )	155
5.2.3.2	Rotating Powder Analysis	158
5.2.3.3	Flow Agents	160
<b>6</b>	<b>Laser Sintering Materials: Commercial Materials</b>	<b>163</b>
6.1	Polyamide (Nylon)	167
6.1.1	Polyamide 12 (PA 12)	169
6.1.1.1	Particle Size Distribution and Particle Form	170
6.1.1.2	Thermal Properties	172
6.1.1.3	Crystal Structure	177
6.1.1.4	Molecular Weight and Post-Condensation	180
6.1.1.5	Powder Aging	184
6.1.1.6	Property Combination of PA 12	185
6.1.2	Polyamide 11 (PA 11)	187
6.1.3	Comparison of PA 12 and PA 11	193
6.1.4	Compound Materials of PA 12 and PA 11	195
6.1.5	Flame-Retardant Materials Based on PA 12 and PA 11	198
6.1.6	Other Polyamides (PA 6, PA 613, PA 1212)	199
6.2	Other Laser Sintering Polymers	202
6.2.1	Thermoplastic Elastomers (TPU, TPA, TPC)	202
6.2.2	High-Performance Polymers (PAEK, PPS)	204
6.2.3	Polyolefins (PP, PE)	207
6.2.4	Polyesters (PBT, PET)	208
6.2.5	Thermosets	209

<b>7</b>	<b>Laser-Sintered Parts</b> .....	<b>213</b>
7.1	Component Properties .....	214
7.1.1	Mechanical Properties .....	214
7.1.1.1	Short-Term Loading: Tensile Test .....	215
7.1.1.2	Laser Sintering Parameters .....	217
7.1.1.3	Component Density .....	218
7.1.1.4	Partial Melting (DoPM) .....	220
7.1.1.5	Anisotropy of Component Properties .....	223
7.1.1.6	Long-Term Resistance .....	226
7.1.2	Component Surfaces .....	227
7.1.2.1	Influencing Parameters .....	227
7.1.2.2	Roughness Determination .....	228
7.1.2.3	Surface Processing .....	229
7.1.2.4	Finishing .....	231
7.2	Applications and Examples .....	233
7.2.1	Prototype Construction and Small Series .....	235
7.2.2	Function Integration .....	236
7.2.3	Part List Reduction .....	238
7.2.4	Individualization and Personalization .....	240
7.2.5	Business Models and Outlook .....	242
	<b>Index</b> .....	<b>245</b>



# 1

# Introduction

## 1.1 Manufacturing Technology

Manufacturing, or production, is the process by which parts, goods, or merchandise, commonly called products, are produced. In the manufacturing process, these products are obtained from other parts (semi-finished products) or created from raw materials. Manufacturing can be manual, mechanical, or mixed (hybrid) processes. The various production technologies are dealt with in the subject area of manufacturing technology [1].

According to German DIN Standard 8580, manufacturing processes are divided into six main groups:

- **Prototyping:** A solid body is created from shapeless materials (liquid, powdery, plastic); the cohesion is created e. g. by casting, sintering, firing, or bonding.
- **Forming:** Changing the shape of a body by pictorial (plastic) alteration without changing the amount of material (e. g. bending, drawing, pressing, or rolling).
- **Joining:** Previously separated work pieces are transferred into a permanent joint (e. g. bonding, welding, or soldering).
- **Cutting:** Change in the shape of a solid body; the cohesion is locally dissolved (typically ablative processes such as grinding or milling).
- **Coating:** Surface finishing of all kinds (e. g. painting, chrome plating, etc.).
- **Changing material properties:** Conversion by post-treatment (e. g. hardening).

Additive manufacturing processes, in which materials are joined layer by layer to form new components, can be clearly assigned to the primary forming processes, and have accordingly been integrated into section 1.10 of the latest draft of DIN 8580 (2020).

## 1.2 Additive Manufacturing

Additive manufacturing technologies have long been known in industry under the term “rapid prototyping”. Rapid prototyping is widely used in model making and product development in many branches of industry. The predominant goal is the fast and uncomplicated production of individual parts, small component series, or functional and design samples to shorten development cycles.

This approach – long known to industry experts – came into the public eye a few years ago, following media hype over “3D printing”. This often gave the impression that 3D printing could be regarded as a universal and disruptive manufacturing process that would completely replace other manufacturing technologies. According to current estimates, however, it is more likely that additive manufacturing is simply joining the large number of diverse manufacturing technologies used in industry, and will only be used if clear cost advantages can be achieved from its application [2].

In the context of this book, the term additive manufacturing is generally used to indicate that the focus is on the production of industrial components. This does not represent a devaluation of rapid prototyping or 3D printing, which enjoy a high degree of importance in their respective fields of application. The terms additive manufacturing and 3D printing are often used synonymously, and a clear demarcation is not always possible.

Other partly historical terms that are (or were) used synonymously for additive manufacturing are: generative manufacturing, eManufacturing, additive manufacturing, additive layer manufacturing, direct digital manufacturing (DDM), solid-state free-form manufacturing, and some others. In addition, everything is often still subsumed under the term 3D printing, especially in the non-scientific literature. In the meantime, however, the term additive manufacturing has become generally accepted and is defined by the current standardization.



**DIN EN ISO/ASTM 52.900** *Additive Manufacturing – Fundamentals – Terminology* is the basic terminology standard for additive manufacturing (AM). The standard defines the most important terms in this context. For example, additive manufacturing itself is defined as:

### **A definition of additive manufacturing**

“Process of joining materials to produce components from 3D model data usually layer by layer, as opposed to subtractive and forming manufacturing methods”

Processes in additive manufacturing therefore take place layer by layer, which is why they are sometimes referred to as layer construction processes. This definition defines the layer-by-layer construction of objects through additive manufacturing. The

geometry of the component is available as an electronic data set in the computer (3D model data), which directly controls the creation of the component (direct digital manufacturing, DDM). This clearly distinguishes it from subtractive, machining, or separating processes.

In additive manufacturing, the final properties of the components are generally only created during production. The process parameters used control the final properties of the components, in close interaction with the properties of the starting materials. This is one of the main differences between additive manufacturing and traditional, ablative separation processes, in which the component properties are already largely predetermined by the original material properties of the semi-finished product before shaping.

Because additive manufacturing creates components layer by layer, in two dimensions so to speak, the complexity of the parts in the third dimension plays a subordinate role during the creation process. Components of almost any complexity can thus be created during the manufacturing process without significant additional effort. Areas of application that require highly complex components are therefore particularly predestined for additive manufacturing, and can be regarded as one of the technology drivers.

### 1.2.1 Application Areas and Technology Drivers

AM processes have one outstanding feature in common: they do not require the use of a mold that determines the shape of the desired component. Because of this layer-by-layer shaping without tools, the approach has many advantages that make it particularly suitable for the following areas of application, and which can be regarded as the main drivers of AM technology:

- Economic production of small numbers of components (even with a batch size of one, “on demand”)
- Geometric freedom in design (free-form surfaces, undercuts, cavities)
- Components with function integration (hinges, joints, flexible units)
- Lightweight construction (lattice structures with high or varying stiffness)
- Product personalization (medical technology, sports)
- Short-term product adjustments (shortening of product cycles)
- Environmental aspects (reduced material consumption, circular economy)
- Bionic structures.


Typical industries in which the advantages of additive manufacturing can be very well applied and targeted are the consumer goods, automotive, aerospace technology,



defense, medical technology, electronics, furniture, jewelry, sports equipment, and tool and mold making.

Some current established business models (personalized drilling jigs for operations, individual prosthetics, complex furniture gliders, novel filter systems, robotic grippers) demonstrate the economic use of AM technologies that have already emerged.

Figure 1.1 shows schematically in what way additive manufacturing is superior to traditional production methods from an economic point of view.

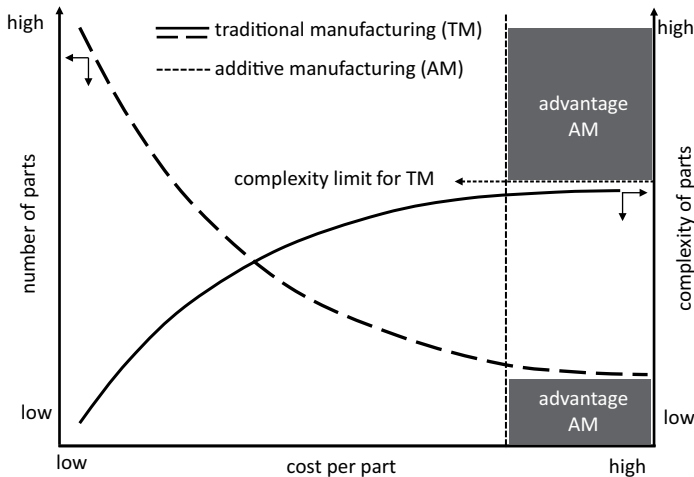

**Figure 1.1** Unit costs in conflict with part count and part complexity for additive and traditional manufacturing; AM is typically not economically viable for mass production of simple parts

Established or traditional manufacturing technologies (TMs) are often optimized to produce large numbers of components at the lowest possible unit costs. Here, the unit costs decrease significantly with the number of parts produced (Figure 1.1, dashed line). At the same time, with TE, the unit costs increase significantly with the component complexity. In general, a complexity limit is even reached which conventional processes cannot overcome, or often only by generating exorbitantly high costs (Figure 1.1, solid line).

This is where the advantages of additive manufacturing processes (dark grey areas in Figure 1.1) come into play. At almost unchanged costs either small component series or components with considerable complexity can be manufactured. However, this also requires the design of the components to be adapted for the additive processes. The part design is changing from one that is required for a *production process* into one that is required for *part functionality*! This paradigm shift does not mean, however, that production-oriented rules can be disregarded. Experience shows clearly

that it is also important to design for production in additive manufacturing. Compared to tool-related manufacturing processes, however, different rules apply, which allow considerably higher degrees of freedom in product design.

However, the adaptations in the part design for additive manufacturing intervene in the complete process chain of manufacturing. In product development projects, it is therefore imperative that the planned manufacturing process be integrated at the beginning of the project, in order to take advantage of the benefits offered by additive processes for part manufacturing [3].

The target-oriented and demand-driven application of additive manufacturing requires a good overview and comprehensive knowledge of the different AM processes, and their respective strengths and weaknesses. In addition, the AM processes are mostly tied to specific material classes. In addition to the shape and type of the starting materials, AM processes differ quite significantly in terms of the underlying process sequences, according to which the classification by main AM groups is made today.

## 1.2.2 Main Groups of Additive Manufacturing

With the progressing standardization in the field of additive manufacturing (see Section 3.2.5), seven main groups are currently defined as essential process categories of additive manufacturing.

The main process categories (I–VII) often contain further subgroups, which may differ to a greater or lesser extent in process details. In the case of powder bed fusion (PBF) processes in particular, it is also useful to distinguish between plastic processes (PBF-P) and metal processes (PBF-M).

### I. Vat photopolymerization (VPP)

- SLA: Stereolithography
- DLP: Digital light processing
- CDLP: Continuous digital light processing
- CLIP: Continuous liquid interface production

### II. Material extrusion (MEX)

- FFF: Fused filament fabrication
- FGF: Fused granulate fabrication
- APF: Arburg plastics freeforming

### III. Material jetting technology (MJT)

- MJ: Material jetting
- DoD: Drop on demand

### IV. Binder jetting technology (BJT)

## V. Powder bed fusion (PBF)


- Polymers
  - PBF-LB/P: Laser-based melting (laser sintering (LS))
  - PBF-IR/P: Infrared-radiation-based melting (MJF, SAF, HSS)
- Metals
  - PBF-LB/M: Laser-beam-based melting (selective laser melting (SLM))
  - PBF-EB/M: Electron-beam-based melting (EBM)

## VI. Directed energy deposition (DED)

- LENS: Laser-engineered net shaping
- EBAM: Electron beam additive manufacturing

## VII. Sheet lamination (SHL)

Figure 1.2 shows a graphical overview of the processes in the seven main classes. The processes that work mainly with plastics as the starting material are located in the upper part of the diagram. The metal processes are grouped underneath. Sheet lamination (SHL) and binder jetting (BJT) at the end cannot be clearly assigned to metal or plastic processes. In BJT in particular, a wide variety of powder substrates can be used in principle. Even chocolate powder has already been processed into “components” using BJT.

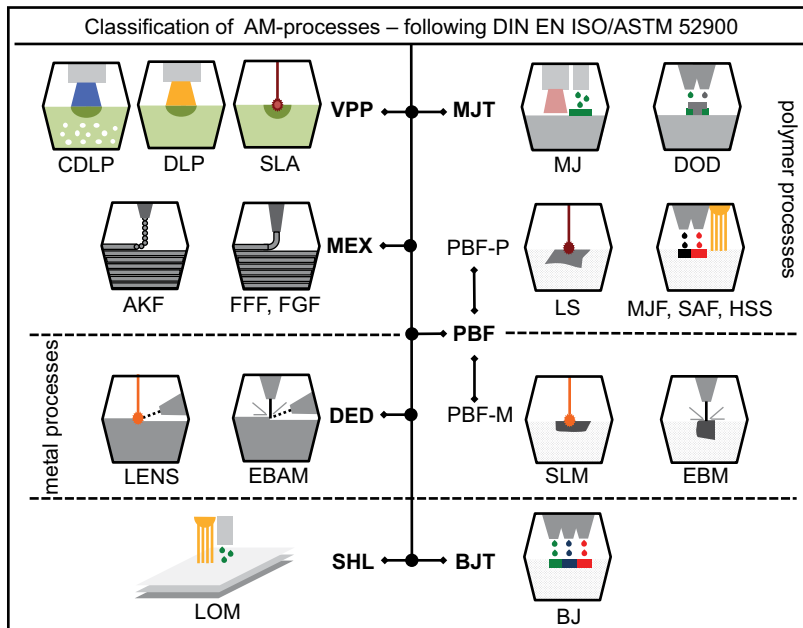

**Figure 1.2** Overview of the main process classes of additive manufacturing based on DIN EN ISO/ASTM 52.900; the AM processes mainly used in the field of plastics are summarized in the upper half

In general, the classification into main categories is essentially made with regard to the differences in the joining of the respective substrates, and less consideration is given to material classes. This results from the fact that different materials such as polymers, metals, ceramics, and composites can frequently be processed with the same process approach.

Depending on whether an AM process leads directly to the finished component or via a “green part” as an intermediate step, a further distinction can be made between direct and indirect AM processes or single-stage or multi-stage processes. Plastics and metals are still to be considered the main material classes employed for additive manufacturing when it comes to the **direct AM processes** used to produce final components for industrial use.

In **indirect AM processes**, which mainly comprise binder jetting (BJ) on a wide variety of substrates, processing pre-polymers in photopolymerization processes (VPP, MJT), and compound processing in MEX processes, final components are obtained via the detour of a “green part”. Ceramics, inorganic materials, fiber composites, and other “composites” are also accessible. Here, polymers or corresponding precursors are often also used as green part binders.

In general, however, plastics in a wide variety of starting forms are still the dominant class of materials in the additive manufacturing of industrial components and in 3D printing [4]. A comprehensive overview of all AM processes with plastics and the companies currently involved in the individual process fields can be found on the AMPOWER homepage [5].

## 1.3 Additive Manufacturing with Plastics

What started about 40 years ago with the first work of Chuck Hull on stereolithography has today developed into a broadly diversified technology spectrum with a wide variety of plastic-based additive processes. The main AM processes in which plastics play a central role for the direct manufacture of AM components (see Figure 2.1) are:

- Vat photopolymerization (VPP)
- Material extrusion (MEX)
- Material jetting technology (MJT)
- Powder bed fusion with polymers (PBF-P).

### 1.3.1 Vat Photopolymerization (VPP)

The processes summarized under vat photopolymerization (VPP), stereolithography (SLA), digital light processing (DLP), and continuous digital light processing (CDLP) are based on the use of high-energy radiation (UV or visible light) for the production


of AM components. This can be done either selectively by a UV laser (SLA) or via planar exposure via projectors (DLP/CDLP) [6].

Where the high-energy radiation hits the substrate (a liquid/viscous photopolymer resin), polymerization is started and spatially resolved curing of the material is induced. The resins usually consist of complex mixtures of active epoxy- or methacrylate-based components and so-called hardeners (alcohols and/or amines), and so elastomers or duromers are formed during the printing process. By varying the chemical composition of the individual components, the properties of the resulting components can be varied over a wide range and adapted to the target applications. The actual polymerization is started by an initiator, which breaks down into radicals during UV irradiation and induces a radical chain-reaction.

With VPP, a component is created layer by layer by continuously feeding in new resin layers. The build platform on which the component is created is either gradually lowered into the resin bath or pulled out of it. Because VPP processes use a liquid to create objects, there is no structural support from the material during the build phase. Support structures must therefore be used if the components have overhangs, cavities, or other complex structures.

VPP processes are usually characterized by high component precision and very good component surfaces. The disadvantage is often a pronounced brittleness of the components (duromer) and low long-term stability due to incompletely converted photo-initiators. Post-curing and degradation effects induced by the UV component in sunlight can lead to disintegration of the components. The following list and Figure 1.3 summarize the main features of the individual VPP processes.

### Vat Photopolymerisation (VPP)



#### Stereolithography (SLA)

UV sensitive prepolymers are cured with pinpoint accuracy using a UV laser

Advantages: high precision; very good component surfaces; large components possible

Disadvantages: support structures; slow process; limited long-term stability UV-sensitive



#### Digital Light Processing (DLP)

UV-sensitive prepolymers are cured over the surface with the aid of a projector

Advantages: high precision; good component surfaces; increased process speed

Disadvantages: support structures; limited part dimensions and long-term stability



#### Continuous Digital Light Processing (CDLP / CLIP)

Illumination from below; inhibition of UV curing by addition of oxygen

advantages: high precision; good part surfaces; very high process speed

Disadvantages: support structures; limited part dimensions

**Figure 1.3** Different photopolymerization processes (VPP) for the production of plastic components

### **Stereolithography (SLA)**

In the SLA process, the material is cured in a spatially resolved manner with the aid of a UV-laser. Exposure often takes place from above, with the laser beam being precisely controlled via mirror systems (scanners). This type of exposure makes large component dimensions possible, and components can even be produced in the meter size range with the corresponding SLA printers (e. g. models of dashboard carriers in the automotive sector).

A newer process, which can be assigned to SLA, is “hot lithography” (Cubicure GmbH). Here, the process temperature is raised significantly above room temperature, which enables the processing of novel SLA resins with higher viscosity at room temperature. Improved properties in terms of temperature stability and mechanical properties can be expected from this process.

### **Digital light processing (DLP)**

In DLP, area exposure takes place with projectors. The exposure can be from above as well as from below through a special light, and (if necessary) a base of the resin tank that is gas-permeable. The component dimensions are dictated by the resolution of the projector and are much more limited than with SLA. Therefore, DLP processes are often used for smaller or filigree components, e. g. for casting negatives in the jewelry sector, or lattice-like structures with small local cross-sectional areas.

### **Continuous digital light processing (CDLP)**

CDLP is a variant of the DLP process. This process became very well known as continuous liquid interface production (CLIP) by the company Carbon 3D. Here, the fact that oxygen ( $O_2$ ) acts as a radical scavenger and can specifically inhibit photopolymerization (quenching) is exploited. If, as in the CLIP process, it is possible to control the local inhibition very precisely, a significant increase in the process speed is possible. The components can be generated freely in the photopolymer resin, if the exposure plane and “quenching zone” are very precisely matched. In addition, the polymer resins developed for these processes often have components that can be thermally cured in post-processing steps. This makes the components significantly more stable and suitable for technical applications in long-term use. However, the component dimensions are just as limited as in the DLP process due to the use of projectors and the negative pressure that develops with larger cross-sectional areas.

## **1.3.2 Material Extrusion (MEX)**

In recent years, additive manufacturing by means of material extrusion (MEX) has developed a wide range of applications in terms of both materials and processes [7]. This ranges from simple DIY printers for do-it-yourselfers at home to special pro-

cesses that are suitable for extruding fiber-reinforced concrete and thus for “printing” entire buildings [8, 9].

Very large components, such as body elements for vehicles (e. g. BigRap), can be produced with this process, as can multi-component and continuous fiber-reinforced work pieces (e. g. Markforged). In addition, MEX can also be used to process composite filaments filled with metal and ceramic particles, which can be converted into pure ceramic or metal parts with appropriate post-treatment steps. Further applications of MEX technology also go in the direction of “food printing” [10].

When non-reinforced plastic filaments are used, it is often referred to as fused deposition modeling (with the abbreviation FDM<sup>®</sup> being registered and trademarked by the Stratasys Company for these processes), or more generally fused filament fabrication (FFF).

### **Fused filament fabrication (FFF)**

Plastics are usually wound as filament onto a spool for use in the FFF process and fed through a heated nozzle as they are unwound in the MEX printer. Proper heating above the glass transition point of the polymer causes the filaments to adhere to each other as the strand is deposited, forming a three-dimensional component when properly processed. A subtype of the FFF process is the continuous filament fabrication (CFF) process. Here, continuous fibers, e. g. carbon fibers, are fed in parallel to the FFF printing process via a second print head in order to generate stiff and high-strength components.

Plastics frequently used in the FFF process, such as ABS or PLA, are amorphous and exhibit sufficient toughness and dimensional stability even far above the glass point, so that the production of three-dimensional components is successful. In addition, amorphous materials show hardly any shrinkage during cooling, which increases the dimensional stability of FFF components and avoids process errors such as warpage and detachment from the build platform during construction.

One problem in the FFF process can be poor layer adhesion if the temperature drops too far during the building process and sufficient adhesion between the filament layers no longer exists. In order to improve layer adhesion in FFF components, closed heated build spaces are used, and there are now also approaches to improve adhesion at the interface between the individual filaments through thermally or chemically induced reactions. A distinction is then made between MEX-TRB (thermal reaction bonding, TRB) and MEX-CRB (chemical reaction bonding, CRB).

Many approaches are also being pursued with FFF to be able to process semi-crystalline polymers, such as polyamides (PA), polyester (PET), or also high-temperature materials, such as polyether ether ketone (PEEK), polyetherimide (PEI) or polysulfone (PSU). Applications in medical technology or aircraft construction, for example, promise great potential. Filled or fiber-reinforced filaments can be used to keep volume change during the crystallization process low and to avoid component distortion.

### Fused granulate fabrication (FGF)

Due to the low material throughput in the FFF process, extruder heads have been developed for “printing” large components, which can directly process micro-granules or standard granules of plastics. An additional process step, the production of plastic filaments on spools, is thus eliminated. Filled or fiber-reinforced materials can also be used to advantage in FGF, which is essential for good dimensional stability. Nozzles in the range of 2 to 10 mm diameter are used. However, this results in rough, wavy surfaces that must be converted into smooth surfaces by appropriate post-treatment steps (e. g., by over-milling). Applications for the fast-growing FGF-MEX variant can be found in mold and sports equipment construction as well as in the furniture industry and for large vehicle parts.

### Arburg plastics freeforming (APF)

One MEX variation is the freeform plastic molding (APF) developed by ARBURG. Instead of filaments, small plastic droplets are continuously ejected (extruded) via piezo-controlled nozzles. The material nozzles are positioned in a fixed location, and the building platform on which the components are created can be moved and positioned in three spatial directions. By using several nozzles, different materials can be processed simultaneously, so that combinations of different materials (e. g. hard/soft) can be linked in one component.


The outstanding advantage of the APF approach is that, in principle, standard polymer granulates can be used as the starting materials, which are already available for other plastics processing methods (injection molding, extrusion). The time-consuming and costly intermediate step of filament production is eliminated. In reality, however, the use of standard pellets is often difficult, since these materials contain all kinds of processing aids that can interfere with the APF process.

Likewise, filled materials are almost impossible to process due to the sensitivity of the high-precision extrusion dies. A disadvantage here, as with the other MEX processes, is the relatively slow process speed when building up the parts and the mandatory use of support materials for complex structures. Figure 1.4 summarizes the essential elements of MEX technology for processing plastics.

### Material Extrusion (MEX)



Fused Filament Fabrication (FFF), Fused Granulate Fabrication (FGF)  
Plastics are heated in a nozzle and deposited on top of each other strand by strand  
Advantages: basically simple (DIY) and wide variety of materials  
Disadvantages: wavy part surfaces, support structures; single parts; slow process



Arburg Plastics Freeformer (APF)  
Polymer granules are extruded droplet by droplet via a piezo-controlled nozzle  
Advantages: Polymer pellets from “bar”; multi-material combinations (hard/soft).  
Disadvantages: support structures required; individual parts; build-up rate very slow


**Figure 1.4** Material extrusion process (MEX) for the production of plastic components



### 1.3.3 Material Jetting Technology (MJT)

Direct manufacturing of plastic components is achieved with material jetting (MJ) or drop-on-demand (DOD) technologies (see Figure 1.5). In principle, these are printing processes analogous to traditional 2D inkjet printing. Viscous materials are applied to a build platform from digitally controlled print heads.

#### Material Jetting Technology (MJT)




##### Material Jetting (MJ)

Pre-polymer droplets are deposited with a print head and cured with UV lamp

Advantages: high precision; very good part surfaces; multi-material processing

Disadvantages: support structures; limited long-term stability



##### Drop on Demand (DOD)

Polymers (waxes) are deposited with a print head and thermally cured

Advantages: high precision; good part surfaces; predominant use as cast cores

Disadvantages: support structures; thermally unstable components

**Figure 1.5** Material jetting technologies for the production of plastic components

If the printing materials are UV-curing pre-polymers (see Section 1.3.1, VPP process), curing of the droplets takes place immediately after deposition by UV lamps positioned in the print head (photopolymerization). However, curing after deposition of the droplets can also take place purely thermally by cooling, if low-melting substances such as waxes are involved.

The basic prerequisite for MJT is always a certain viscosity of the pre-polymers, which must be adapted to the high-precision print heads. If this is given, the process is basically well-suited to processing several materials with different property profiles at the same time. The production of components from “gradient material”, i. e. with locally adapted material properties, by adjusting the mixing ratio of the starting materials directly in the printing process, is thus possible. In general, MJ is very versatile and generates components with very low surface roughness and high dimensional accuracy at high speed by precisely controlling material deposition.

Disadvantages of MJ are, as already mentioned in Section 1.3.1 (VPP process) for UV-curing systems:

- A certain brittleness of the components (duromers)
- Low long-term stability (post-curing and degradation effect induced by the UV component in the sunlight).

# Index

## Symbols

3D Systems 25, 44  
3MF 56  
6-aminohexanecarboxylic acid 168  
 $\alpha$ - and  $\gamma$ -forms 177  
 $\alpha$ -triclinic 194  
 $\gamma$ -crystal structure 178

## A

A-A/B-B polyamides 168  
A-B polyamides 168  
absorption coefficient 130  
absorption of radiation 130  
absorption, transmission, and reflection  
  in the melting range 132  
active chain ends 105  
additive manufacturing 2  
adhesion of the coating 183  
Advanced Laser Materials (ALM) 196  
aerospace 242  
agglomeration 153  
AM  
  – standardization activities 95  
  – standards 94  
AMF 56  
amidation 105  
amide group 168

amine group 168  
Andrew number (AN) 31, 63  
anisotropy of component properties 223  
area coverage (solidity, S) 147  
aspect 46  
aspect ratio (AR) 147, 150  
Association of German Engineers (VDI) 95  
ASTM F42 94  
asymmetry 174  
automotive fluids 226  
avalanche angle 159

## B

balling effect 128  
BET method 149  
B. F. Goodrich 163  
blade  
  – double 35  
blade and powder cartridge 35  
blasting with air 66  
blend materials 225  
bonds  
  – chemical 103  
  – covalent 103  
brittle fracture 215

build area  
 – partial melt 70  
 build cavity 29  
 build height in Z-direction 70  
 building chamber parameters 63  
 build job 54, 56  
 build process 58  
 – abortion of 66  
 build residues 54  
 build spaces  
 – cuboid-shaped 223  
 bulk density 156  
 buoyancy 218  
 business models 4, 242

## C

calibration 30  
 caprolactam 168  
 CarbonMide® 225  
 carboxyl group 168  
 cavities 58, 218, 233  
 CEN/TC 438 94  
 chain breaks 184  
 chain growth 105  
 characterization of the surface area 149  
 chemical structure (morphology) 106  
 circularity (C) 147, 150  
 clamping and gripping technology 241  
 coalescence 59  
 – insufficient 108  
 – isothermal 127  
 – of Duraform® PA particles 128  
 coarse particle content 149  
 coating 232  
 cohesive 153  
 color and light fastness 233  
 coloring 232  
 colors 233  
 color saturation 219  
 commercial materials 163  
 commodities 167  
 comparability (sR) 156  
 comparison of PA 12 and PA 11 193  
 complete homogenization 117  
 complexity 4, 233  
 component data 20  
 component density 218  
 component properties 214  
 – direction-dependent 224  
 compound LS materials 195  
 compound materials of PA 12 and PA 11 195  
 computed tomography (CT) 219  
 cone-plate rheometers 122  
 cooling and unpacking 65  
 cooling down of the LS build 118  
 cooling phase 54  
 cooling rates 114  
 correction lens 40  
 cracking 218  
 crack initiators 218  
 creep behavior 226  
 cross-contamination 56  
 crosslinks 103  
 cross-mixing of materials 56  
 cryogenic milling 138  
 crystallinity  
 – degree of 106  
 crystallite size 116  
 crystallization 59, 115  
 – inhomogeneous 65  
 – non-isothermal 115  
 crystallization aids 117  
 crystallization behavior in the LS process 117  
 crystallization enthalpy  $\Delta H_c$  118, 177  
 crystallization kinetics 120  
 crystallization nuclei 220  
 crystallization point  $T_c$  177  
 crystal structure 177  
 curling 67  
 cyclone separator 142

## D

data quality 20  
 decomposition point 107

- deformation of parts 67
  - degree of fracturing of the particles 149
  - degree of particle melted 117
  - dental tooth correction 240
  - DeskTop Manufacturing (DTM) 163
  - determination of the viscosity number 126
  - differential scanning calorimetry (DSC) 113
  - diffuse reflection 131
  - DIN SPEC 96
  - DIN SPEC 17028 98
  - DIN SPEC 17071 99
  - directional orientation of component naming 224
  - disturbance of the molecular order 177
  - DMA 226
  - drilling jigs 4
  - drilling templates 240
  - droplet extrusion 142
  - droplet-matrix morphology 139
  - dry blends 169, 196
  - ductility 194
  - Duraform® HST 197, 225
  - Duraform® PA 169
  - dust particles 26
- E**
- economic production 3
  - effect of vibration 144
  - eGrip 241
  - electrical conductivity 231
  - electronics 243
  - Electro Optical Systems (EOS) 25, 43
  - electrostatic shielding 231
  - elongation at break 116, 182, 194, 225
  - E-modulus 182
  - emulsion polymerization 136
  - end groups 182
  - energy absorption 32
  - engineering polymers 166
  - entangled polymer chains 109
  - enthalpy of fusion 118
  - EOSint P 800 44
  - EOS P 800 206
  - equilibrium reactions 181
  - equilibrium state 34
  - esterification 105
  - ether and keto groups 205
  - exposure
    - strategy 63
    - variation 65
    - vectors 63
  - extrusion conditions 139
- F**
- FAR-25 (25.853) 198
  - Farsoon Technologies 44
  - fibers 169, 196
  - filter systems 4
  - fine dust 56
  - fine particle fraction 153
  - fine particle quantity 171
  - fine particles 152
  - finish 230
  - finishing 66, 231
    - professional 232
  - first-order physical transformations 113
  - flame-retardants
    - based on PA 12 and PA 11 198
    - halogen-containing 198
  - flowing point 107, 108
  - fluidization 36
  - fluidized height 159
  - focal plane 40
  - focus correction 40
  - follow-up rounding of particles 138
  - freedom of design 233
  - free-flowing behavior 154
  - Frenkel and Eshelby model 127
  - fresh powder 30
  - F-Theta lens 40
  - fumed silica 160
  - functional end groups 104
  - function integration 3, 236

**G**

gel formation 185  
 gel permeation chromatography  
 (GPC) 126  
 gel permeation chromatography (GPC)  
 measurements 181  
 GelSight 229  
 geometric freedom 233  
 Gibbs–Thomson equation 179  
 glass beads 169, 196  
 glass transition point 107  
 gravitation 127  
 Grilamid® L20G 173  
 grinding 138  
 gripper fingers 242  
 group or deformation vibrations 130

**H**

Hampel estimator 156  
 Hausner ratio (HR) 153, 155  
 hearing aids 240  
 heat and UV radiation 184  
 heat capacity 118  
 heat capacity measurements 113  
 heating 58  
 heating rates 114  
 heat radiation 121  
 heat radiation effects 119  
 heat resistance 201  
 heat sources 29  
 holes 58  
 hollow spheres 142  
 humidity 34  
 hydrogen bonds 168, 194

**I**

image analysis  
 – dynamic 150  
 – static 150  
 impact strength 116, 194  
 incoming inspection 153

individualization 240  
 individual parts 66  
 industrial grippers  
 – individualized 241  
 industry  
 – aerospace 234  
 – automotive 234  
 – defense 234  
 – electronic 234  
 – furniture 234  
 – jewelry 234  
 – medical 234  
 – tool and mold making 234  
 infrared spectra 130  
 initiator 136  
 internal stress 121  
 IR emitters 30  
 ISO 17296-2 98  
 ISO 17296-3 100  
 ISO 27547-1 100  
 ISO/ASTM 52901 100  
 ISO/ASTM 52902 97  
 ISO/ASTM 52910 97  
 ISO/ASTM 52911-2 99  
 ISO/ASTM 52915 97  
 ISO/ASTM 52920 98  
 ISO/ASTM 52921 98  
 ISO/ASTM 52924 100  
 ISO/ASTM 52925 99  
 ISO/ASTM 52930 99  
 ISO/ASTM 52936-1 100  
 ISO/ASTM 52950 98  
 ISO TC 261 94  
 isothermal laser sintering 168  
 isotropy of the components 116

**K**

kinetic energy 138

**L**

Lambert–Beer law 130  
 lamella thickness (lc) 179

- laser beam
  - deflection speed of the 32
  - positioning 39
- laser diffraction 150
- laser energy
  - variation of the 221
  - input 31
- laser module 26
- laser power 32
- laser scan lines
  - visible 227
- laser scan spacing 32
- laser spot 40
- laser window 26
- lauro lactam 168, 180
- layer bonding 117
- layer boundaries 117, 183
- layer-by-layer construction 2
- layer delamination 70, 183
- layer times 58
- Le Chatelier's principle 105
- lifestyle and fashion 242
- lifestyle products 233
- lightweight structures 233
- liquid nitrogen 138
- living anionic polymerization 136
- long-term resistance 226
- LS
  - industrial equipment 41
  - material portfolio 20
  - process chain 19
- LS components
  - professional design 224
- LS machines
  - basic structure 25
- LS parameters 217
- LS parts 213
  - homogeneous 220
- LS process 23, 53, 74
  - capability 170
  - errors 70
  - simulation 118
  - stability 174
- LS process capability of powders 155

- LS technology
  - development history 23

## M

- machine configuration 25
- machine market 41
- machinery and tools 243
- machine technology 25
- manual work 230
- manufacturing technology 1
- market shares 166
- Massachusetts Institute of Technology 229
- material optimization through additives 224
- material selection 20
- matrix polymer 139
- maximum roughness (RZ) 228
- maximum tensile strength 215
- mean roughness (Ra) 228
- mechanical comminution 138
- mechanical properties 214
  - comparison of 216
- medicine/dentistry 242
- melt flowability 124
- melt flow indexing (MFI) method 124
- melt flow index (MFI) 55
- melting 117
- melting point 59, 107
- melt-spinning 141
- melt viscosity 68, 122
- melt volume rate (MVR) 55
- melt volume rate (MVR) method 124
- metal and non-metal oxides 130
- metal powders 169, 196
- metastable 113
- microscope with heating stage 128
- military 243
- moisture 197
- mold 3
- mold cooling 117
- molecular weight 106, 109, 126, 180, 182
  - average 110

- distribution 126
- number-average 126
- weight-average 126
- monoclinic (pseudohexagonal) symmetry 178
- morphology 106
- multi-zone heater 29
- MVR control points 55
- MVR measurements 125

## N

- name of the polyamides 168
- needle tip 228
- Newtonian fluid 122
- nitrogen 34
- non-contact optical measurement techniques 228
- numerical simulation 120
- nylon (polyamide) 163

## O

- oligomers 127
- onset 115
- optical components 39
- orange peel 68, 69
- organic chemical reactions 181
- Orgasol® Invent Smooth 136, 169
- original forming process 217
- oven aging 184
- overheating of individual layers 66
- overlap of the laser traces 63
- oxidation 28, 65
- oxidative degradation reactions 184

## P

- PA 12 base powders 169
- PA 12 powder
  - with carbon fiber 196
- PA 12 “virgin” powder 54
- packing density 54, 150
- parameter sets 63
- part collision 58

- part density 218
- part distortion 67
- part distribution
  - homogeneous 58
- part functionality 4
- part growth
  - uncontrolled 70
- partial melting 220
- partial pressure difference 181
- particle coalescence 129
- particle fines
  - proportion of 138
- particle geometry 146
- particle size distribution
  - homogeneous 172
- part list reduction 238
- part positioning
  - incorrect 66, 68
- part properties
  - homogeneity of the 220
  - isotropic 65
- parts assembly (build job) 57
- pendant-drop method 128
- penetration depth of the radiation 131
- plasticizer content 197
- plastic measuring cylinder 156
- plate–plate rheometers 122
- plate–plate viscometer 123
- polishing 232
- polyamide 11 (PA 11) 187
- polyamide 12 (PA 12) 169
- polyamide (nylon) 167
- polyamide PA 6 199
- polyaryletherketones (PAEKs) 205
- polycarbonate (PC) 109, 163
- polycondensation 105
- polydispersity index (PDI) 126
- polymer and laser sintering market in
  - comparison 166
- polymer chains
  - extension 182
  - with open chain ends 180
- polymerization 104
  - ionic 104
  - radical 104

- polymer powders 135
  - polymer properties 103
  - polymer pyramid 166
  - polymers
    - amorphous 106
    - elastomeric 103
    - hydrolysis-sensitive 125
    - schematic structure 104
    - semi-crystalline 106
    - thermoplastic 103
    - thermoset 103
  - polymethyl methacrylate (PMMA) 109
  - polymorphism 177
  - polyphosphinate 199
  - polyvinyl chloride (PVC) 163
  - pores 219
  - porosity
    - determination 219
    - non-destructive determination of the 219
    - residual 220
  - post-condensation 122, 180, 183
    - effects 184
    - of PA 12 in the solid state 180
    - reactions 180
  - powder
    - distribution curves of 150
    - exposure of the surface 64
    - highly porous 149
    - overflow 54
    - unprocessed 55
    - used 55
    - virgin 55
  - powder agglomeration 70
  - powder aging 184
  - powder application 34
  - powder bed
    - cracks 70
  - powder behavior 146
  - powder cake 65
  - powder circuit in the LS process 55
  - powder coatings 135
  - powder condition 55
    - correct control 55
  - powder density 38
  - powder distribution 152, 170
  - powder feed 34
  - powder flowability 35, 149, 153, 154
    - method overview 154
  - powder mixture 54
  - powder production 136, 139
  - powder shape 150
  - powder “short feed” 70
  - powder state 34, 155
  - powder supply 33
  - powder surrounding 119
  - precipitation of substances 137
  - precipitation process 137
  - preheating phase 54
  - primary processing 108
  - process chain 5, 54
  - process chamber 28
  - process control 120, 213
  - process error 66
  - process flow 59
  - processing temperature 107
  - process suitability of the powders 174
  - production process 4
  - production technology 53
  - product personalization 3
  - properties
    - extrinsic 112
    - for LS polymers 111
    - intrinsic 112
    - optical 129
    - thermal 112
    - viscoelastic 122
  - property combination of PA 12 185
  - property matrix of LS materials 226
  - prosthetics 4
  - prototype construction 235
  - prototyping 1
  - ProX™ 500 25
  - Push™ process 230
- Q**
- qualification
    - for industrial series production 71



**R**

recycling 185  
 reflectance 130  
 reflection 129  
 repeatability (sr) 156  
 repeating units 182  
 research & development facilities 48  
 residual monomer content 126  
 RESS process 143  
 rheology of the polymer melt 122  
 ring-opening polyaddition 169  
 robotic grippers 4  
 RoHS Directive 198  
 roll coaters 37  
 rotational speed 159  
 roughness  
 – determination 228  
 – parameters 229  
 roundness 146  
 round-robin test 156

**S**

sample construction 235  
 scan head  
 – mirror position of 63  
 scanning electron microscope (SEM) 142  
 scattering phenomena 129  
 Schleiss RPTech 56  
 secondary processing 108  
 secondary valence forces 168  
 sedimentation time 159  
 segments  
 – hard 103  
 – soft 103  
 serial parts 213  
 shear 109  
 shielding gas 58  
 short-term loading 215  
 sieve analysis 150  
 simulation  
 – of the degree of solidification 120  
 – thermal processes 121  
 sintered necks 108  
 sintering cycle 59  
 sintering window 113  
 – determination of the 113  
 – modeling of the processes 120  
 Sinterline™ 200  
 SinterStation 24  
 skin contact 233  
 snap functions 58  
 solid–liquid state 120  
 solution polymerization 136  
 solvents 230  
 spatial directions 223  
 spatial orientation 223  
 special materials 63  
 spectacle models 232  
 sphericity 136, 146, 148, 172  
 spherulite boundaries 116  
 spherulitic crystals 116  
 sports and racing applications 196  
 spray-drying 142  
 stabilizers 184  
 staircase effect 227  
 standard deviations 156  
 standardization 94  
 standardization bodies (ASTM, ISO, CEN) 94  
 standards committees 95  
 step-growth reaction 104  
 stereolithography 7  
 STL file 56  
 streaming 70  
 structural body 109  
 structural density 122  
 sublimation 199  
 super-cooled melt 122  
 support structures 57  
 surface  
 – contour of the 228  
 – defects 68  
 – heating 59  
 – large 58

- of the build area 62
- smooth 58
- surface-active additives 129
- surface-fractal 159
- surface quality 20
- surface roughness 148
- surface roughness of the LS components 172
- surface temperature 30, 31
- surface tension 109, 122, 127
- suspension polymerization 136

## T

- tacticity 106
- tactile/touching measurement 228
- tangential speed 37
- tapped density 156
- technology drivers 3
- temperature control 28, 29
- temperature jump in the laser trace 114
- tensile strength 116, 182
- tensile test 215
- thermal aging 226
- thermal behavior 107
- thermal conductivity 118
- thermal equilibrium 59
- thermal properties 172
- thermal radiation 118
- thermal shock 59
- thermal stress 185
- thermal transitions 108
- thermogravimetry (TGA) 197
  - measuring curve 197
- thermo-oxidative damage 138
- thermoplastic elastomers 158, 202
- thermoplastic elastomers (TPEs) 103
- time constant 32
- titanium dioxide (TiO<sub>2</sub>) 130
- tomography (CT) 142
- translation speed 37
- transmission 130, 131
- trowalizing 230

## U

- unit costs 4
- University of Austin 23, 163
- University of Sheffield 230

## V

- vapor phase 230
- varnishing 232
- VDI 3405 Blatt 1 100
- VDI 3405 Blatt 1.1 99
- VDI 3405 Blatt 6.2 99
- VDI 3405 Blatt 7 100
- VDI status report “Additive manufacturing processes” 234
- vehicles and mobility 242
- vibrations of the powder coater 227
- vibratory grinding 230
- viscosity 109
- viscosity curve 109, 122
- viscous behavior 122
- voids 146, 218
  - form factors of the 219

## W

- warpage 67
- wash-out 70
- wash-out effects 227
- water absorption 201
- waterproofing 231
- weld lines 42
- white pigment 130
- wide-angle X-ray scattering (WAXS) 178
- Windform® 196

## X

- X-Ray diffraction reflections (WAXS) 178
- X-ray structure analyses 178
- XYZ-direction 194

**Y**

- yellowing
  - of the parts 70
  - of the surfaces 65
- yield stress 116

**Z**

- zero-shear viscosity 109, 122
- zinc selenide (ZnSe) 26